

PERC Table 1
Viscaria Exploration Results, Q1 2026

MAY 2026



Table of Contents

PERC REPORTING STANDARD	1
Section 1 Project Outline	1
1.0. Introduction – General	1
1.0. Introduction – General	2
1.0. Introduction – General	3
1.1. Property Description.....	3
1.2. Location.....	4
1.3. Adjacent Properties	5
1.4. History	5
1.5. Legal Aspects and Permitting	6
1.6. Royalties.....	7
1.7. Liabilities	8
Section 2 Geological Setting, Deposit, Mineralisation	9
2.1. Geological Setting, Deposit Type and Mineralisation Style	9
Section 3 Exploration and Drilling, Sampling Techniques and Data	13
3.1. Exploration	13
3.2. Drilling Techniques	14
3.3. Sample Method, Collection, Capture, and Storage	15
3.4. Sample Preparation and Analysis	16
3.5. Sampling Governance	17
3.6. Quality Control/Quality Assurance	18
3.7. Bulk Density	18
3.8. Bulk-Sampling and/or Trial-mining	19
Section 4 Estimation and Reporting of Exploration Results, Mineral Resources and Mineral Reserves	20
4.1. Geological model and interpretation	20
4.2. Estimation and modelling techniques	21
4.3. Reasonable prospects for eventual economic extraction.....	22
4.4. Classification Criteria	22
4.5. Reporting.....	23
4.5. Reporting.....	24
Section 5 Technical Studies	25
5.1. Introduction	25
5.2. Mining Design.....	26
5.3. Metallurgical and Test work.....	28
5.4. Infrastructure.....	30
5.5. Environmental, Social Performance, and Governance.....	31
5.6. Market Studies and Economic Criteria	35

5.7.	Risk Analysis	39
5.8.	Economic Analysis	39
Section 6 Estimation and Reporting of Mineral Reserves		41
6.1.	Estimation and Modelling Techniques.....	41
6.2.	Classification Criteria	43
6.3.	Reporting.....	43
6.4.	Specific for Metal Equivalents or Combined Grades Reporting	45
Section 7 Audits and Reviews		46
7.1.	Audits and Reviews	46
Section 8 Other Relevant Information.....		47
8.1.	Other Relevant Information	47
Section 9 Qualification of Competent Person(s) and other key technical staff. Date and Signature Page.....		48
9.1.	Competent Person Details.....	48
APPENDIX 1: FIGURES		49
APPENDIX 2: ASSAY RESULTS		54
APPENDIX 2.1: Summary		54
APPENDIX 2.2: Full assay results.....		55
APPENDIX 3: REFERENCES.....		90
APPENDIX 4: CERTIFICATE OF COMPETENT PERSON		91

Table 1. PERC Reporting Standard

PERC REPORTING STANDARD

Section 1 Project Outline			
1.0. Introduction – General			Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves
(i)	<p>The terms of reference or scope of work.</p> <p>During Q1 2026 Table 1 preparation, the Company identified that drillhole 'VDD24115B' final assay results were incorporated into the Q1 2025 Mineral Resource Estimate but were not disclosed as standalone exploration results, having previously been reported as assays pending in Q4 2024. The material information was already disclosed through the published MRE.</p>		<p style="text-align: center;">Competent Person’s Report (CPR)</p> <ul style="list-style-type: none"> • Reporting of PERC (2021) compliant Exploration Results of the Viscaria deposit located in Kiruna, Sweden. • The Report has been prepared by Viscaria Kiruna AB (“VISCARIA”), formerly Copperstone Viscaria AB (“Copperstone”) to disclose the most recent results from the near mine exploration campaigns performed in 2026. The program has been performed close in accordance with the Pan European Reserves and Resources Reporting Committee (“PERC”) on the Viscaria Copper-Iron Project in Sweden. • This report covers assay results for two completed diamond drillholes and one on-going drillhole from the current drilling program: <ul style="list-style-type: none"> • VDD25013D: Completed; targeting the gap between B Zone and B Zone Deep • VDD24036: Completed; targeting down-dip extension of D Zone mineralization at depth • VDD25013E: On-going; southwest step-out (~770 m) from existing D Zone mineralisation intersected, assays pending. • During Q1 2026 Table 1 preparation, the Company identified that drillhole 'VDD24115B' final assay results were incorporated into the Q1 2025 Mineral Resource Estimate but were not disclosed as standalone exploration results, having previously been reported as assays pending in Q4 2024. The material information was already disclosed through the published MRE.

(Continued on next page)

1.0. Introduction – General			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	The terms of reference or scope of work.		<ul style="list-style-type: none"> For completeness, transparency, and full traceability of the data supporting Mineral Resource, the Company has decided to formally report the detailed exploration results for drillhole VDD24115B in this update. <u>This disclosure does not represent new material information</u> but provides supporting detail for data previously included in the published Mineral Resource Statement. The report is prepared by Gruvaktiebolaget Viscaria and evaluated by an independent Competent Person (CP): Mr. Thomas Lindholm.
(ii)	The Competent Person's relationship to the issuer of the report, if any.		<ul style="list-style-type: none"> The CP for the Exploration Results is Mr. Thomas Lindholm MSc FAusIMM, FAMMP, who is a senior associate of and Principal Consultant (Resource Geology) at GeoVista AB. He is a Fellow of the Australasian Institute of Mining and Metallurgy, a Recognised Professional Organisation ("RPO") within the meaning of PERC. Mr. Lindholm is a senior mining engineer and has long and extensive experience in exploration, mining and mineral resource estimation of iron ore, base and precious metals. The Competent Person is independent of the issuer.
(iii)	A statement for whom the report was prepared; whether it was intended as a full or partial evaluation or other purpose, work conducted, effective date of report, and remaining work.		<ul style="list-style-type: none"> This Technical Report has been prepared on behalf of the Company with effective date May 7, 2026.
(iv)	Sources of information and data contained in the report or used in its preparation, with citations if applicable, and a list of references.		See APPENDIX 2
(v)	A title page and a table of contents that includes figures and tables.		See Table of Contents
(vi)	<p>An Executive Summary, which briefly summarises important information in the public report, including property description and ownership, geology and mineralisation, the status of exploration, development and operations, Mineral Resource and Mineral Reserve estimates, and the Competent Person's conclusions and recommendations.</p> <p>If Inferred Mineral Resources are used, a summary valuation with and if practical without inclusion of such Inferred Mineral Resources. The Executive Summary should have sufficient detail to allow the reader to understand the essentials of the project.</p>		N/A

1.0. Introduction – General			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(vii)	A declaration from the Competent Person, stating whether “the declaration has been made in terms of the guidelines of the PERC Reporting Standard”.		See the certificate of the Competent Person in APPENDIX 3
(viii)	Diagrams, maps, plans, sections and illustrations, which are dated, legible and prepared at an appropriate scale to distinguish important features. Maps including a legend, author or information source, coordinate system and datum, a scale in bar or grid form, and an arrow indicating north. Reference to a location or index map and more detailed maps showing all important features described in the text, including all relevant cadastral and other infrastructure features.		See APPENDIX 1
(ix)	The units of measure, currency and relevant exchange rates.		<ul style="list-style-type: none"> The units of measure are in SI.
(x)	The details of the personal inspection on the property by each Competent Person or, if applicable, the reason why a personal inspection has not been completed.		<ul style="list-style-type: none"> The Competent Person has visited the site on several occasions, the most recent being in October 2025, and maintained frequent online communication with the Geology team up to the preparation of Table 1.
1.1. Property Description			Competent Person's Report (CPR)
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Brief description of the scope of project (i.e. whether in preliminary sampling, advanced exploration, scoping, pre-feasibility, or feasibility phase, Life of Mine plan for an ongoing mining operation or closure).		<ul style="list-style-type: none"> A Feasibility Study for the project was published in May 2025, with a planned mine opening in 2028.
(ii)	Describe (noting any conditions that may affect possible prospecting/mining activities) topography, elevation, drainage, fauna and flora, the means and ease of access to the property, the proximity of the property to a population center, and the nature of transport, the climate, known associated climatic risks and the length of the operating season and to the extent relevant to the mineral project, the sufficiency of surface rights for mining operations including the availability and sources of power, water, mining personnel, potential tailings storage areas, potential waste disposal areas, heap leach pad areas, and potential processing plant sites.		<ul style="list-style-type: none"> The location of the mine site, 150 km north of the Arctic Circle and 250 km east of the North Atlantic Sea, strongly affects the climate in the area. February had the lowest temperature down to average -21° C. The warmest month is July, when the temperature normally varies between 9,2° C and 17,6° C. Precipitation is greatest during the summer months with an average precipitation of 94 mm in July, followed by August with 68 mm. Snow and ice cover the landscape from October to May, with a snow depth average of 75 cm. Rapid melting during the spring results in a short and intensive spring flood normally lasting a few weeks in May and June. The average wind speed at Kiruna Airport measuring station is 3,5 m/s and the dominant wind direction is from the south to south-west. <i>(Continued on next page)</i>

1.1. Property Description				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(ii)	Describe (noting any conditions that may affect possible prospecting/mining activities) topography, elevation, drainage, fauna and flora, the means and ease of access to the property, the proximity of the property to a population center, and the nature of transport, the climate, known associated climatic risks and the length of the operating season and to the extent relevant to the mineral project, the sufficiency of surface rights for mining operations including the availability and sources of power, water, mining personnel, potential tailings storage areas, potential waste disposal areas, heap leach pad areas, and potential processing plant sites.			<ul style="list-style-type: none"> Mining in subarctic conditions means climatic risk to machinery and labour force, but 100 years of mining tradition in the area has developed modern technology and work methods that are very well adapted to the environmental conditions. Water supply and mine drainage systems must be adapted to arctic dry periods during winter and high flows during late spring and summer, to support process- and drilling water. (Viscaria Kiruna AB, 2025a) Viscaria Kiruna AB has built a new bridge and road to the area to support the establishment of the mine. The location of the mine near LKAB Kiirunavaara ensures that the local infrastructure and workforce are well adapted to underground mining.
(iii)	Specify the details of the personal inspection on the property by each CP or, if applicable, the reason why a personal inspection has not been completed.			<ul style="list-style-type: none"> The Competent Person has visited the site, inspected drill core and discussed the new discoveries with the geologists on several occasions, latest in October of 2025. Between site visits, online technical review sessions are conducted at intervals to monitor ongoing exploration activities and maintain continuity of technical oversight.
1.2. Location				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Describe (noting any conditions that may affect possible prospecting/mining activities) topography, elevation, drainage, fauna and flora, the means and ease of access to the property, the proximity of the property to a population center, and the nature of transport, the climate, known associated climatic risks and the length of the operating season and to the extent relevant to the mineral project, the sufficiency of surface rights for mining operations including the availability and sources of power, water, mining personnel, potential tailings storage areas, potential waste disposal areas, heap leach pad areas, and potential processing plant sites.			<ul style="list-style-type: none"> The A, B, D and ABBA zones of the Viscaria Copper Project (the Project) are located in Kiruna Municipality in Norrbotten County, the northernmost county in Sweden. The project lies approximately 5 km northwest of the town of Kiruna. The project is located 270 km north-northwest of the port city of Luleå, which lies on the Gulf of Bothnia in the northern Baltic Sea, and 130 km southeast of the port city of Narvik in northern Norway. (Viscaria Kiruna AB, 2025a) The coordinate system used in the Project is SWEREF 99 20 15.
(ii)	Country Profile: describe information pertaining to the project host country that is pertinent to the project, including relevant applicable legislation, environmental and social context etc. Assess, at a high level, relevant technical, environmental, social, economic, political and other key risks.			<ul style="list-style-type: none"> Information pertaining to the project host country, including applicable legislation, environmental and social context, and other relevant factors can be found in Viscaria Kiruna AB, 2025b.

1.2. Location				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(iii)	Provide a general topocadastral map	Provide a topo-cadastral map in sufficient detail to support the assessment of eventual economics. State the known associated climatic risks.	Provide a detailed topo-cadastral map. Confirm that applicable aerial surveys have been checked with ground controls and surveys, particularly in areas of rugged terrain, dense vegetation or high altitude.	See Figure 2
1.3. Adjacent Properties				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Discuss details of relevant adjacent properties	If adjacent or nearby properties have an important bearing on the report, then their location and common mineralized structures should be included on the maps. Reference all information used from other sources.		N/A
1.4. History				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	State historical background to the project and adjacent areas concerned, including known results of previous exploration and mining activities (type, amount, quantity and development work), previous ownership and changes thereto.			<ul style="list-style-type: none"> • There has been very limited mining in the B Zone and no mining in the D Zone. Hence there is no reconciliation information available for these zones. • In the A zone, 12,5 Mt at 2,3% copper was mined between 1982-1997. Experience from past mining operations improves the technical knowledge used to plan future mining. The old Viscaria mine was opened and initially operated by LKAB. The mine was later run by Outokumpu, before being closed in 1997 due to declining copper prices. • In the 2000s rising copper prices led to renewed interest in the property and exploration was undertaken by Avalon Minerals. • In 2019 the Project was acquired by Gruvaktiebolaget Viscaria (then Copperstone Resources AB). (Viscaria Kiruna AB, 2025a)

1.4. History				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(ii)	Present details of previous successes or failures with reasons why the project may now be considered potentially economic.			<ul style="list-style-type: none"> The previous mine closed due to declining copper prices. Copper prices are now much higher and projected to remain high.
(iii)		Discuss known or existing historical Mineral Resource estimates and performance statistics on actual production for past and current operations.		N/A
(iv)			Discuss known or existing historical Mineral Reserve estimates and performance statistics on actual production for past and current operations.	N/A
1.5. Legal Aspects and Permitting				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	A statement from the Competent Person on the confirmation of the legal tenure, including a description of (the following):			<ul style="list-style-type: none"> The Competent Person has verified the company's tenure in the publicly available database at the Inspector of Mines office.
(ii)	Discuss the nature of the issuer's rights (e.g. prospecting and/or mining) and the right to use the surface of the properties to which these rights relate. Disclose the date of expiry and other relevant details.			<ul style="list-style-type: none"> Viscaria Kiruna AB has three granted exploitation concessions under the Minerals Act (SFS1991: 45); Viscaria K no 3 and K no 4 which were granted by Bergsstaten (Mining Inspectorate) in January 2012, both expiring 2037, and Viscaria K no 7 which was granted in March 2018, expiring 2043. The exploration results presented are from drilling within or directly adjacent to these concessions. If mining, development for mining or other significant work to continue extraction are on-going at the time of expiry, the concessions will automatically be extended for a 10-year period.

(Continued on next page)

1.5. Legal Aspects and Permitting			Back to Table of Contents	
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(ii)	Discuss the nature of the issuer's rights (e.g. prospecting and/or mining) and the right to use the surface of the properties to which these rights relate. Disclose the date of expiry and other relevant details.			<ul style="list-style-type: none"> The area around the deposit has a detailed plan for mining operations and is designated as an area of national interest for deposits of valuable minerals or materials that are of great importance for the country's supply readiness. (Viscaria Kiruna AB, 2025b) Viscaria Kiruna AB also has 11 exploration licenses surrounding the exploitation concessions. Details for all concessions and licenses can be found at https://www.viscaria.com/en/
(iii)	Present the principal terms and conditions of all existing agreements, and details of those still to be obtained, (such as, but not limited to, concessions, partnerships, joint ventures, access rights, leases, historical and cultural sites, wilderness or national park and environmental settings, royalties, consents, permission, permits or authorisations).			See the company's tenures at http://www.viscaria.com/en/
(iv)	Present the security of the tenure held at the time of reporting or that is reasonably expected to be granted in the future along with any known impediments to obtaining the right to operate in the area. State details of applications that have been made. See Clause 8.1 for declaration of a Mineral Reserve.			See the company's tenures at http://www.viscaria.com/en/
(v)	Provide a statement of any legal proceedings for example, land claims, that may have an influence on the rights to prospect or mine for minerals, or an appropriate negative statement.			See the company's tenures at http://www.viscaria.com/en/
(vi)	Provide a statement relating to governmental/statutory requirements and permits as may be required, have been applied for, approved or can be reasonably be expected to be obtained. Provide a review of risks that permits will not be received as expected and impact of delays to the project.			<ul style="list-style-type: none"> The final environmental permit for mining was approved in April 2025. All public information on the permitting process can be found on the company webpage http://www.viscaria.com/en/
1.6. Royalties				Competent Person's Report (CPR)
	Exploration Results	Mineral Resources	Mineral Reserves	
(i)	Describe the royalties that are payable in respect of each property.			<ul style="list-style-type: none"> Pursuant to Swedish law, a mineral royalty of 0.2% of the value of ROM is payable. This comprises 0.05% to the state and 0.15% to landowners (private landowners own a small part of property inside the land lease). The royalty cost is estimated to be around US\$ 500,000 per annum (net cost).

(Continued on next page)

1.6. Royalties			Back to Table of Contents	
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Describe the royalties that are payable in respect of each property.			<ul style="list-style-type: none"> VISCARIA is a party to two of so-called Net Smelter Return ("NSR") royalty agreements, entered in February 2008 in connection with Copperstone Viscaria's (with a different governance regime and under another company name) acquisition the Viscaria asset. The agreements entails a certain industry specific royalty obligation, originally for the benefit of two different previous owners of this mine asset, of which the larger royalty right of 1.0 % has been transferred to EMX Corp ("EMX"), that inter alia, administer NSR-rights professionally, while the smaller royalty right of 0.5 %, although capped at MUSD 12, has been transferred to Outokumpu Oyj ("Outokumpu"), parent company to the Swedish subsidiary that managed and subsequently closed the previous mine. The payment of the smaller royalty is deductible from the larger royalty, meaning that the royalty obligation shall not exceed 1.0 % of the net sales revenue. VISCARIA and Laevas Sami village have entered a cooperation agreement to enhance both mining operations and reindeer husbandry in the Viscaria area. As part of the agreement, the parties have agreed on compensation to be paid for the impact of the mining operations on the reindeer husbandry.
1.7. Liabilities				Competent Person's Report (CPR)
	Exploration Results	Mineral Resources	Mineral Reserves	
(i)	Describe any liabilities, including rehabilitation guarantees that are pertinent to the project. Provide a description of the rehabilitation liability, including, but not limited to, legislative requirements, assumptions and limitations.			<ul style="list-style-type: none"> The mine area will have to be rehabilitated when operations cease. As a security a bond of 344 MSEK will be deposited with the Norrbotten County Administrative Board. In the first phase a 60.6 MSEK bond was deposited in order to guarantee rehabilitation of the initial mine drainage and the water treatment plant.

Section 2 Geological Setting, Deposit, Mineralisation

2.1. Geological Setting, Deposit Type and Mineralisation Style

[Back to Table of Contents](#)

	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Describe the regional geology.			<ul style="list-style-type: none"> • The Viscaria Cu project is located in the center of the Kiruna mining district, which consists of a Paleoproterozoic (2.5 – 1.8 Ga) supracrustal sequence, including clastic sedimentary rocks together with basic and intermediate to acid felsic volcanic rocks. • The Paleoproterozoic Karelian Suite was formed during a continental rifting event between 2.5 Ga and 2.0 Ga, and consists of metamorphosed volcanic, volcano-sedimentary, and sedimentary rocks. In the Kiruna area, the lowermost unit of the Karelian Suite is the Kovo Group, which is comprised of quartzite and meta-conglomerate, overlain by the Kiruna Greenstone Group. • The Kiruna Greenstone Group is the host group of the Viscaria and Pahtohavare deposits. It consists of a 2 to 4 km thick sequence of submarine and subaerial basalts, andesites, volcanoclastic rocks, turbidites and chemical sedimentary rocks, which were formed between 2.2 Ga and 2.0 Ga. Several of the sedimentary formations can be easily traced along 10 km length on the Kiruna district. The whole sequence is affected by extensional tectonics and igneous sill emplacements. • Around 2.0 Ga, there was a shift from extensional to compressional tectonics, marked by the onset of the Svecokarelian orogeny (1.96 Ga to 1.75 Ga). The Kurravaara Conglomerate Formation unconformably overlies the Kiruna Greenstone Group. • The Svecofennian Suite is a supracrustal sequence represented by arc-related volcanic and sedimentary rocks that include the Porphyrite Group, the Porphyry Group, and the Hauki Quartzite, arranged from oldest to youngest, respectively. The volcanic rocks of the Porphyry Group host economically important IOA's, such as the Kiirunavaara and the Per Geijer deposits.
(ii)	Describe the project geology including mineral deposit type, geological setting and style of mineralisation.			<ul style="list-style-type: none"> • The Kiruna Greenstone Group was deposited on a continental rift setting and exhibits an evolution from within-plate to mid-ocean-ridge-type volcanism. The group has been divided into six formations based on petrographic and geochemical criteria. <p align="right"><i>(Continued on next page)</i></p>

2.1. Geological Setting, Deposit Type and Mineralisation Style			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(ii)	Describe the project geology including mineral deposit type, geological setting and style of mineralisation.		<p>The bottom of the group is dominated by basaltic lavas, dolerite and locally conglomerates (Såkevaratjah Formation). This is subsequently overlain by peridotitic to basaltic komatiites of the Ädnamvare Formation, followed by the subaqueous-subaerial tholeiitic basalts of the Pikse Formation.</p> <ul style="list-style-type: none"> • The district spans around 150 km by 20 km, hosting Kiruna-type Iron Oxide Apatite (IOA) deposits, including Kiirunavaara - the world's largest underground iron ore mine, Malmberget, Gruvberget, Tuolluvaara, and the Per Geijer deposits. • The Viscaria Formation, the host formation of the Viscaria Cu-Fe orebodies, is composed of a steeply SE-dipping, NE-SW-striking sequence of volcanoclastic, chemical and organic sedimentary rocks. Overlying the Viscaria Formation is the Peuravaara Formation, composed of basaltic pillow lavas. The whole sequence has been metamorphosed in upper greenschist to lower amphibolite facies. The hydrothermal alteration spans over 20 km², and includes district-wide sodic alteration, followed by widespread Fe-K-Ca±Mg metasomatism, marked by biotite, K-feldspar, amphibole, and magnetite alterations. • The Viscaria deposit is situated within the now inverted former rift basin of the crust within the northern Norrbotten area. E-W late-orogenic crustal shortening formed major regional folds and penetrative regional steeply dipping N-S foliation. This N-S structural pattern controls inflections, steps and terminations in the Viscaria Formation. The complex evolution resulted in a SE-dipping, NE-SW-striking stratigraphy younging to the east. • At Viscaria, the rheological heterogeneity of the rock units has led to strain partitioning, resulting in localized bedding-parallel shear/fault zones close to major rheological contacts and intraformational folding with meter scale parasitic folds normally observed within mechanically weaker rocks; marble, talc schists and graphite schists. • The rocks show steep to locally overturned dips close to the surface while the dips become gentler towards the depth. <p style="text-align: right;"><i>(Continued on next page)</i></p>

2.1. Geological Setting, Deposit Type and Mineralisation Style			Back to Table of Contents	
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(ii)	Describe the project geology including mineral deposit type, geological setting and style of mineralisation.			<ul style="list-style-type: none"> The stratigraphy is overprinted by steeply dipping reverse faults with west side up kinematics and intraformational folds moderately plunging to the S and SW. Viscaria is a copper sulfide deposit with chalcopyrite as the main copper mineral. In the D Zone, Cu sulfides are linked to the replacement of pyrite along magnetite grain margins. Rare replacement of bornite in chalcopyrite also occurs. In the A and B Zones, Cu sulfides are paragenetically associated with pyrrhotite and pyrite which replace magnetite.
(iii)	Discuss the geological model or concepts being applied in the investigation and on the basis of which the exploration program is planned. Describe the inferences made from this model.			<ul style="list-style-type: none"> The geological model at Viscaria comprises stratabound mineralized zones. An exploration campaign commenced in mid-2024 to test the strike and depth extensions of these known mineralized zones beyond the established Mineral Resources. Results from that 2024 exploration program were incorporated into the feasibility study and resource update published in May 2025 (available at http://www.viscaria.com/en/). The drillholes reported here were planned based on the outcomes of the 2024 and early 2025 exploration results and are designed to further delineate the extent and continuity of mineralization identified during that phase.
(iv)	Discuss data density, distribution and reliability and whether the quality and quantity of information are sufficient to support statements, made or inferred, concerning the project.			<ul style="list-style-type: none"> Results published here consist of 2 assayed diamond drillholes, all in close proximity to existing declared resources. The purpose is to further investigate the extension of the B and D Zone at depth.

2.1. Geological Setting, Deposit Type and Mineralisation Style			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(v)	Discuss the significant minerals present in the deposit, their frequency, size and other characteristics. These include minor and gangue minerals where these will have an effect on the processing steps. Indicate the variability of each important mineral within the mineral deposit.		<ul style="list-style-type: none"> Mineralogy of the Viscaria Deposit is described in Table 1 for Mineral Resource Update May 2025 (Viscaria Kiruna AB, 2025b). Other recent articles regarding mineral characterization can be found in Imana et al., 2023 and Tasbicen et al., 2023.
(vi)	Describe the significant mineralised zones encountered on the property, including a summary of the surrounding rock types, relevant geological controls, and the length, width, depth, and continuity of the mineralisation, together with a description of the type, character, and distribution of the mineralisation		<ul style="list-style-type: none"> The property hosts four principal mineralised zones: A, B, ABBA, and D. The drillhole under review intersected the B Zone, which is hosted predominantly in biotite-altered calcsilicate units. The B Zone mineralisation is characterized by copper sulphide dissemination and veining, commonly occurring in bed-parallel and cross-cutting orientations, consistent with previously logged observations in the area (Viscaria Kiruna AB, 2025a, 2025b). In contrast, the A Zone exhibits similar structural controls but contains a carbonaceous graphitic ore type, while the D Zone is hosted within a thick carbonate unit (>15 m) showing magnetite-chalcopyrite replacement along both margins, with localized talc and amphibole associated with lower Cu grades. D Zone has elevated Fe oxide content (22–26% of Fe hosted in magnetite) with chalcopyrite and pyrite replacing magnetite grain boundaries, and peripheral areas containing sparse pyrite replacement and a low-Cu specular hematite zone near the tectonic footwall of the marble unit. Both A and B Zone orebodies are generally harder and more competent than the carbonate- and magnetite-rich D Zone. ABBA Zone is positioned between the A and B Zones, in the southwestern portion of the deposit, and consists of high-grade copper mineralisation with a lower grade envelope, hosted within volcano-sedimentary rocks.

Section 3 Exploration and Drilling, Sampling Techniques and Data

3.1. Exploration			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Describe the data acquisition or exploration techniques and the nature, level of detail, and confidence in the geological data used (i.e. geological observations, remote sensing results, stratigraphy, lithology, structure, alteration, mineralisation, hydrology, geophysical, geochemical, petrography, mineralogy, geochronology, bulk density, potential deleterious or contaminating substances, geotechnical and rock characteristics, moisture content, bulk samples etc.). Confirm that data sets include all relevant metadata, such as unique sample number, sample mass, collection date, spatial location etc.		<ul style="list-style-type: none"> The geological data for the project have been acquired through standard exploration techniques, including detailed core logging of lithology, structure, alteration, and mineralisation, as well as field observations of host rock characteristics. Core samples have been collected systematically, with unique sample numbers, collection dates, sample mass, and spatial location recorded for each. Additional geological data such as bulk density, geotechnical and rock characteristics, and moisture content have been noted where relevant. Sample preparation and assaying have been performed at ALS Geochemistry laboratories in Piteå. Details of the assay process are listed in Section 3.3.
(ii)	Identify and comment on the primary data elements (observation and measurements) used for the project and describe the management and verification of these data or the database. This should describe the following relevant processes: acquisition (capture or transfer), validation, integration, control, storage, retrieval and backup processes. It is assumed that data are stored digitally but hand-printed tables with well-organized data and information may also constitute a database.		<ul style="list-style-type: none"> A custom SQL database from M-Solutions Oy is used, called M-IDIS® Industry Data Integration System. The database downloads assay results directly from the laboratory ALS's (see Section 3.4.(i)) cloud-based database Webtrieve. Database is backed up daily.
(iii)	Acknowledge and appraise data from other parties and reference all data and information used from other sources.		See APPENDIX 2 for references.
(iv)	Clearly distinguish between data / information from the property under discussion and that derived from surrounding properties		N/A
(v)	Describe the survey methods, techniques and expected accuracy of data, including the methods for downhole surveying of drillholes. Specify the grid system used.		<ul style="list-style-type: none"> A gyroscope sensor (SPT GyroMaster) is used for downhole surveying. Surveys are completed by trained drilling contractors and requested by Viscaria geologists. The grid system used is SWEREF 99 20 15.

3.1. Exploration			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(vi)	Discuss whether the data spacing and distribution is sufficient to establish the degree of geological and grade continuity appropriate for the estimation procedure(s) and classifications applied.		<ul style="list-style-type: none"> Drillhole spacing supports promising geological interpretations of the B Zone and D Zone.
(vii)	Present representative models and / or maps and cross sections or other two- or three-dimensional illustrations of results, showing location of samples, accurate drill-hole collar positions, down-hole surveys, exploration pits, underground workings, relevant geological data, etc.		<ul style="list-style-type: none"> See APPENDIX 1 for figures
(viii)	Report the relationships between mineralisation widths and intercept lengths are particularly important, the geometry of the mineralisation with respect to the drill hole angle. If it is not known and only the down-hole lengths are reported, confirm it with a clear statement to this effect (e.g. down-hole length, true width not known').		<ul style="list-style-type: none"> Down-hole lengths are given only, rather than true width calculations. Drill holes are nominally planned to intersect the target mineralization with a perpendicular angle. Directional drilling has been utilized also to ensure adequate intersection angles (i.e., to avoid drilling along mineralization, rather than through it).
3.2. Drilling Techniques			Competent Person's Report (CPR)
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Present the type of drilling undertaken (e.g. core, reverse circulation, open-hole hammer, rotary air blast, auger, Banka, sonic, etc.) and details (e.g. core diameter, triple or standard tube, depth of diamond tails, face-sampling bit or other type, whether core is oriented and if so, by what method, etc.).		<ul style="list-style-type: none"> All drilling undertaken is standard tube diamond drilling. Cores are NQ2 size (50 mm diameter, measured with calipers regularly during logging). Directional drilling has been used to ensure drilling hits the planned targets. Directional drilling core has a diameter of 40.7 mm. All core, excluding sections where directional drilling is done, is oriented by the drillers where possible.
(ii)	Describe whether core and chip samples have been geologically and geotechnically logged to a level of detail to support appropriate Mineral Resource estimation, technical studies, mining studies and metallurgical studies.		N/A
(iii)	Describe whether logging is qualitative or quantitative in nature; indicate if core photography. (or costean, channel, etc.) was undertaken		<ul style="list-style-type: none"> Logging is qualitative. All cores are photographed dry and wet.
(iv)	Present the total length and percentage of the relevant intersections logged.		<ul style="list-style-type: none"> Geological and geotechnical logging has been completed for 2543 meters of drillcore (VDD24036, VDD25013D, VDD24115B). Of these, 2229 meters have undergone geochemical sampling. See Appendix 2 for full sample lists and weighted average grades for significant intercepts. VDD25013E results will be reported when received and validated.

3.2. Drilling Techniques			Back to Table of Contents	
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(v)	Discuss the results of any downhole surveys of the drill holes.			<ul style="list-style-type: none"> • Deviation surveys are regularly carried out during drilling and at the end of hole to monitor the drilling trajectory. • BHEM surveys are also routinely conducted as part of the exploration program. Results were used to plan further drilling.
3.3. Sample Method, Collection, Capture, and Storage				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Describe the nature and quality of sampling (e.g. cut channels, random chips, or specific specialised industry standard measurement tools appropriate to the minerals under investigation, such as down hole gamma sondes, or handheld XRF instruments, etc.). These examples should not be taken as limiting the broad meaning of sampling.			<ul style="list-style-type: none"> • Drillhole cut channels are used. Handheld XRF instruments were occasionally used to assist in preliminary estimation of Cu content or to identify minerals.
(ii)	Describe the sampling processes, including sub-sampling stages to maximize representivity of samples. This should include whether sample sizes are appropriate to the grain size of the material being sampled. Indicate whether sample compositing has been applied.			<ul style="list-style-type: none"> • For sampling process, see Section 3.4.(iii) • Sample compositing has not been applied.
(iii)	Appropriately describe each data set (e.g. geology, grade, density, quality, diamond breakage, geo-metallurgical characteristics etc.), sample type, sample-size selection and collection methods			<ul style="list-style-type: none"> • For grade samples, see Section 3.4.(iii) • For density samples, see Sections 3.7.(i) and 3.7.(iv)
(iv)	Report the geometry of the mineralisation with respect to the drill-hole angle. State whether the orientation of sampling achieves unbiased sampling of possible structures and the extent to which this is known, considering the Mineral deposit type. State if the intersection angle is not known and only the downhole lengths are reported.			<ul style="list-style-type: none"> • Drillhole is designed to intersect with a perpendicular angle and usually southeast-dipping mineralization. Where drillcore is oblique to mineralisation orientation, cutting line was used to ensure a more representative sample.
(v)	Describe retention policy and storage of physical samples (e.g. core, sample reject, etc.)			<ul style="list-style-type: none"> • All core (sampled and non-sampled) will be placed in a storage tent. Pulps and rejects will be returned from lab and will be stored in library at the Core Shed.
(vi)	Describe the method of recording and assessing core and chip sample recoveries and results assessed, measures taken to maximise sample recovery and ensure representative nature of the samples and whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material.			<ul style="list-style-type: none"> • Total Core Recovery (TCR) and Rock Quality Designation (RQD) are measured for all cores. Drillers report core loss measured after every run. Drillers reports are compared to TCR. Where core loss (according to TCR) exceeds 0.3 m sample intervals are not extended across the incomplete section.

(Continued on next page)

3.3. Sample Method, Collection, Capture, and Storage			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(vi)	Describe the method of recording and assessing core and chip sample recoveries and results assessed, measures taken to maximise sample recovery and ensure representative nature of the samples and whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material.		<ul style="list-style-type: none"> Where core cannot be assayed, results are diluted with 0 grade material in grade calculations. As such, where grade is reported across an interval with core loss, Cu and Fe content is underestimated. Core loss in the reported intersections is minimal.
(vii)	If a drill-core sample is taken, state whether it was split or sawn and whether quarter, half or full core was submitted for analysis. If a non-core sample, state whether the sample was riffled, tube sampled, rotary split etc. and whether it was sampled wet or dry. The impact of water table or flow rates on recovery and introduction of sampling biases or contamination from above. Discuss the impact of variable hole diameters, e.g., by the use of a caliper tool.		<ul style="list-style-type: none"> Core is sawn and half core is analyzed. Hole diameter is very consistent.
(viii)	If a drill-core sample is taken, sufficient information should be supplied to assess the effects of core loss. Occasionally, only total core recovery is mentioned but at the same time the mineralized parts are designated as poor quality. This type of reporting is against the main principles of Transparency and Materiality. Heavy core losses throughout an ore body intersection can seriously undermine the confidence in a resource estimate. It is important to determine whether a relationship exists between grade and recovery (either positive or negative) to assess the potential for grade bias. In addition, it is important to state the method used to determine the core recovery: Total Core Recovery (TCR), Solid Core Recovery (SCR) and Rock Quality Designation (RQD).		<ul style="list-style-type: none"> Core recovery is determined using TCR. TCR and RQD are collected for the full drillhole. Average recovery of the three logged drillholes was 97%. Average RQD was 89%. For handling of core loss, see Section 3.3.(vi).
3.4. Sample Preparation and Analysis			Competent Person's Report (CPR)
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Identify the laboratory(s) and state the accreditation status and Registration Number of the laboratory or provide a statement that the laboratories are not accredited. Record the steps taken by the Competent Person to ensure the results from a non-accredited laboratory are of an acceptable quality.		<ul style="list-style-type: none"> Sample preparation and assaying were performed at ALS Geochemistry laboratories in Piteå, Sweden and Loughrea, Ireland, respectively.

3.4. Sample Preparation and Analysis			Back to Table of Contents	
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(ii)	Identify the analytical method. Discuss the nature, quality and appropriateness of the assaying and laboratory processes and procedures used and whether the technique is considered partial or total.			<ul style="list-style-type: none"> • Multielement method ME-MS61 has been utilized. It is considered appropriate for the mineralisation at Viscaria.
(iii)	Describe the process and method used for sample preparation, sub-sampling and size reduction, and the likelihood of inadequate or non-representative samples (i.e. improper size reduction, contamination, screen sizes, granulometry, mass balance, etc.)			<ul style="list-style-type: none"> • Sample interval boundaries are marked by geologists. Cores are then transported via courier to ALS, Piteå using Chain of Custody procedure. Diamond drill core is sawn longitudinally and split in half for sampling. Sample preparation procedures are appropriate, with ALS preparing samples by crushing to <2 mm, splitting using a riffle splitter, the pulverizing to achieve a 250 g sample mass that is sub-sampled for analysis. Sample sizes have varied according to the length of core sample taken as determined by geological logging. Sample lengths are appropriate for the intersected mineralization and minimum core diameters are greater than the maximum mineralisation crystal size. Pulverizing of crush materials is acceptable under the quality standard by ALS. ALS ships the sampled half-core, pulp and reject material via courier to Viscaria Kiruna AB, where pulps are stored in a dry and heated library and the half-core and rejects are stored in cold facilities for later use and/or review. (Viscaria AB, 2025b)
3.5. Sampling Governance				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Discuss the governance of the sampling campaign and process, to ensure quality and representivity of samples and data, such as sample recovery, high grading, selective losses or contamination, core/hole diameter, internal and external QA/QC, and any other factors that may have resulted in or identified sample bias.			<ul style="list-style-type: none"> • The sampling campaign has been conducted under standard site procedures to ensure representivity and data integrity. Core recovery was monitored throughout drilling, and no significant loss or high grading was observed during logging. Core diameter and condition were recorded to maintain consistency in sampling. • Internal QA/QC measures, including duplicate sampling and systematic logging, have been applied. External QA/QC protocols will be implemented once samples are submitted for assay. QA/QC validation is not yet complete for drillholes with assays pending. However, the procedures followed provide confidence that the collected geological data accurately represent the mineralisation style and host lithologies.

3.5. Sampling Governance			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(ii)	Describe the measures taken to ensure sample security and the Chain of Custody.		<ul style="list-style-type: none"> Measures described by Viscaria Kiruna AB, 2025a and 2025b.
(iii)	Describe the validation procedures used to ensure the integrity of the data, e.g. transcription, input or other errors, between its initial collection and its future use for modelling (e.g. geology, grade, density, etc.)		<ul style="list-style-type: none"> Geological data collected from the drillholes have been validated through systematic core logging and field checks to ensure accuracy and completeness. Unique sample numbers, collection dates, spatial locations, and sample masses have been recorded to maintain traceability. Data entry into databases is conducted following standard procedures, with checks to minimize transcription or input errors. Assay results are pending, and once received, they will undergo standard QA/QC validation, including verification against duplicates, standards, and blanks, to ensure integrity prior to use in modelling for geology, grade, or density.
(iv)	Describe the audit process and frequency (including dates of these audits) and disclose any material risks identified.		<ul style="list-style-type: none"> Regular internal audits are performed by the Viscaria geology team.
3.6. Quality Control/Quality Assurance			
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Demonstrate that adequate field sampling process verification techniques (QA/QC) have been applied, e.g. the level of duplicates, blanks, reference material standards, process audits, analysis, etc. If indirect methods of measurement were used (e.g. geophysical methods), these should be described, with attention given to the confidence of interpretation. Refer to measures taken to ensure sample representivity and the appropriate calibration of any measurement tools or systems used. QA/QC procedures used to check databases augmented with 'new' data have not resulted in corruption of previous versions containing stored 'old' data.		<ul style="list-style-type: none"> Duplicates (crush and field), blanks and standards are inserted into sample program at a frequency of minimum 1 duplicate/blank/standards per 10 samples.
(ii)	Document the use of any independent check laboratory (umpire check samples). Identify the independent laboratory and details of its accreditation.		<ul style="list-style-type: none"> No umpire check has been used for the results reported here.
3.7. Bulk Density			
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Describe the method of bulk density determination with reference to the frequency of measurements, the size, nature and representativeness of the samples.		<ul style="list-style-type: none"> Density measurements are made on whole core, with buoyancy method, before core is sent to the lab. <p style="text-align: right;"><i>(Continued on next page)</i></p>

3.7. Bulk Density			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Describe the method of bulk density determination with reference to the frequency of measurements, the size, nature and representativeness of the samples.		<ul style="list-style-type: none"> Density measurements are focused in sampled intervals, with representative samples in non-sampled intervals. Measured core pieces were between 10 and 30 cm. Measured bulk density ranges from 2.81 to 3.24 g/cm³ (P10–P90), with a median of 3.01 g/cm³. The full dataset ranges from 2.58 to 4.83 g/cm³, with values outside the P10–P90 range representing localized zones of high-grade massive sulphide mineralization (upper outliers) or weathered/ fractured/ porous intervals (lower outliers).
(ii)	If target tonnage ranges are reported state the preliminary estimates or basis of assumptions made for bulk density.		
(iii)	Discuss the representivity of bulk density samples of the material for which a grade range is reported.		N/A
(iv)	Discuss the adequacy of the methods of bulk density determination for bulk material with special reference to accounting for void spaces (vugs, porosity etc.), moisture and differences between rock and alteration zones within the mineral deposit.		<ul style="list-style-type: none"> Porous and/or clay-rich rock are avoided as the measurement method is not accurate for these rocks. Very low density measurements (≤ 2.6 g/cm³) are likely due to porosity not visible to the technician.
3.8. Bulk-Sampling and/or Trial-mining			
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Indicate the location of individual samples (including map).		N/A
(ii)	Describe the size of samples, spacing/density of samples recovered and whether sample sizes and distribution are appropriate to the grain size of the material being sampled.		N/A
(iii)	Describe the method of mining and treatment.		N/A
(iv)	Indicate the degree to which the samples are representative of the various types and styles of mineralisation and the mineral deposit as a whole.		N/A

Section 4 Estimation and Reporting of Exploration Results, Mineral Resources and Mineral Reserves

4.1. Geological model and interpretation			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Describe the geological model, construction technique and assumptions that form the basis for the Exploration Results or Mineral Resource estimate. Discuss the sufficiency of data density to assure continuity of mineralisation and geology and provide an adequate basis for the estimation and classification procedures applied.		<ul style="list-style-type: none"> Resource models are published in 2025, See http://www.viscaria.com/en/ No estimation or classification is reported here.
(ii)	Describe the nature, detail and reliability of geological information with which lithological, structural, mineralogical, alteration or other geological, geotechnical and geo-metallurgical characteristics were recorded.		<ul style="list-style-type: none"> Geological logging is qualitative, performed by Viscaria geologists as well as skilled contractors. Details of data collection are described in Section 3: Exploration and Drilling, Sampling Techniques and Data.
(iii)	Describe any obvious geological, mining, metallurgical, environmental, social, infrastructural, legal and economic factors that could have a significant effect on the prospects of any possible exploration target or mineral deposit.		<ul style="list-style-type: none"> The report covers near-mine exploration, inside or directly adjacent to existing exploitation concessions. There are no factors specific to these findings.
(iv)		Discuss all known geological data that could materially influence the estimated quantity and quality of the Mineral Resource.	N/A
(v)		Discuss whether consideration was given to alternative interpretations or models and their possible effect (or potential risk) if any, on the Mineral Resource estimate.	N/A
(vi)		Discuss geological discounts (e.g. magnitude, per reef, domain, etc.), applied in the model, whether applied to mineralized and / or un-mineralized material (e.g. potholes, faults, dykes, etc.).	N/A

4.2. Estimation and modelling techniques				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Describe in detail the estimation techniques and assumptions used to determine the grade and tonnage ranges for any Exploration Targets, if reported in a Public Report.			N/A
(ii)		Discuss the nature and appropriateness of the estimation technique(s) applied and key assumptions, including treatment of extreme grade values (cutting or capping), compositing (including by length and/or density), domaining, sample spacing, estimation unit size (block size), selective mining units, interpolation parameters and maximum distance of extrapolation from data points.		N/A
(iii)		Describe assumptions and justification of correlations made between variables.		N/A
(iv)		Provide details of any relevant specialized computer program (software) used, with the version number, together with the estimation parameters used.		N/A
(v)		State the processes of checking and validation, the comparison of model information to sample data and use of reconciliation data, and whether the Mineral Resource estimate takes account of such information.		N/A
(vi)		Describe the assumptions made regarding the estimation of any co-products, by-products or deleterious elements.		N/A

4.3. Reasonable prospects for eventual economic extraction				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)		Disclose and discuss the geological parameters. These would include (but not be limited to) volume / tonnage, grade and value / quality estimates, cut-off grades, strip ratios, upper- and lower- screen sizes.		N/A
(ii)		Disclose and discuss the engineering parameters. These would include mining methods, dilution, processing, geotechnical, geohydraulic and metallurgical) parameters.		N/A
(iii)		Disclose and discuss the infrastructural including, but not limited to, power, water, site-access.		N/A
(iv)		Disclose and discuss the legal, governmental, permitting, statutory parameters.		N/A
(v)		Disclose and discuss the environmental and social (or community) parameters.		N/A
(vi)		Disclose and discuss the marketing parameters.		N/A
(vii)		Disclose and discuss the economic assumptions and parameters. These factors will include, but not limited to, commodity prices and potential capital and operating costs		N/A
(viii)		Discuss any material risks		N/A
(ix)		Discuss the parameters used to support the concept of "eventual"		N/A
4.4. Classification Criteria				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)		Describe criteria and methods used as the basis for the classification of the Mineral Resources into varying confidence categories.		N/A

4.5. Reporting			Back to Table of Contents	
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Discuss the reported low and high-grades and widths together with their spatial location to avoid misleading the reporting of Exploration Results, Mineral Resources or Mineral Reserves.			<ul style="list-style-type: none"> Only exploration results are reported.
(ii)	Discuss whether the reported grades in Exploration Targets are regional averages or if they are selected individual samples taken from the property under discussion.			<ul style="list-style-type: none"> No exploration targets are reported.
(iii)	State assumptions regarding mining methods, infrastructure, metallurgy, environmental and social parameters. State and discuss where no mining related assumptions have been made.			<ul style="list-style-type: none"> No mining-related assumptions are made in the report.

4.5. Reporting				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(iv)	State the specific quantities and grades / qualities which are being reported in ranges and/or widths, and explain the basis of the reporting			See Appendix 2
(v)		Present the details for example open pit, underground, residue stockpile, remnants, tailings, and existing pillars or other sources in the Mineral Resource statement		N/A
(vi)		Present a reconciliation with any previous Mineral Resource estimates. Where appropriate, report and comment on any historical trends (e.g. global bias).		N/A
(vii)		Present the defined reference point for the tonnages and grades reported as Mineral Resources. State the reference point if the point is where the run of mine material is delivered to the processing plant. It is important that, in all situations where the reference point is different, such as for a saleable product, a clarifying statement is included to ensure that the reader is fully informed as to what is being reported.		N/A
(viii)	If the CP is relying on a report, opinion, or statement of another expert who is not a CP, disclose the date, title, and author of the report, opinion, or statement, the qualifications of the other expert and why it is reasonable for the CP to rely on the other expert, any significant risks and any steps the CP took to verify the information provided.			N/A
(ix)	State the basis of equivalent metal formulae, if applied.			N/A

Section 5 Technical Studies

5.1. Introduction				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Not applicable to Exploration Results	State the level of study – whether Scoping, Pre-Feasibility, Feasibility or ongoing Life of Mine	State the level of study – whether Pre-feasibility, Feasibility or ongoing Life of Mine. The Standard requires that a study to at least a Pre-Feasibility level has been undertaken to convert Mineral Resource to Mineral Reserve. Such studies will have been carried out and will include a mine plan or production schedule that is technically achievable and economically viable, and that all Modifying Factors have been considered.	N/A
(ii)	Not applicable to Exploration Results		Provide a summary table of the Modifying Factors used to convert the Mineral Resource to Mineral Reserve for Pre-feasibility, Feasibility or on-going Life-of-Mine studies.	N/A

5.2. Mining Design				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	not applicable to Exploration Results	State assumptions regarding mining methods and parameters when estimating Mineral Resources or explain where no mining assumptions have been made.		N/A
(ii)	not applicable to Exploration Results	Discuss Modifying factors taken into account in estimation of Mineral Resources	State and justify all modifying factors and assumptions made regarding mining methods, minimum mining dimensions (or pit shell) and internal and, if applicable, external) mining dilution and mining losses used for the techno-economic study and signed-off, such as mining method, mine design criteria, infrastructure, capacities, production schedule, mining efficiencies, grade control, geotechnical and hydrological considerations, closure plans, and personnel requirements.	N/A

5.2. Mining Design				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(iii)	not applicable to Exploration Results	State what mineral resource models have been used in the study.		N/A
(iv)	not applicable to Exploration Results	State what mineral resource models have been used in the study.		N/A
(v)	not applicable to Exploration Results		Description and justification of mining method(s) to be used.	N/A
(vi)	not applicable to Exploration Results		For open-pit mines, include a discussion of pit slopes, slope stability, and strip ratio.	N/A
(vii)	not applicable to Exploration Results		For underground mines, discuss mining method, geotechnical considerations, mine design characteristics, and ventilation/cooling requirements.	N/A
(viii)	not applicable to Exploration Results		Discuss mining rate, equipment selected, grade control methods, geotechnical and hydrogeological considerations, health and safety of the workforce, staffing requirements, dilution, and recovery.	N/A

5.2. Mining Design				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(ix)	not applicable to Exploration Results		State the optimisation methods and any software used in planning, list of constraints (practicality, plant, access, exposed Mineral Reserves, stripped Mineral Reserves, bottlenecks, draw control).	N/A
5.3. Metallurgical and Test work				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	not applicable to Exploration Results	Discuss the source of the sample, the representivity of the potential feed and the techniques used to obtain the samples, laboratory and metallurgical testing techniques.		N/A
(ii)	not applicable to Exploration Results	Explain the basis for assumptions or predictions regarding metallurgical amenability and any preliminary mineralogical test work already carried out.		N/A
(iii)	not applicable to Exploration Results	Discuss the possible processing methods and any processing factors that could have a material effect on the reasonable expectations of eventual economic extraction. Discuss the appropriateness of the processing methods to the style of mineralisation.	Describe and justify the processing method(s) to be used, equipment, plant capacity, efficiencies, and personnel requirements.	N/A

5.3. Metallurgical and Test work				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(iv)	not applicable to Exploration Results		Discuss the nature, amount and representativeness of metallurgical test work undertaken and the recovery factors used. A detailed flow sheet / diagram and a mass balance should exist ,especially for multi-product operations from which the saleable materials are priced for different chemical and physical characteristics.	N/A
(v)	not applicable to Exploration Results		State what assumptions or allowances have been made for deleterious elements and the existence of any bulk-sample or pilot-scale test work and the degree to which such samples are representative of the ore body as a whole.	N/A

5.3. Metallurgical and Test work				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(vi)	not applicable to Exploration Results		State whether the metallurgical process is well-tested technology or novel in nature. If novel, justify its use in Mineral Reserve estimation.	N/A
5.4. Infrastructure				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	not applicable to Exploration Results	Comment regarding the current state of infrastructure or the ease with which the infrastructure can be provided or accessed		N/A
(ii)	not applicable to Exploration Results		Report in sufficient detail to demonstrate that the necessary facilities have been allowed for (which may include, but not be limited to, processing plant, tailings dam, leaching facilities, waste dumps, road, rail or port facilities, water and power supply, offices, housing, security, resource sterilisation testing etc.). Provide detailed maps showing locations of facilities.	N/A

5.4. Infrastructure				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(iii)			Statement showing that all necessary logistics have been considered.	N/A
5.5. Environmental, Social Performance, and Governance				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)		<p>General:</p> <ul style="list-style-type: none"> - Confirm that the company or reporting entity has addressed the host country environmental legal compliance requirements and any mandatory and/or voluntary standards or guidelines to which it subscribes - Identify the necessary permits that will be required and their status and where not yet obtained, confirm that there is a reasonable basis to believe that all permits required for the project will be obtained - Identify and discuss any sensitive areas that may affect the project as well as any other environmental factors including Interested and Affected Parties (I&AP) and/or studies that could have a material effect on the likelihood of eventual economic extraction. Discuss possible means of mitigation. - Identify any legislated social management programmes that may be required and discuss the content and status of these. - Outline and quantify the material socio-economic and cultural impacts that need to be mitigated, and their mitigation measures and where appropriate the associated costs. 		N/A

5.5. Environmental, Social Performance, and Governance			Back to Table of Contents	
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)	
<p>(ii) Context: The project context is determined and described, including the following aspects:</p> <ul style="list-style-type: none"> • The locality's physical geography, centers of population, economic and cultural characteristics; • Existing land and natural resource use for economic, cultural, recreational and conservation purposes (inclusive of environmental and cultural sites of interest); • Existing or historical industrial development and associated infrastructure including mining and quarrying in the region; and • Local governance structures and administrative bodies, their roles and responsibilities in relation to permitting and regulations. • Site access routes and any potential impact on environment or local communities • Provision of energy for activities (e.g. off-grid renewable energy, or sourced direct from local non-renewable power grid with plans for decarbonisation for future project if possible) 			<p>See Section 1 Project Outline and Section 2 Geological Setting, Deposit, Mineralisation for descriptions of locality.</p> <p>The Tillståndsportal (Permit Portal) available on the website for information on permitting, regulations and existing land use. See the company's webpage https://www.viscaria.com/sv/tillstandsportal/</p>	
<p>(iii)</p> <ul style="list-style-type: none"> • High level assessment of level of water stress (e.g. potential for drought, flood and impact on water quality) • High level assessment of biodiversity (e.g. endangered species known in area) 			<p>• Associated Environmental and seasonal constraint/ control/consent measures/modifying factors described</p> <p>• Identification of potential climate associated risks and impacts</p> <p>• Social economic and cultural constraint /control/consent measures/ modifying factors described</p> <p>• Any sensitive areas that may affect the project as well as any other environmental factors including I&AP and/or studies that could have a material effect on the likelihood of eventual economic extraction.</p> <p>• Management of project waste and anticipated requirements for large scale infrastructure for mine waste for future, including but not limited to waste dumps and tailings dams.</p>	<p>See the company's application for an environmental permit, found in Tillståndsportal at https://www.viscaria.com/sv/tillstandsportal/</p>

5.5. Environmental, Social Performance, and Governance			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(iv)	Permits and permission: Identification of the necessary permits that will be required and their status, and where not yet obtained, and confirmation that there is a reasonable basis to believe that all permits required for the project will be obtained in a timely manner. Also include any records of penalties / fines or revoked permits complete with rationale.		All public documents relating to the permitting process can be found in Tillståndsportal at https://www.viscaria.com/sv/tillstandsportal/
(v)	Liabilities: Describe any known rehabilitation activities, liability and / or compliance costs	<ul style="list-style-type: none"> • Describe the best cost estimate for closure inclusive of environmental, social material remaining liability and compliance costs. • Provide a description of mechanisms in place to address unplanned closure • If appropriate, describe bonding obligations in place to ensure that these liabilities can be funded on a qualitative and quantitative basis. 	All public documents relating to the permitting process can be found in Tillståndsportal at https://www.viscaria.com/sv/tillstandsportal/
(vi)	Description of stakeholder group characteristics Records of Community and Stakeholder relationships: Records kept of all engagements with all stakeholders from the outset of the project; A grievance and/or complaints procedure established, stakeholders' issues, concerns recorded and tracked until resolved.		All public documents relating to the permitting process can be found in Tillståndsportal at https://www.viscaria.com/sv/tillstandsportal/
(vii)		A data management system implemented to record and track engagements; Provisions made for vulnerable and or underrepresented stakeholder groups Presence, or not of Indigenous People, if FPIC triggered, how is this managed	N/A
(viii)	Health and safety protocols and procedures required for exploration target definition inclusive of evidence of adherence to them and ongoing health and safety record.	Health and safety procedures and protocols, including community safety and security, across the exploration program inclusive of evidence of adherence to them and ongoing health and safety record	<ul style="list-style-type: none"> • Viscaria Kiruna AB has health and safety protocols and uses the GRIA reporting system for systematic safety work. The company has standard contracts quality assured by lawyers, as well as associated basic requirements and a supplier handbook to meet requirements regarding corruption, bribery and other irregularities, as well as to ensure "good suppliers" at Viscaria.

5.5. Environmental, Social Performance, and Governance			Back to Table of Contents	
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(ix)	Opportunities for contributing to the local economy identified and utilized where appropriate.	Legislated and or voluntary social development programs that may be required and content and status of these.		All public documents relating to the permitting process can be found in Tillståndsportal at https://www.viscaria.com/sv/tillstandsportal/
(x)		Material socio-economic and cultural impacts that need to be managed, and where appropriate the associated costs.		N/A
(xi)	Description of corporate governance board structure: gender, nationality, tenure, roles, responsibilities and process for selection of Board members, and Board remuneration processes and procedures			<ul style="list-style-type: none"> Gruvaktiebolaget Viscaria is a listed company on Nasdaq and follows the requirements and policies of the stock exchange. The company has been awarded by AllBrights Green List (gender equality in leadership). See http://www.viscaria.com/en/
(xii)	<ul style="list-style-type: none"> Commitment to GIIP: transparency, diversity, commitment to ESG described Corporate commitment to social performance described/ provided Corporate commitment to environmental stewardship described / provided 	<ul style="list-style-type: none"> Description of how corporate compliance is assured and verified Demonstrable commitment to GIIP: transparency, diversity, commitment to ESG described Demonstrable commitment to social performance described Demonstrable commitment to environmental stewardship described 		All public documents relating to the permitting process can be found in Tillståndsportal at https://www.viscaria.com/sv/tillstandsportal/

5.5. Environmental, Social Performance, and Governance				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(xiii)	Integrated Risk Management: Description of identified potential modifying factors and management actions taken to manage them where appropriate	<ul style="list-style-type: none"> • Description of proposed mitigation plans for identified modifying factors and management actions taken to manage them where appropriate. • Description of any additional risks that may impact on the long term future of the project, even if not deemed to be material at the current time. • Description of how the risk assessment process outlined here is integrated with the overall risk management framework for the company as a whole. 		<p>All public documents relating to the permitting process can be found in Tillståndsportal at https://www.viscaria.com/sv/tillstandsportal/</p>
5.6. Market Studies and Economic Criteria				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	not applicable to Exploration Results	Discuss any technical and economic factors likely to influence the prospect of economic extraction.	Describe the valuable and potentially valuable product(s) including suitability of products, co-products and by products to market.	N/A

5.6. Market Studies and Economic Criteria				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(ii)	not applicable to Exploration Results	Discuss any technical and economic factors likely to influence the prospect of economic extraction.	Describe product to be sold, customer specifications, testing, and acceptance requirements. Discuss whether there exists a ready market for the product and whether contracts for the sale of the product are in place or expected to be readily obtained. Present price and volume forecasts and the basis for the forecast.	N/A
(iii)	not applicable to Exploration Results	Discuss any technical and economic factors likely to influence the prospect of economic extraction.	State and describe all economic criteria that have been used for the study such as capital and operating costs, exchange rates, revenue / price curves, royalties, cut-off grades, reserve pay limits.	N/A

5.6. Market Studies and Economic Criteria				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(iv)	not applicable to Exploration Results	Discuss any technical and economic factors likely to influence the prospect of economic extraction.	Summary description, source and confidence of method used to estimate the commodity price/value profiles used for cut-off grade calculation, economic analysis and project valuation, including applicable taxes, inflation indices, discount rate and exchange rates.	N/A
(v)	not applicable to Exploration Results	Discuss any technical and economic factors likely to influence the prospect of economic extraction.	Present the details of the point of reference for the tonnages and grades reported as Mineral Reserves (e.g. material delivered to the processing facility or saleable product(s)). It is important that, in any situation where the reference point is different, a clarifying statement is included to ensure that the reader is fully informed as to what is being reported.	N/A

5.6. Market Studies and Economic Criteria				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(vi)			Justify assumptions made concerning production cost including transportation, treatment, penalties, exchange rates, marketing and other costs. Provide details of allowances that are made for the content of deleterious elements and the cost of penalties.	N/A
(vii)			Provide details of allowances made for royalties payable, both to Government and private.	N/A
(viii)			State ownership, type, extent and condition of plant and equipment that is significant to the existing operation(s).	N/A
(ix)			Provide details of all environmental, social and labour costs considered	N/A

5.7. Risk Analysis				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	A high-level assessment should be made of key areas of uncertainty which may affect exploration outcomes. An assessment should be provided on the chances of exploration success, together with consideration of any potential threats, such as ESG aspects, which could hinder eventual development of a mining or extraction project in the exploration area.”	Report an assessment of technical, environmental, social, economic, political and other key risks to the project. Describe actions that will be taken to mitigate and/or manage the identified risks.		<ul style="list-style-type: none"> • This report concerns near-mine exploration, within or directly adjacent to existing exploitation concessions. The main risk is the lack of sufficient data to declare exploration targets and mineral resources. • The increasing depth of the deposit introduces risks related to mining operations at deep levels. These include higher mining costs as well as effects on in situ stress on the rock mass, higher temperature and water pressure. The exploration results fall within the current analysis for the mining operation, due to their spatial proximity to declared mineral resources.
5.8. Economic Analysis				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	not applicable to Exploration Results	Describe the basis on which reasonable prospects for eventual economic extraction have been determined, including any material assumptions made in determining the 'reasonable prospects for eventual economic extraction'.	State and justify the inclusion of any Inferred Resources in the Pre-feasibility and Feasibility Studies economic analysis. Report the sensitivity to the inclusion of any Inferred Resources.	N/A

5.8. Economic Analysis			Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves
	Competent Person's Report (CPR)		
(ii)	not applicable to Exploration Results	At the relevant level (Scoping Study, Pre-feasibility, Feasibility or on-going Life-of Mine), provide an economic analysis for the project that includes:	
			N/A
(iii)	not applicable to Exploration Results	Cash Flow forecast on an annual basis using Mineral Reserves or an annual production schedule for the life of the project	
			N/A
(iv)	not applicable to Exploration Results	A discussion of net present value (NPV), internal rate of return (IRR) and payback period of capital	
			N/A
(v)	not applicable to Exploration Results	Sensitivity or other analysis using variants in commodity price, grade, capital and operating costs, or other significant parameters, as appropriate and discuss the impact of the results.	
			N/A

Section 6 Estimation and Reporting of Mineral Reserves

6.1. Estimation and Modelling Techniques				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	not applicable to Exploration Results	Describe the Mineral Resource estimate used as a basis for the conversion to a Mineral Reserve.		N/A
(ii)	not applicable to Exploration Results	Report the Mineral Reserve Statement with sufficient detail indicating if the mining is open pit or underground plus the source and type of mineralisation, domain or ore body, surface dumps, stockpiles and all other sources.		N/A
(iii)	not applicable to Exploration Results		If Inferred resources are used in assessing Mineral reserves, then report and discuss a comparison between the two possibilities, the one with inclusion of Inferred Mineral Resources and the one without inclusion, in such a way so as not to mislead the investors. Identify the quantity of the Inferred Mineral Resources included and the sensitivity of the inclusion to the study.	N/A

6.1. Estimation and Modelling Techniques				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(iv)	not applicable to Exploration Results		A Mineral Reserve Statement in sufficient detail indicating if the mining is open pit or underground plus the source and type of mineralisation , domain or ore body, surface dumps, stockpiles and all other sources.	N/A
(v)	not applicable to Exploration Results		Provide a reconciliation reporting historic reliability of the performance parameters, assumptions and modifying factors including a comparison with the previous Reserve quantity and qualities, if available. Where appropriate, report and comment on any historic trends (e.g. global bias)	N/A

6.2. Classification Criteria				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)			Describe and justify criteria and methods used as the basis for the classification of the Mineral Reserves into varying confidence categories, based on the Mineral Resource category, and including consideration of the confidence in all the modifying factors.	N/A
6.3. Reporting				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)			Discuss the proportion of Probable Mineral Reserves, which have been derived from Measured Mineral Resources (if any), including the reason(s) therefore.	N/A
(ii)			Present details of for example open pit, underground, residue stockpile, remnants, tailings, and existing pillars or other sources in respect of the Mineral Reserve statement	N/A

6.3. Reporting				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(iii)			Present the details of the defined reference point for the Mineral Reserves. State where the reference point is the point where the run of mine material is delivered to the processing plant. It is important that, in all situations where the reference point is different, such as for a saleable product, a clarifying statement is included to ensure that the reader is fully informed as to what is being reported. State clearly whether the tonnages and grades reported for Mineral Reserves are in respect of material delivered to the plant or after recovery.	N/A
(iv)			Present a reconciliation with the previous Mineral Reserve estimates. Where appropriate, report and comment on any historic trends (e.g. global bias).	N/A

6.3. Reporting				Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(v)			Confirm that only Measured and Indicated Mineral Resources can be considered for inclusion in the Mineral Reserve.	N/A
(vi)		State whether the Measured Mineral Resources and Indicated Mineral Resources are inclusive of or additional to the Mineral Reserves.		N/A
6.4. Specific for Metal Equivalents or Combined Grades Reporting				
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Confirm that all reports comply with section 9 (paragraphs 9.1 to 9.5) of the PERC Reporting Standard.			N/A
(ii)		Discuss and describe the basis for the grade estimation for each metal relating to the metal equivalence or combined grade		N/A
(iii)		Disclose all economic criteria that have been used for the calculation such as exchange rates, revenue / price curves, royalties, cut-off grades, pay limits.		N/A
(iv)		Discuss the basis for assumptions or predictions regarding metallurgical factors such as recovery used in the metal equivalents or combined grades calculation.		N/A
(v)		Show the calculation formula used.		N/A

Section 7 Audits and Reviews

7.1. Audits and Reviews			Back to Table of Contents
Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	State type of review/audit (e.g. independent, external), area (e.g. laboratory, drilling, data, environmental compliance etc.), date and name of the reviewer(s) together with their recognized professional qualifications. State the level of review/audit (desk-top, on-site comparison with standard procedures, or endorsement where auditor/reviewer has checked the work to the extent they stand behind it as if it were their own work).		<ul style="list-style-type: none"> • Exploration results reported here have been subject to peer audits as described in Section 3.5.(iii).
(ii)	Disclose the conclusions of relevant audits or reviews. Note where significant deficiencies and remedial actions are required.		N/A

Section 8 Other Relevant Information

8.1. Other Relevant Information			Back to Table of Contents	
	Exploration Results	Mineral Resources	Mineral Reserves	Competent Person's Report (CPR)
(i)	Discuss all other relevant and material information not discussed elsewhere.			N/A

Section 9 Qualification of Competent Person(s) and other key technical staff. Date and Signature Page

9.1. Competent Person Details			Back to Table of Contents
	Exploration Results	Mineral Resources	Mineral Reserves
			Competent Person's Report (CPR)
(i)	State the full name, registration number and name of the professional body or RPO, for all the Competent Person(s). State the relevant experience of the Competent Person(s) and other key technical staff who prepared and are responsible for the Public Report.		<ul style="list-style-type: none"> • Thomas Lindholm is a member of the Fennoscandian Association of Metals and Mining Professionals, FAMMP as well as a Fellow of AusIMM (#230476). • He graduated with a M.Sc. in mining engineering from the Luleå University of Technology in 1982 and has since worked in exploration and mine development projects in Sweden and abroad.
(ii)	State the Competent Person's relationship to the issuer of the report.		<ul style="list-style-type: none"> • The Competent Person is independent of the company.
(iii)	Provide the Certificate of the Competent Person, including the date of sign-off and the effective date, in the Public Report.		See Competent Person's Certificate

APPENDIX 1: FIGURES

Table of Figures

Figure 1 Geological map of Norrbotten	50
Figure 2 Map of Viscaria's tenures	51
Figure 3 Plan view of mineralized zone and DH traces – with DH names.	52
Figure 4 Section view of mineralized zone and DH traces – with DH names. Facing NE.	53

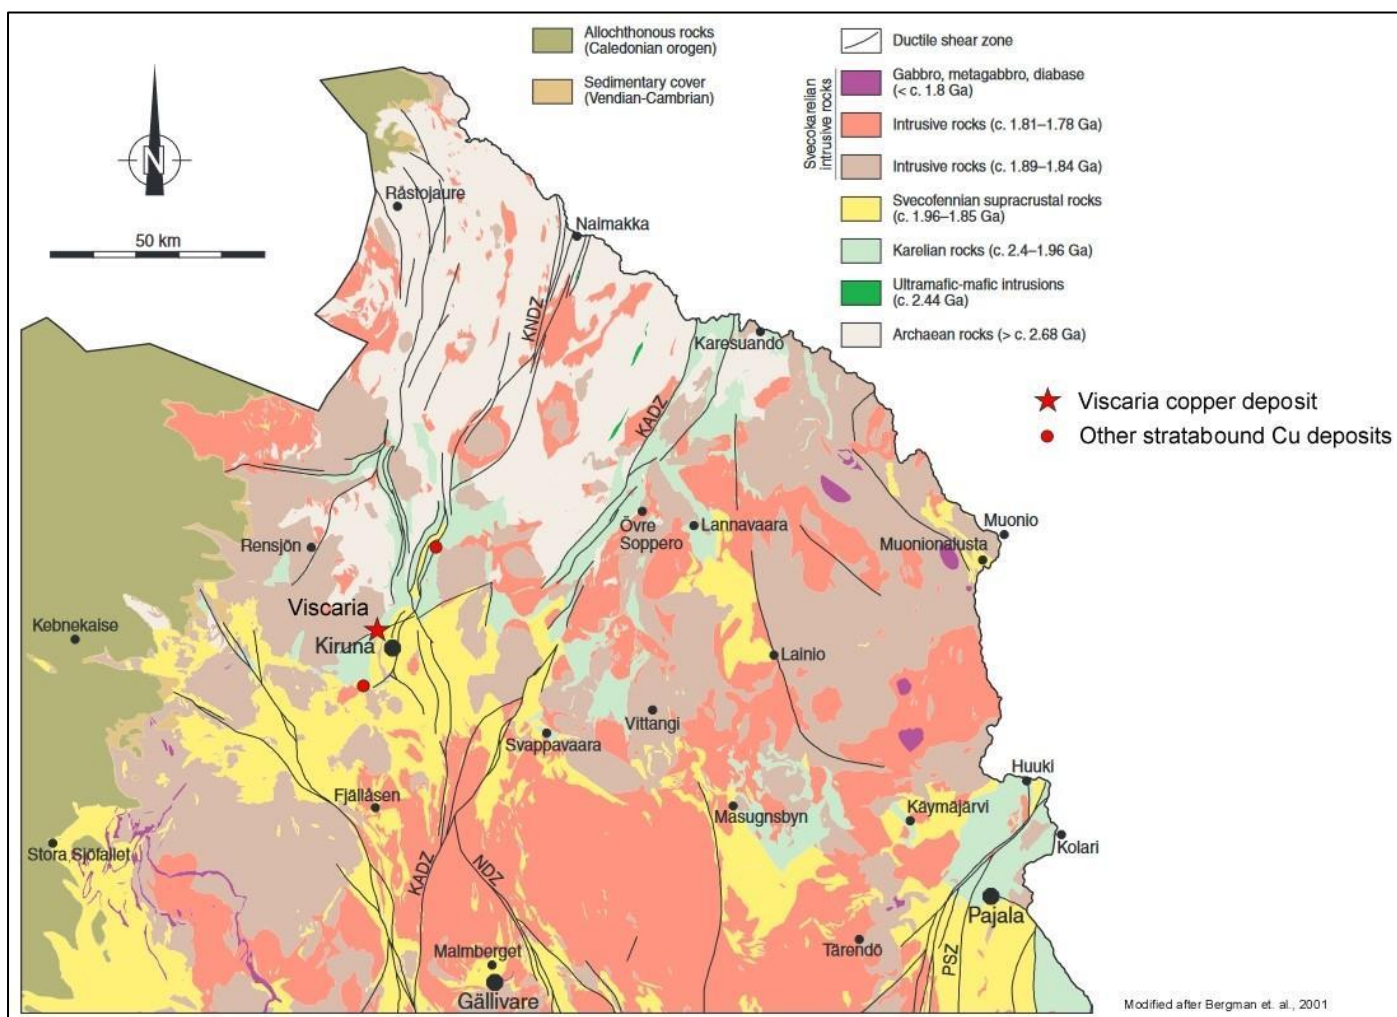


Figure 1 Geological map of Norrbotten

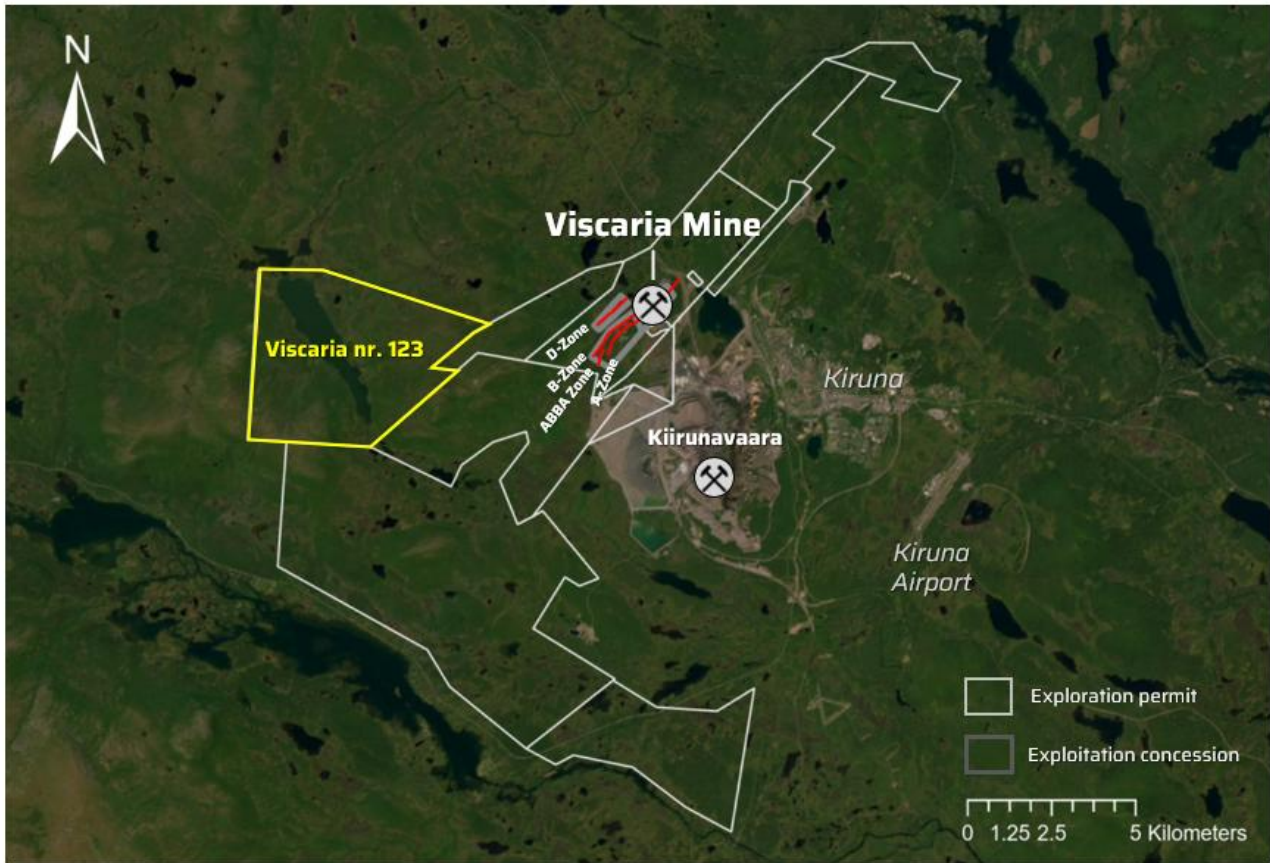


Figure 2 Map of Viscaria's tenures

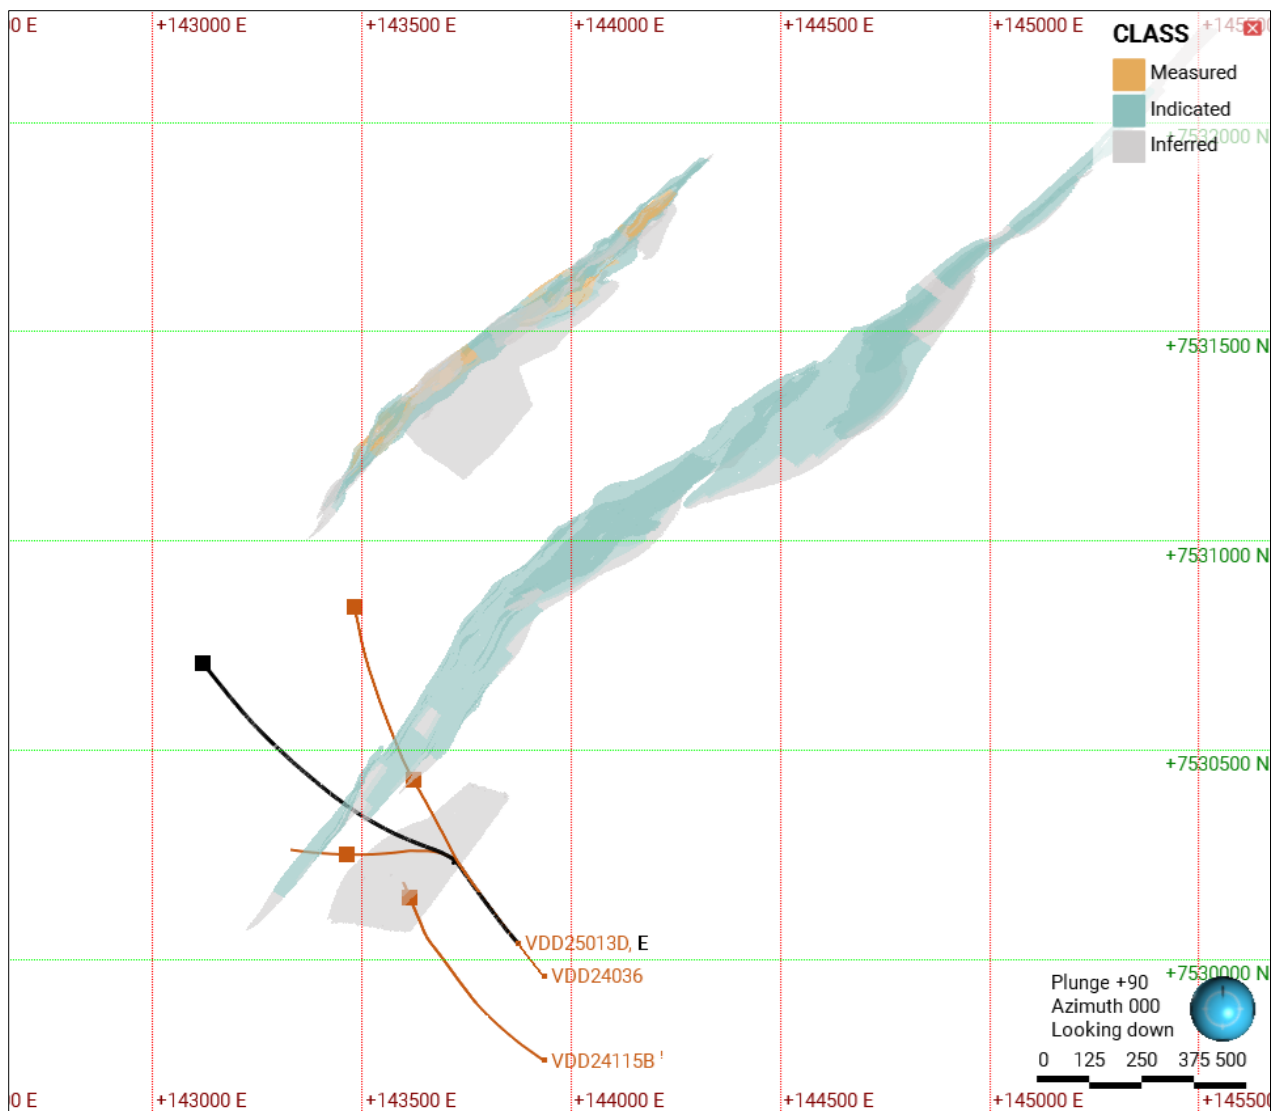


Figure 3 Plan view of mineralized zone and DH traces – with DH names.

VDD24115B¹

During preparation of the Q1 2026 Table 1, the Company identified that while final assay results for drillhole 'VDD24115B' were validated and incorporated into the Mineral Resource Estimate reported in the Company's [Interim Report Q1 2025](#) (released May 8, 2025 in accordance with the PERC Reporting Standard), the detailed exploration results for this drillhole had not been presented as a standalone exploration result disclosure, noting that the drillhole had previously been reported as ongoing drillhole and assay pending in the [Year-end Report Q4 2024](#) (See Figure 4). The Company has assessed that the material information associated with drillhole 'VDD24115B' was already disclosed to the market through its inclusion in the published Mineral Resource Estimate, which incorporated this data into the resource model for the B Zone Deep.

For completeness, transparency, and full traceability of the data supporting Mineral Resource, the Company has decided to formally report the detailed exploration results for drillhole VDD24115B in this update. This disclosure does not represent new material information but provides supporting detail for data previously included in the published [Mineral Resource Statement](#).

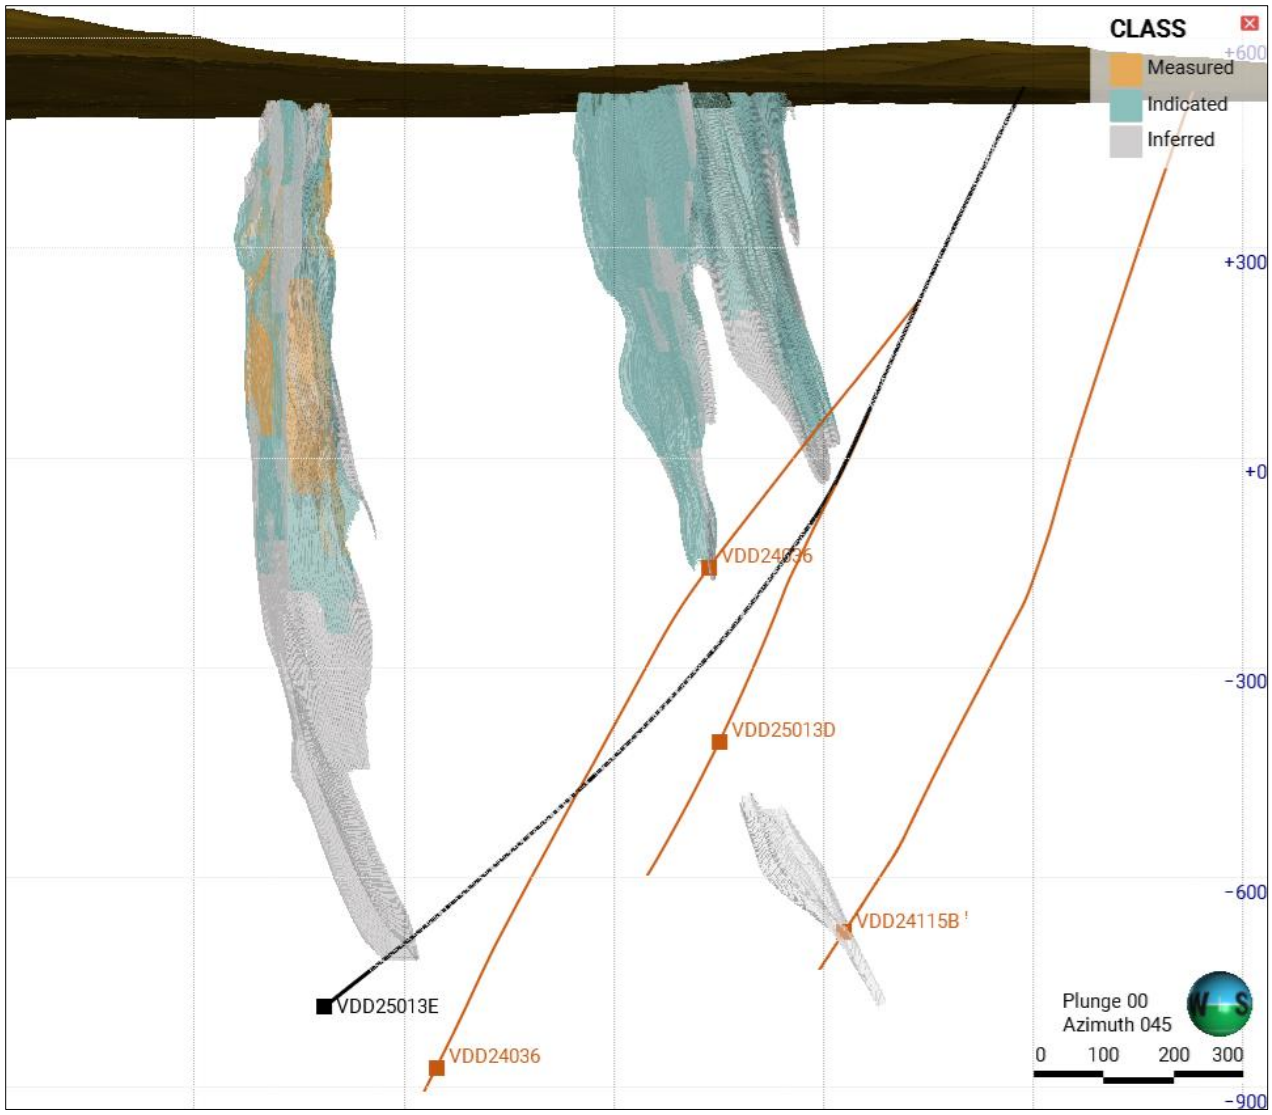


Figure 4 Section view of mineralized zone and DH traces – with DH names. Facing NE.

APPENDIX 2: ASSAY RESULTS

APPENDIX 2.1: Summary

Table 1: Collar table

Zone	Hole ID	X	Y	Z	Depth (m)	Core size
B and D	VDD24036	143934.5	7529959.15	536.3	1775.5	NQ
B	VDD25013D	143873	7530039	540.3	1673.2	NQ
B	VDD24115B ¹	143934.96	7529758.47	537.76	1392	NQ

Table 2: Selected intersections

- Ore grades are weighted by density and length with the formula:

$$\frac{\sum(\text{length} \times \text{grade} \times \text{density})}{\sum(\text{length} \times \text{density})}$$
- Density measurements are focused in sampled intervals, with representative samples in non-sampled intervals. In mineralised and ore zone samples, density measurements were made on every sample interval. Measured core pieces were between 3 and 30 cm. Measured bulk density ranged from 2.58 to 4.83 g/cm³.

Zone	Hole ID	From	To	Total length (m)	Cu%	Fe%
-	VDD24036	1377.5	1393	15.5	1.15	4.04
D	VDD24036	1718.9	1757.08	38.2	0.58	24.7
B	VDD25013D	782.8	796.55	13.8	1.13	12.2
B	VDD25013D	844	858	14	1.01	12.1
B	VDD25013D	871.45	878	6.5	1.14	13.6
B	VDD25013D	957.4	966	8.6	1.07	13.43
B	VDD25013D	1025.6	1036.95	11.4	1.17	11.28
B	VDD24115B ¹	1307	1328.33	21.33	1.24	9.31
B	VDD24115B ¹	1286.9	1330.95	44.05	0.97	11.6

VDD24115B¹: Assay results does not represent new material information but provides supporting detail for data previously included in the published [Mineral Resource Statement](#).

APPENDIX 2.2: Full assay results

In the drillhole tables below, CU_PCT and FE_PCT columns are thematically colour-coded based on value ranges.

In DENSITY column pale pink-shaded values are directly assigned based on the average bulk density of the local rock type. The remaining values, i.e., those without shading, have density values derived from direct measurements.

In SAMPLE_ID column NO SAMPLE intervals represent unmineralised zones identified by geological logging and not submitted for assay. Assay values shown are database placeholders, not analytical results. Density values are assigned based on the average bulk density of the local rock type.

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
398.2	399.77	1.57	VS049422	0.002	10.25	0.04	3.02
399.77	400.96	1.19	VS049423	0.003	10.35	0.04	3.03
400.96	402.67	1.71	VS049424	0.002	9.61	0.01	2.96
402.67	404.2	1.53	VS049425	0.003	9.43	0.02	2.95
404.2	405.66	1.46	VS049426	0.02	9.28	0.13	2.95
405.66	407.1	1.44	VS049427	0.001	8.77	0.01	2.94
407.1	408.68	1.58	VS049428	0.003	8.78	0.01	2.93
408.68	409.74	1.06	VS049429	0.004	8.74	0.04	2.98
409.74	410.66	0.92	VS049430	0.007	9.15	0.07	2.97
410.66	411.81	1.15	VS049431	0.002	8.59	0.03	2.93
411.81	412.2	0.39	VS049433	0.003	9.35	0.03	2.96
412.2	413.5	1.3	VS049434	0.063	8.04	0.28	2.95
413.5	414.26	0.76	VS049435	1.29	7.88	5.13	2.91
414.26	415.34	1.08	VS049436	1.445	3.69	5.34	2.70
415.34	415.96	0.62	VS049438	0.47	2.92	1.66	2.72
415.96	416.92	0.96	VS049439	0.074	1.1	0.55	2.68
416.92	417.49	0.57	VS049440	0.182	1.66	1.52	2.76
417.49	417.86	0.37	VS049442	0.094	4.62	0.86	2.93
417.86	418.84	0.98	VS049443	0.112	11.5	0.48	3.03
418.84	420.06	1.22	VS049444	0.15	14.7	0.31	3.06
420.06	421.04	0.98	VS049445	0.052	7.65	0.09	2.89
421.04	422.03	0.99	VS049446	0.076	7.81	0.14	2.92
422.03	422.58	0.55	VS049448	0.066	10.2	0.13	2.95
422.58	424.04	1.46	VS049449	0.167	11.35	0.38	2.88
424.04	424.95	0.91	VS049450	0.121	13.95	0.26	3.16
424.95	426.23	1.28	VS049451	0.056	11.25	0.15	3.03
426.23	427.1	0.87	VS049452	0.071	10.45	0.17	3.02
427.1	428.66	1.56	VS049454	0.061	12.85	0.19	2.86
428.66	429.37	0.71	VS049455	0.043	9.15	0.13	2.90
429.37	430.59	1.22	VS049456	0.033	13.2	0.07	3.13
430.59	431.63	1.04	VS049457	0.011	9.71	0.04	3.02
431.63	432.77	1.14	VS049458	0.042	11.9	0.12	3.03
432.77	434.28	1.51	VS049459	0.035	11.6	0.09	2.93
434.28	435.76	1.48	VS049461	0.375	14.15	0.53	3.08
435.76	437.2	1.44	VS049462	0.028	10.55	0.08	2.95

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
437.2	438.68	1.48	VS049463	0.012	9.1	0.04	2.95
438.68	440	1.32	VS049464	0.004	8.53	0.03	2.93
440	441.33	1.33	VS049465	0.002	9.33	0.02	2.93
441.33	441.98	0.65	VS049466	0.009	10.45	0.02	3.02
441.98	443.04	1.06	VS049468	0.008	11.5	0.05	3.06
443.04	444.46	1.42	VS049469	0.007	11.3	0.03	3.07
548.44	549.73	1.29	VS049627	0.007	8.14	0.01	2.98
549.73	551	1.27	VS049628	0.029	10.15	0.06	2.96
551	552	1	VS049629	0.044	9.68	0.12	3.03
552	553.02	1.02	VS049630	0.005	9.84	0.005	2.92
553.02	554.08	1.06	VS049631	0.007	11.5	0.005	2.93
554.08	555	0.92	VS049633	0.007	9.42	0.005	2.94
555	556.32	1.32	VS049634	0.04	10.35	0.1	2.95
556.32	557.45	1.13	VS049635	0.011	7.96	0.05	2.76
557.45	558.49	1.04	VS049636	0.034	6.01	0.14	2.76
558.49	559.49	1	VS049637	0.009	6.52	0.08	2.77
559.49	560.54	1.05	VS049639	0.005	5.47	0.05	2.64
560.54	561.41	0.87	VS049640	0.003	9.47	0.01	2.89
561.41	562.27	0.86	VS049641	0.009	9.17	0.02	2.90
562.27	563.68	1.41	VS049642	0.004	5.64	0.02	2.82
563.68	564.7	1.02	VS049643	0.002	9.89	0.005	2.89
564.7	566	1.3	VS049644	0.009	9.76	0.02	2.93
566	567.22	1.22	VS049646	0.006	10.3	0.01	2.93
567.22	568.59	1.37	VS049647	0.009	10.25	0.01	2.95
568.59	570.04	1.45	VS049648	0.006	10.8	0.02	2.97
570.04	571.13	1.09	VS049649	0.023	12.15	0.11	2.99
571.13	572.35	1.22	VS049650	0.009	11.15	0.02	3.01
572.35	573.61	1.26	VS049652	0.007	11.05	0.005	3.04
573.61	575	1.39	VS049653	0.003	12.1	0.005	3.02
575	576.32	1.32	VS049654	0.004	11.3	0.005	3.01
576.32	577.55	1.23	VS049655	0.011	10.55	0.04	2.99
577.55	578.74	1.19	VS049656	0.022	10.05	0.1	2.91
578.74	579.97	1.23	VS049658	0.008	10.85	0.02	3.01
579.97	581.3	1.33	VS049659	0.041	11.65	0.2	3.01
581.3	582.53	1.23	VS049660	0.012	10.4	0.08	3.03
582.53	583.72	1.19	VS049661	0.016	11.1	0.16	3.05
583.72	585	1.28	VS049662	0.008	11.05	0.11	3.02
585	586	1	VS049663	0.16	10.65	0.97	3.03
586	587.08	1.08	VS049665	0.026	11.55	0.28	3.03
637.06	638.1	1.04	VS049666	0.016	9.75	0.08	3.04
638.1	639.16	1.06	VS049667	0.008	9.07	0.07	2.97
639.16	640.11	0.95	VS049668	0.002	7.37	0.02	2.93
640.11	641.23	1.12	VS049669	0.013	4.44	0.07	2.95
641.23	642.27	1.04	VS049670	0.003	3.47	0.05	2.69
642.27	643.44	1.17	VS049672	0.035	5.41	0.24	2.67
643.44	644.04	0.6	VS049673	0.035	10.95	0.54	3.03
644.04	645	0.96	VS049674	0.013	5.41	0.06	2.78

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
645	645.71	0.71	VS049675	0.059	7.7	0.42	2.80
645.71	646.34	0.63	VS049676	0.003	6.99	0.06	2.76
646.34	647.55	1.21	VS049678	0.029	12.4	0.27	2.95
647.55	648.86	1.31	VS049679	0.01	10.7	0.07	3.00
648.86	650	1.14	VS049680	0.006	6.63	0.05	3.02
650	651.15	1.15	VS049681	0.011	8.88	0.04	3.00
651.15	652.52	1.37	VS049682	0.005	8.48	0.06	2.80
652.52	653.79	1.27	VS049683	0.01	9.22	0.06	2.84
653.79	655	1.21	VS049685	0.014	9.58	0.06	2.86
655	656.3	1.3	VS049686	0.032	8.94	0.15	3.14
656.3	657.71	1.41	VS049687	0.051	7.37	0.3	2.79
657.71	659.1	1.39	VS049688	0.067	12.4	0.24	3.01
659.1	660.13	1.03	VS049689	0.02	10.25	0.09	2.90
660.13	661.37	1.24	VS049691	0.018	9.44	0.1	2.88
661.37	662.45	1.08	VS049692	0.074	11.9	0.5	2.94
662.45	663.51	1.06	VS049693	0.012	11.4	0.06	2.85
663.51	664.6	1.09	VS049694	0.01	11.45	0.04	2.91
664.6	665.83	1.23	VS049695	0.011	8.93	0.08	2.81
665.83	667	1.17	VS049697	0.009	10.05	0.01	3.16
667	668.33	1.33	VS049698	0.007	10.65	0.02	2.97
668.33	669.66	1.33	VS049699	0.002	11.05	0.01	2.91
669.66	670.14	0.48	VS049700	0.076	13.25	0.32	3.10
670.14	670.86	0.72	VS049701	0.026	9.07	0.08	2.93
670.86	671.75	0.89	VS049702	0.007	9.7	0.03	3.23
671.75	672.35	0.6	VS049704	0.032	10.1	0.06	2.94
672.35	672.93	0.58	VS049705	0.091	11.05	0.09	2.88
672.93	673.62	0.69	VS049706	0.025	10.05	0.09	2.89
673.62	674.89	1.27	VS049707	0.017	9.49	0.03	3.01
674.89	676.48	1.59	VS050057	0.005	10.25	0.03	3.00
676.48	677.16	0.68	VS050058	0.05	10.3	0.26	3.00
677.16	679.66	2.5	VS050059	0.013	8.53	0.04	3.00
679.66	682.12	2.46	VS050060	0.04	8.64	0.08	3.00
682.12	683.73	1.61	VS050061	0.005	9.66	0.01	3.00
683.73	685.18	1.45	VS050063	0.005	9.23	0.01	3.00
685.18	687.59	2.41	VS050064	0.002	9.17	0.01	3.00
687.59	690	2.41	VS050065	0.01	9.31	0.05	3.00
690	692.35	2.35	VS050066	0.004	9	0.02	3.00
692.35	694.72	2.37	VS050067	0.006	8.62	0.04	3.00
694.72	695.88	1.16	VS050068	0.128	10.3	0.32	3.00
695.88	697.79	1.91	VS050070	0.013	10	0.11	3.00
797.66	799.1	1.44	VS050071	0.169	12	0.37	3.00
799.1	800.54	1.44	VS050072	0.031	12	0.04	3.00
800.54	801.97	1.43	VS050073	0.018	12.3	0.06	3.00
801.97	803.42	1.45	VS050074	0.01	11.55	0.09	3.00
803.42	804.86	1.44	VS050075	0.018	10.6	0.05	3.00
804.86	806.32	1.46	VS050076	0.046	11.7	0.28	3.00
806.32	807.74	1.42	VS050078	0.003	10.15	0.02	3.00

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
807.74	809.2	1.46	VS050079	0.023	10.95	0.14	3.00
823.73	824.89	1.16	VS048971	0.016	10.9	0.05	3.00
824.89	826.05	1.16	VS048972	0.008	10.7	0.01	3.00
839.72	841.11	1.39	VS048973	0.013	11.2	0.02	3.00
841.11	842.5	1.39	VS048974	0.011	11.4	0.03	3.00
842.5	843.89	1.39	VS048975	0.009	11.25	0.04	3.00
843.89	845.28	1.39	VS048976	0.019	11.05	0.02	3.00
845.28	846.67	1.39	VS048977	0.017	11	0.02	3.00
846.67	848.06	1.39	VS048978	0.008	11.85	0.02	3.00
848.06	849.21	1.15	VS048979	0.03	11	0.05	3.00
849.21	850.36	1.15	VS048981	0.091	11.45	0.12	3.00
864.94	865.28	0.34	VS048982	0.078	10.7	0.06	3.00
865.28	866.4	1.12	VS048983	0.043	11.4	0.03	3.00
866.4	867.52	1.12	VS048984	0.04	11.95	0.08	3.00
867.52	868.64	1.12	VS048985	0.019	11.3	0.07	3.00
879.08	880.2	1.12	VS048986	0.014	12.85	0.05	3.00
880.2	881.32	1.12	VS048987	0.026	12.5	0.06	3.00
881.32	882.46	1.14	VS048988	0.041	13.6	0.07	3.00
882.46	883.76	1.3	VS048989	0.022	12.5	0.04	3.00
883.76	885.18	1.42	VS048990	0.138	19.2	0.44	3.00
885.18	886.6	1.42	VS048992	0.067	13.5	0.22	3.00
886.6	888.02	1.42	VS048993	0.194	15.2	1.1	3.00
888.02	889.44	1.42	VS048994	0.272	17.5	0.9	3.00
889.44	890.86	1.42	VS048995	0.152	18.2	0.62	3.00
890.86	892.28	1.42	VS048996	0.1	17.65	0.41	3.00
892.28	893.53	1.25	VS048998	0.01	11.7	0.04	3.00
893.53	894.78	1.25	VS048999	0.006	11.3	0.02	3.00
894.78	895.98	1.2	VS049000	0.024	8.02	0.04	3.00
895.98	897.49	1.51	VS049001	0.023	12.9	0.06	3.00
897.49	899	1.51	VS049002	0.064	13.95	0.35	3.00
899	900.34	1.34	VS049003	0.014	13.85	0.1	3.00
900.34	901.68	1.34	VS049004	0.007	12.25	0.03	3.00
901.68	903.03	1.35	VS049005	0.004	11.75	0.01	3.00
903.03	904.3	1.27	VS049007	0.296	13.85	0.92	3.00
904.3	905.57	1.27	VS049008	0.324	12.8	0.76	3.00
905.57	906.87	1.3	VS049009	0.09	15.85	0.12	3.00
906.87	908.14	1.27	VS049010	0.079	15.05	0.17	3.00
908.14	909.47	1.33	VS049011	0.03	10.75	0.08	3.00
909.47	910.66	1.19	VS049012	0.07	12.1	0.2	3.00
910.66	913	2.34	VS049013	0.044	12.75	0.09	3.00
929.6	930.83	1.23	VS049014	0.019	14.7	0.05	3.04
930.83	932.06	1.23	VS049015	0.02	13.9	0.04	3.05
932.06	933.29	1.23	VS049017	0.018	14.1	0.04	3.04
933.29	934.54	1.25	VS049018	0.008	14.55	0.02	3.06
934.54	935.77	1.23	VS049019	0.024	14.3	0.05	3.05
935.77	937.03	1.26	VS049020	0.028	14.9	0.08	3.06
937.03	938.39	1.36	VS049021	0.093	12.7	0.24	3.03

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
938.39	939.75	1.36	VS049022	0.016	14.9	0.04	3.07
939.75	941.11	1.36	VS049023	0.025	13.6	0.07	2.95
941.11	942.48	1.37	VS049024	0.016	14.05	0.05	2.92
942.48	943.63	1.15	VS049025	0.112	14.65	0.27	3.01
943.63	944.78	1.15	VS049027	0.016	14.75	0.06	3.05
944.78	945.93	1.15	VS049028	0.11	14.6	0.3	2.92
945.93	947.08	1.15	VS049029	0.071	14.75	0.16	2.89
947.08	948.23	1.15	VS049030	0.004	16.25	0.01	3.08
948.23	949.38	1.15	VS049031	0.012	14.6	0.05	2.99
949.38	950.53	1.15	VS049032	0.092	16.3	0.22	3.04
950.53	951.7	1.17	VS049033	0.034	15.1	0.07	3.06
951.7	952.71	1.01	VS049034	0.138	22.4	0.36	3.59
952.71	953.72	1.01	VS049036	0.361	27.7	0.94	3.52
953.72	954.87	1.15	VS049037	0.181	17.15	0.36	3.19
954.87	956.02	1.15	VS049038	0.174	22	0.57	3.20
956.02	957.17	1.15	VS049039	0.338	24.6	0.47	3.25
957.17	958.32	1.15	VS049040	0.388	24.9	0.56	3.08
958.32	959.47	1.15	VS049041	0.145	21.1	0.29	3.24
959.47	960.62	1.15	VS049043	0.149	22.8	0.37	3.11
960.62	961.82	1.2	VS049044	0.255	20.2	0.44	3.42
961.82	962.86	1.04	VS049045	0.036	14.95	0.07	3.12
962.86	963.9	1.04	VS049046	0.016	14.35	0.03	2.92
963.9	964.94	1.04	VS049047	0.529	26.8	0.93	3.59
964.94	966.09	1.15	VS049049	0.01	13.2	0.03	3.01
966.09	967.24	1.15	VS049050	0.008	13.2	0.01	3.08
967.24	968.4	1.16	VS049051	0.01	13.2	0.03	3.04
968.4	969.43	1.03	VS049052	0.006	13.65	0.01	3.04
969.43	970.46	1.03	VS049053	0.029	14.35	0.04	3.03
970.46	971.5	1.04	VS049054	0.034	12.6	0.07	3.00
971.5	972.7	1.2	VS049055	0.021	13.2	0.05	3.00
972.7	973.9	1.2	VS049056	0.007	14.3	0.02	3.09
973.9	975.1	1.2	VS049057	0.084	14.35	0.19	3.04
975.1	976.3	1.2	VS049059	0.07	12.75	0.17	3.05
976.3	977.5	1.2	VS049060	0.009	13.1	0.03	3.00
977.5	978.74	1.24	VS049061	0.02	13.9	0.12	3.04
978.74	979.62	0.88	VS049062	0.06	14.3	0.14	3.02
979.62	980.5	0.88	VS049063	0.159	15.5	0.38	3.23
980.5	981.72	1.22	VS049065	0.042	13.2	0.12	3.03
981.72	982.94	1.22	VS049066	0.092	13.05	0.27	2.96
982.94	984.09	1.15	VS049067	0.039	10.25	0.14	2.87
984.09	985.24	1.15	VS049068	0.071	12.65	0.13	2.77
985.24	986.4	1.16	VS049069	0.043	10	0.1	2.83
986.4	987.65	1.25	VS049070	0.056	8.65	0.17	2.96
987.65	988.9	1.25	VS049071	0.007	6.66	0.04	2.92
988.9	989.92	1.02	VS049072	0.009	9.95	0.05	2.92
989.92	990.94	1.02	VS049073	0.018	11.1	0.07	2.90
990.94	991.96	1.02	VS049075	0.033	11.1	0.1	2.88

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
991.96	993	1.04	VS049076	0.072	12.7	0.19	2.97
993	994.28	1.28	VS049077	0.015	12.15	0.03	2.93
994.28	995.56	1.28	VS049078	0.029	12.7	0.04	2.95
995.56	996.84	1.28	VS049079	0.013	12.3	0.03	2.99
996.84	998.12	1.28	VS049080	0.007	11.65	0.04	2.95
998.12	999.41	1.29	VS049081	0.062	10	0.13	2.93
999.41	1000.51	1.1	VS049082	0.214	24.2	0.73	3.26
1000.51	1001.62	1.11	VS049083	0.2	17.95	0.78	3.29
1001.62	1002.7	1.08	VS049085	0.108	16.4	0.35	2.99
1002.7	1003.82	1.12	VS049086	0.432	23.6	1.26	3.57
1003.82	1005.05	1.23	VS049088	0.04	12.7	0.1	2.93
1005.05	1006.28	1.23	VS049089	0.001	10.25	0.01	2.87
1006.28	1007.52	1.24	VS049090	0.001	11	0.005	2.88
1007.52	1008.75	1.23	VS049091	0.006	8.7	0.03	2.74
1008.75	1009.98	1.23	VS049092	0.104	11.9	0.27	2.91
1009.98	1011.23	1.25	VS049093	0	12.45	0.01	2.88
1011.23	1012.44	1.21	VS049094	0	13.7	0.005	2.98
1012.44	1013.67	1.23	VS049095	0.017	13.95	0.04	3.11
1013.67	1014.9	1.23	VS049096	0.003	12.75	0.03	3.16
1014.9	1016.13	1.23	VS049098	0.001	11.75	0.03	2.97
1016.13	1017.4	1.27	VS049099	0.002	10.95	0.02	2.93
1017.4	1019.06	1.66	VS049100	0.013	13.55	0.05	3.09
1019.06	1020.72	1.66	VS049101	0.001	12.35	0.01	3.02
1020.72	1022.38	1.66	VS049102	0	10.85	0.01	2.92
1022.38	1024.04	1.66	VS049103	0.01	11.65	0.05	2.98
1024.04	1026.09	2.05	VS049104	0.003	11.9	0.01	2.95
1026.09	1028.14	2.05	VS049105	0.003	12.55	0.01	2.95
1028.14	1030.2	2.06	VS049106	0.003	10.55	0.03	2.95
1030.7	1032.83	2.13	VS049108	0.013	11.6	0.04	2.95
1032.83	1034.94	2.11	VS049109	0.002	11.5	0.05	2.95
1034.94	1037.1	2.16	VS049110	0.07	10.45	0.38	2.95
1037.1	1039.85	2.75	VS074661	0.043	11.25	0.17	2.97
1039.85	1042.8	2.95	VS074662	0.092	9.65	0.24	2.95
1042.8	1045.8	3	VS074663	0.006	9.33	0.05	2.95
1045.8	1047.8	2	VS074664	0.004	9.43	0.03	2.95
1047.8	1048.9	1.1	VS074665	0.052	9.49	0.13	2.95
1048.9	1051.5	2.6	VS074666	0.001	10.25	0.03	2.95
1051.5	1053.8	2.3	VS074667	0.005	9.41	0.04	2.91
1053.8	1056.1	2.3	VS074668	0.005	10.3	0.03	2.95
1056.1	1059	2.9	VS074669	0.051	12	0.23	2.95
1059	1061	2	VS074670	0.082	13.1	0.53	2.95
1061	1063.4	2.4	VS074672	0.017	11.3	0.05	2.95
1063.4	1065.85	2.45	VS074673	0.019	11.15	0.07	2.95
1065.85	1067.8	1.95	VS074674	0.001	10.55	0.005	2.98
1067.8	1070.7	2.9	VS074675	0.046	11.1	0.08	2.95
1070.7	1072.9	2.2	VS074676	0.002	10.95	0.06	2.95
1072.9	1074.2	1.3	VS074677	0.002	10.7	0.005	2.95

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1074.2	1075.8	1.6	VS074678	0.019	11.95	0.21	2.95
1075.8	1077.2	1.4	VS074679	0.001	10	0.02	2.95
1077.2	1078.5	1.3	VS074680	0.039	11.75	0.17	2.96
1078.5	1080.2	1.7	VS074681	0.022	10.6	0.08	2.95
1080.2	1081.5	1.3	VS074683	0.065	11.2	0.27	2.95
1081.5	1082.4	0.9	VS074684	0.022	11.75	0.09	2.95
1082.4	1085.1	2.7	VS074685	0.004	10.05	0.02	2.95
1085.1	1087.3	2.2	VS074686	0.001	10.35	0.02	2.95
1087.3	1089.3	2	VS074687	0.001	10.95	0.03	2.94
1089.3	1091.5	2.2	VS074688	0.001	9.68	0.05	2.95
1091.5	1094	2.5	VS074689	0.005	8.88	0.02	2.95
1094	1096.65	2.65	VS074690	0.002	9.05	0.005	2.95
1096.65	1098.15	1.5	VS074691	0.009	10.1	0.03	2.95
1098.15	1099.7	1.55	VS074692	0.004	10.6	0.02	2.95
1099.7	1102.2	2.5	VS074694	0.078	11.65	0.47	2.99
1102.2	1104.7	2.5	VS074695	0.021	11.55	0.06	2.95
1104.7	1107.65	2.95	VS074696	0.026	12.05	0.07	2.95
1107.65	1109.5	1.85	VS074697	0.022	11.2	0.08	2.95
1109.5	1111.2	1.7	VS074698	0.015	11.7	0.06	2.95
1111.2	1112	0.8	VS074699	0.04	12.1	0.14	2.95
1112	1113	1	VS074700	0.06	12	0.36	2.98
1113	1114.1	1.1	VS074701	0.031	11.55	0.66	2.99
1114.1	1115.05	0.95	VS074702	0.025	12.25	0.12	2.99
1115.05	1116	0.95	VS074703	0.037	12.6	0.28	3.03
1116	1117	1	VS074705	0.028	13.55	0.12	3.07
1117	1118.3	1.3	VS074706	0.054	15.1	0.28	3.15
1118.3	1119.05	0.75	VS074707	0.097	18.15	0.43	3.06
1119.05	1120	0.95	VS074708	0.034	11.95	0.2	2.99
1120	1121.1	1.1	VS074709	0.034	13.25	0.23	3.03
1121.1	1122.2	1.1	VS074711	0.106	13	0.46	3.02
1122.2	1123	0.8	VS074712	0.095	15.15	0.8	3.09
1123	1123.9	0.9	VS074713	0.329	30.9	2.06	3.52
1123.9	1125	1.1	VS074714	0.19	16.75	0.94	3.13
1125	1125.7	0.7	VS074715	0.4	18.85	2.27	3.20
1125.7	1126.7	1	VS074716	0.374	20.5	1.73	3.27
1126.7	1127.9	1.2	VS074717	0.594	21.3	3.09	3.31
1127.9	1128.35	0.45	VS074719	0.457	25.7	2.37	3.80
1128.35	1129.05	0.7	VS074720	0.362	18.45	1.91	3.29
1129.05	1129.7	0.65	VS074721	0.215	11.65	0.98	3.20
1129.7	1130.9	1.2	VS074722	0.073	15.8	0.42	3.17
1130.9	1132	1.1	VS074723	0.068	16.25	0.43	3.06
1132	1132.85	0.85	VS074724	0.1	15.35	0.47	3.26
1132.85	1133.5	0.65	VS074725	0.11	20.8	0.49	3.35
1133.5	1134.3	0.8	VS074726	0.229	19.65	1.04	3.34
1134.3	1135.45	1.15	VS074727	0.085	16	0.82	3.09
1135.45	1135.9	0.45	VS074728	0.114	30.4	2.51	3.80
1135.9	1136.9	1	VS074730	0.095	13.1	0.66	3.00

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1136.9	1138.15	1.25	VS074731	0.054	10.5	0.41	2.92
1138.15	1139.2	1.05	VS074732	0.005	10.95	0.03	2.98
1139.2	1140.3	1.1	VS074733	0.014	9.58	0.06	2.96
1140.3	1141.2	0.9	VS074734	0.004	10.65	0.04	2.97
1141.2	1142.3	1.1	VS074735	0.029	9.6	0.07	2.98
1142.3	1143.2	0.9	VS074736	0.132	12.55	0.35	3.09
1143.2	1144	0.8	VS074737	0.02	10.65	0.07	2.95
1144	1145	1	VS074738	0.015	10.3	0.05	2.95
1145	1146	1	VS074739	0.009	8.84	0.04	2.95
1146	1148	2	VS074741	0.002	10.15	0.02	2.95
1148	1149.8	1.8	VS074742	0.002	10.05	0.005	2.96
1149.8	1152	2.2	VS074743	0.003	9.81	0.005	2.95
1152	1155	3	VS074744	0.018	10.2	0.05	2.95
1155	1157.1	2.1	VS074745	0.049	10	0.17	2.95
1157.1	1160	2.9	VS074746	0.016	9.42	0.06	2.95
1160	1162	2	VS074747	0.004	9.94	0.02	2.95
1162	1164	2	VS074748	0.016	10.15	0.06	2.95
1164	1166	2	VS074749	0.066	10.9	0.17	2.95
1166	1167.95	1.95	VS074750	0.038	11.35	0.1	2.95
1167.95	1170.4	2.45	VS074752	0.014	8.89	0.03	2.95
1170.4	1173.3	2.9	VS074753	0.006	8.64	0.02	2.95
1173.3	1176	2.7	VS074754	0.007	9.17	0.02	2.90
1176	1177.8	1.8	VS074755	0.007	9.77	0.02	2.95
1177.8	1180.1	2.3	VS074756	0.022	8.29	0.03	2.95
1180.1	1182	1.9	VS074757	0.029	9.32	0.07	2.95
1182	1183.3	1.3	VS074758	0	11.2	0.005	2.95
1183.3	1184.9	1.6	VS074759	0.002	10.15	0.005	2.93
1184.9	1186.85	1.95	VS074760	0.002	6.4	0.02	2.82
1186.85	1188	1.15	VS074761	0.016	7.44	0.06	2.92
1188	1190.8	2.8	VS074763	0.007	12.15	0.005	3.01
1190.8	1192.55	1.75	VS074764	0.024	7.29	0.03	2.93
1192.55	1193.8	1.25	VS074765	0.074	10.2	0.17	2.84
1193.8	1194.5	0.7	VS074766	0.001	7.32	0.005	2.94
1194.5	1195.5	1	VS074767	0.019	13.65	0.03	2.94
1195.5	1195.8	0.3	VS074768	0.089	16.65	0.08	3.03
1195.8	1196.7	0.9	VS074769	0.048	15.65	0.05	2.95
1196.7	1197.9	1.2	VS074770	0.079	16.65	0.12	2.95
1197.9	1198.2	0.3	VS074771	0.044	5.16	0.05	2.95
1198.2	1200	1.8	VS074974	0.03	4.33	0.09	2.74
1200	1202.7	2.7	VS074975	0.022	6.53	0.11	2.87
1202.7	1205.35	2.65	VS074976	0.03	4.62	0.13	2.96
1205.35	1208.05	2.7	VS074977	0.046	5.57	0.26	2.75
1208.05	1210.8	2.75	VS074978	0.059	5.29	0.24	2.82
1210.8	1213.3	2.5	VS074979	0.047	5	0.19	2.73
1213.3	1214.97	1.67	VS074980	0.025	5.12	0.3	2.81
1214.97	1216.65	1.68	VS074981	0.043	7.08	0.17	2.67
1216.65	1219.65	3	VS074982	0.29	7.72	0.84	2.83

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1219.65	1221.8	2.15	VS074983	0.631	17.3	2.5	3.13
1221.8	1224.4	2.6	VS074985	0.374	9.29	1.06	2.94
1224.4	1227.05	2.65	VS074986	0.313	5.16	1	2.71
1227.05	1227.7	0.65	VS074987	0.052	10.1	0.19	2.78
1227.7	1229.5	1.8	VS074988	0.362	5.55	1.14	2.84
1229.5	1232.04	2.54	VS074989	0.174	5.79	0.52	2.78
1232.04	1234.5	2.46	VS074990	0.132	7.65	0.36	2.73
1234.5	1237	2.5	VS074991	0.65	7.38	1.6	2.76
1237	1239.2	2.2	VS074992	0.066	5.46	0.19	2.66
1239.2	1241.15	1.95	VS074993	0.295	5.91	0.62	2.70
1241.15	1243.35	2.2	VS074994	0.138	6.84	0.37	2.70
1243.35	1245.45	2.1	VS074995	0.293	4.91	0.67	2.72
1245.45	1247.7	2.25	VS074996	0.069	9.02	0.17	2.93
1247.7	1250.54	2.84	VS074997	0.01	9.23	0.03	3.12
1250.54	1253.3	2.76	VS074998	0.035	10.05	0.07	2.97
1253.3	1256	2.7	VS074999	0.035	10.5	0.06	3.09
1256	1258.3	2.3	VS075001	0.11	10.85	0.18	2.90
1258.3	1260.82	2.52	VS075002	0.182	11.25	0.39	3.02
1260.82	1263	2.18	VS075003	0.158	10.7	0.23	2.90
1263	1265.75	2.75	VS075004	0.03	10.2	0.03	3.05
1265.75	1268.6	2.85	VS075005	0.017	10.5	0.03	3.10
1268.6	1271.36	2.76	VS075006	0.047	10.6	0.05	2.99
1271.36	1274.22	2.86	VS075007	0.102	11.25	0.12	3.10
1274.22	1277	2.78	VS075008	0.102	10.45	0.09	3.02
1277	1279.7	2.7	VS075009	0.026	10.6	0.09	2.94
1279.7	1282.4	2.7	VS075010	0.022	10.6	0.03	2.99
1282.4	1285	2.6	VS075011	0.006	9.29	0.04	3.12
1285	1287.3	2.3	VS075012	0.017	9.61	0.005	2.93
1287.3	1290	2.7	VS075013	0.007	10.45	0.005	3.01
1290	1293	3	VS075014	0.01	9.53	0.02	2.92
1293	1296	3	VS075015	0.007	9.28	0.02	3.08
1296	1299	3	VS075016	0.01	8.9	0.02	2.94
1299	1302	3	VS075018	0.009	9.63	0.02	2.92
1302	1305	3	VS075019	0.005	9.52	0.02	3.04
1305	1308	3	VS075020	0.008	9.85	0.03	3.10
1308	1310.8	2.8	VS075021	0.01	9.8	0.04	2.96
1310.8	1313.56	2.76	VS075022	0.034	10.1	0.07	3.02
1313.56	1316.38	2.82	VS075023	0.037	10.8	0.03	3.09
1316.38	1319.2	2.82	VS075024	0.022	10.15	0.02	3.08
1319.2	1322	2.8	VS075025	0.011	9.52	0.02	3.08
1322	1324.74	2.74	VS075026	0.011	9.44	0.02	3.04
1324.74	1327.5	2.76	VS075027	0.013	8.85	0.02	3.11
1327.5	1330.25	2.75	VS075028	0.004	9.1	0.005	2.89
1330.25	1332.98	2.73	VS075029	0.003	8.81	0.005	3.03
1332.98	1335.73	2.75	VS075030	0.009	8.31	0.02	2.88
1335.73	1338.44	2.71	VS075031	0.003	8.93	0.005	3.04
1338.44	1341	2.56	VS075032	0.002	9.04	0.005	2.99

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1341	1343.1	2.1	VS075548	0.009	8.27	0.03	3.00
1343.1	1345	1.9	VS075549	0.013	8.34	0.02	3.01
1345	1348	3	VS075550	0.008	8.65	0.02	3.01
1348	1351	3	VS075551	0.011	8.72	0.03	3.02
1351	1353	2	VS075552	0.013	8.65	0.03	3.02
1353	1355.05	2.05	VS075553	0.013	8.72	0.03	2.95
1355.05	1356.05	1	VS075554	0.002	9.77	0.005	2.95
1356.05	1359	2.95	VS075555	0.012	9.01	0.02	2.95
1359	1362	3	VS075556	0.009	8.94	0.02	3.03
1362	1365	3	VS075557	0.015	9.01	0.03	3.04
1365	1368	3	VS075559	0.056	9.97	0.05	3.04
1368	1371	3	VS075560	0.028	9.2	0.04	3.04
1371	1374	3	VS075561	0.025	9.8	0.03	2.92
1374	1375.25	1.25	VS075562	0.119	6.78	0.05	2.92
1375.25	1376.5	1.25	VS075563	0.075	4.24	0.08	2.92
1376.5	1377.5	1	VS075564	0.412	3.78	0.41	2.80
1377.5	1378.7	1.2	VS075565	1.185	5	1.92	2.80
1378.7	1380	1.3	VS075566	0.652	3.93	0.44	2.74
1380	1381	1	VS075567	0.226	4.03	0.13	2.80
1381	1382	1	VS075568	0.242	2.92	0.12	2.80
1382	1383.3	1.3	VS075569	0.194	1.78	0.12	2.80
1383.3	1383.8	0.5	VS075571	1.29	3.99	0.7	2.73
1383.8	1384.9	1.1	VS075572	5.42	11.55	2.52	3.17
1384.9	1386	1.1	VS075573	1.335	4.93	0.64	2.75
1386	1386.78	0.78	VS075574	0.801	3.48	0.52	2.71
1386.78	1388	1.22	VS075576	0.289	2.5	0.3	2.80
1388	1389	1	VS075577	0.198	1.76	0.13	2.80
1389	1390.05	1.05	VS075578	0.449	2.24	0.29	2.80
1390.05	1390.4	0.35	VS075579	7.07	11.05	5.78	2.80
1390.4	1391.7	1.3	VS075580	0.49	2.11	0.38	2.80
1391.7	1393	1.3	VS075581	1.075	3.44	0.94	2.80
1393	1393.85	0.85	VS075582	0.216	2.82	0.26	2.80
1393.85	1394.65	0.8	VS075583	0.091	1.92	0.09	2.72
1394.65	1395.9	1.25	VS075584	0.162	2.12	0.08	2.80
1395.9	1397	1.1	VS075585	0.456	2.49	0.45	2.80
1397	1398.25	1.25	VS075587	0.655	3.36	0.6	2.80
1398.25	1399.5	1.25	VS075588	0.024	3.46	0.03	2.78
1399.5	1400.85	1.35	VS075589	0.001	3.23	0.02	2.78
1400.85	1403.1	2.25	VS075590	0	3.26	0.005	2.75
1403.1	1405.5	2.4	VS075591	0.017	3.74	0.03	2.95
1405.5	1407.3	1.8	VS075592	0.015	3.42	0.05	2.95
1407.3	1409.1	1.8	VS075593	0.293	4.6	0.07	2.95
1409.1	1410	0.9	VS075594	0.937	8.57	0.82	3.02
1410	1411.2	1.2	VS075595	1.21	8.86	0.26	2.86
1411.2	1412.9	1.7	VS075596	0.299	3.05	0.06	2.70
1412.9	1415	2.1	VS075598	0.004	2.38	0.04	2.76
1415	1417	2	VS075599	0.051	2.8	0.04	2.76

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1417	1419	2	VS075600	0.187	3.96	0.04	2.82
1419	1420.3	1.3	VS075601	0.148	7.4	0.02	2.90
1420.3	1423.3	3	VS075602	0.118	11.55	0.09	2.90
1423.3	1426	2.7	VS075603	0.142	8.99	0.27	2.97
1426	1428.5	2.5	VS075604	0.128	10.9	0.14	2.95
1428.5	1429.8	1.3	VS075605	0.122	10.25	0.37	2.95
1429.8	1431.1	1.3	VS075606	0.098	10.55	0.13	2.95
1431.1	1432.4	1.3	VS075607	0.069	10.8	0.06	2.95
1432.4	1433.7	1.3	VS075609	0.037	12.15	0.09	2.96
1433.7	1435	1.3	VS075610	0.251	11.2	0.24	2.95
1435	1436.3	1.3	VS075611	0.09	10.9	0.08	2.95
1436.3	1437.6	1.3	VS075612	0.134	10.45	0.3	2.95
1437.6	1438.9	1.3	VS075613	0.084	9.7	0.05	2.95
1438.9	1439.8	0.9	VS075614	0.011	9.88	0.03	2.95
1439.8	1440.6	0.8	VS075615	0.015	10	0.03	2.95
1440.6	1441.8	1.2	VS075617	0.212	13.05	0.08	2.96
1441.8	1443.1	1.3	VS075618	0.125	13.45	0.11	2.95
1443.1	1444.3	1.2	VS075619	0.211	13.8	0.08	2.95
1444.3	1445.6	1.3	VS075620	0.19	15.85	0.09	2.95
1445.6	1446.9	1.3	VS075621	0.138	16.35	0.08	2.95
1446.9	1448.2	1.3	VS075622	0.118	17.5	0.05	3.06
1448.2	1449.5	1.3	VS075623	0.066	17.25	0.05	3.07
1449.5	1450.7	1.2	VS075624	0.07	17	0.05	3.07
1450.7	1452	1.3	VS075625	0.156	16.5	0.07	3.08
1452	1453.15	1.15	VS075626	0.103	16.25	0.07	3.08
1453.15	1454.4	1.25	VS075627	0.183	16.05	0.09	3.08
1454.4	1455.6	1.2	VS075629	0.198	15	0.11	3.08
1455.6	1456.9	1.3	VS075630	0.369	15.75	0.67	2.95
1456.9	1458.2	1.3	VS075631	0.615	14.8	0.91	2.95
1458.2	1459.5	1.3	VS075632	0.466	9.68	0.78	2.76
1459.5	1460.5	1	VS075633	0.625	14.85	1.04	2.95
1460.5	1461.2	0.7	VS075634	1.12	13.9	0.45	2.99
1461.2	1462.2	1	VS075635	1.585	14.2	0.67	2.95
1462.2	1463.2	1	VS075636	0.45	11.8	0.29	2.95
1463.2	1464.2	1	VS075637	0.545	18.85	0.26	2.95
1464.2	1465.2	1	VS075638	0.496	16.4	0.25	3.04
1465.2	1466.2	1	VS075640	1.06	18	0.29	2.95
1466.2	1467.45	1.25	VS075641	0.64	17	0.21	2.95
1467.45	1468.6	1.15	VS075642	0.885	11.9	0.3	2.95
1468.6	1469.8	1.2	VS075643	0.892	12	0.3	2.95
1469.8	1471.1	1.3	VS075644	0.589	15.8	0.24	3.02
1471.1	1472.2	1.1	VS075645	0.174	17.7	0.13	3.11
1472.2	1473.3	1.1	VS075646	0.04	18.6	0.07	3.11
1473.3	1474.6	1.3	VS075647	0.061	19.6	0.08	3.11
1474.6	1475.9	1.3	VS075648	0.355	18.2	0.14	3.20
1475.9	1477.2	1.3	VS075649	0.305	18	0.13	3.12
1477.2	1478.5	1.3	VS075651	0.032	17	0.05	3.12

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1478.5	1479.8	1.3	VS075652	0.054	16.55	0.06	3.03
1479.8	1481.1	1.3	VS075653	0.064	17.05	0.08	3.04
1481.1	1482.3	1.2	VS075654	0.405	16.25	0.2	3.04
1482.3	1483.6	1.3	VS075655	0.065	16.7	0.07	3.04
1483.6	1484.9	1.3	VS075656	0.071	13.85	0.1	3.04
1484.9	1485.9	1	VS075657	0.066	16.2	0.08	3.08
1485.9	1487.2	1.3	VS075659	0.05	15.55	0.06	3.08
1487.2	1488.5	1.3	VS075660	0.03	14.9	0.1	3.07
1488.5	1489.8	1.3	VS075661	0.041	15.5	0.09	3.01
1489.8	1490.8	1	VS075662	0.04	14.75	0.09	3.01
1490.8	1492.1	1.3	VS075663	0.264	12.75	0.42	3.01
1492.1	1493.4	1.3	VS075664	0.067	13.1	0.09	2.95
1493.4	1494.65	1.25	VS075665	0.007	14.35	0.02	3.04
1494.65	1495.9	1.25	VS075666	0.012	14.45	0.03	3.04
1495.9	1497.2	1.3	VS075667	0.071	13.15	0.09	3.04
1497.2	1498.4	1.2	VS075668	0.012	14.55	0.03	3.13
1498.4	1499.5	1.1	VS075670	0.026	14.6	0.05	3.12
1499.5	1502.5	3	VS075671	0.086	15.6	0.16	3.10
1502.5	1505.5	3	VS075672	0.03	14.15	0.04	3.12
1505.5	1508	2.5	VS075673	0.062	14.55	0.07	3.14
1508	1510	2	VS075675	0.049	15.35	0.08	3.14
1510	1512.55	2.55	VS075676	0.047	15.35	0.07	3.16
1512.55	1515	2.45	VS075855	0.052	15.9	0.04	3.11
1515	1516.9	1.9	VS075856	0.051	14.5	0.06	3.13
1516.9	1519.3	2.4	VS075857	0.082	11.2	0.08	3.13
1519.3	1520.8	1.5	VS075858	0.024	10.1	0.04	3.13
1520.8	1523	2.2	VS075859	0.023	10.2	0.06	3.13
1523	1526	3	VS075860	0.025	10.1	0.03	3.13
1526	1529	3	VS075861	0.116	9.75	0.06	3.14
1529	1532	3	VS075862	0.05	10.1	0.03	3.02
1532	1535	3	VS075863	0.015	9.79	0.02	2.89
1535	1538	3	VS075864	0.03	9.98	0.02	3.04
1538	1541	3	VS075865	0.106	10.5	0.1	3.04
1541	1544	3	VS075867	0.026	10.1	0.05	3.04
1544	1547	3	VS075868	0.02	10.2	0.02	3.04
1547	1550	3	VS075869	0.018	9.86	0.03	3.04
1550	1553	3	VS075870	0.008	9.96	0.005	3.04
1553	1556	3	VS075871	0.019	10.05	0.03	3.04
1556	1559	3	VS075872	0.08	9.9	0.04	3.04
1559	1562	3	VS075873	0.018	9.8	0.02	3.04
1562	1565	3	VS075874	0.016	10.55	0.03	3.04
1565	1568	3	VS075875	0.02	9.57	0.02	3.04
1568	1571	3	VS075876	0.014	10	0.005	3.18
1571	1574	3	VS075878	0.017	10.25	0.005	3.01
1574	1577	3	VS075879	0.02	9.99	0.03	3.01
1577	1580	3	VS075880	0.009	9.99	0.02	3.01
1580	1583	3	VS075881	0.012	9.94	0.02	3.01

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1583	1586	3	VS075882	0.011	10.35	0.005	3.01
1586	1589	3	VS075883	0.021	10	0.02	3.01
1589	1592	3	VS075884	0.027	10.65	0.005	3.01
1592	1594.9	2.9	VS075885	0.019	10.45	0.03	3.01
1594.9	1597.5	2.6	VS075886	0.016	10.95	0.02	3.01
1597.5	1600	2.5	VS075887	0.011	10.95	0.02	3.01
1600	1603	3	VS075889	0.002	10.75	0.005	3.01
1603	1605.8	2.8	VS075890	0.005	11.05	0.02	2.84
1605.8	1608.8	3	VS075891	0.011	9.77	0.02	2.84
1608.8	1611.8	3	VS075892	0.004	8.96	0.005	2.83
1611.8	1614	2.2	VS075893	0.03	10.05	0.02	2.74
1614	1617	3	VS075894	0.034	4.64	0.005	2.65
1617	1620	3	VS075895	0.004	6.35	0.03	3.00
1620	1621.85	1.85	VS075896	0.013	4.54	0.03	3.00
1621.85	1623.7	1.85	VS075897	0.172	9.46	0.11	3.35
1623.7	1625.7	2	VS075898	0.008	2.25	0.03	3.63
1625.7	1628	2.3	VS075900	0.244	13.25	0.15	3.91
1628	1631	3	VS075901	0.035	7.64	0.04	3.31
1631	1633	2	VS075902	0.004	5.12	0.02	2.71
1633	1635	2	VS075903	0	5.1	0.005	2.83
1635	1638	3	VS075904	0.002	5.91	0.02	2.83
1638	1641	3	VS075905	0	5.24	0.005	2.83
1641	1644	3	VS075906	0	4.99	0.005	2.83
1644	1644.6	0.6	VS075907	0.001	5.02	0.005	2.83
1644.6	1647	2.4	VS075908	0.001	9.21	0.005	2.83
1647	1650	3	VS075909	0.015	12.5	0.02	2.94
1650	1652	2	VS075911	0.01	9.96	0.03	2.95
1652	1655	3	VS075912	0.04	9.63	0.06	2.95
1655	1657.05	2.05	VS075913	0.01	6.92	0.005	2.95
1657.05	1659.9	2.85	VS075914	0.009	3.09	0.005	2.71
1659.9	1661.5	1.6	VS075915	0.001	4.18	0.02	2.68
1661.5	1664.45	2.95	VS075916	0.003	3.34	0.005	2.64
1664.45	1667	2.55	VS075917	0.047	6.37	0.04	2.85
1667	1670	3	VS075918	0.014	7.64	0.02	2.85
1670	1673	3	VS075919	0.057	7.55	0.03	2.85
1673	1676	3	VS075920	0.037	5.9	0.005	3.05
1676	1677	1	VS075922	0.085	5.4	0.03	2.95
1677	1679.1	2.1	VS075923	0.11	4.32	0.04	2.95
1679.1	1681	1.9	VS075924	0.295	7.43	0.06	2.95
1681	1682.5	1.5	VS075925	0.295	5.61	0.06	2.84
1682.5	1682.8	0.3	VS075926	0.01	36.8	0.005	3.87
1682.8	1685	2.2	VS075927	0.002	8.93	0.06	3.26
1685	1687.8	2.8	VS075928	0.072	7.85	0.04	3.26
1687.8	1690.8	3	VS075929	0.013	3.52	0.005	3.26
1690.8	1693.7	2.9	VS075930	0.004	2.9	0.005	2.65
1693.7	1696.4	2.7	VS075931	0.013	6.52	0.02	2.70
1696.4	1698.5	2.1	VS075933	0.014	8.09	0.02	2.70

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1698.5	1701.1	2.6	VS075934	0.192	4.19	0.09	2.75
1701.1	1704	2.9	VS075935	0.04	4.61	0.02	2.74
1704	1707	3	VS075936	0.001	3.55	0.005	2.73
1707	1708.95	1.95	VS075937	0	3.45	0.005	2.76
1708.95	1710.25	1.3	VS075938	0	6.29	0.005	2.78
1710.25	1711.3	1.05	VS075939	0	2.78	0.005	2.72
1711.3	1712.6	1.3	VS075940	0	4.46	0.005	2.72
1712.6	1713.9	1.3	VS075942	0.001	3.13	0.005	2.66
1713.9	1715.2	1.3	VS075943	0.004	3.59	0.02	2.70
1715.2	1716.3	1.1	VS075944	0.009	4.21	0.005	2.70
1716.3	1717.3	1	VS075945	0.176	4.5	0.03	2.73
1717.3	1718.15	0.85	VS075946	0.024	6.57	0.03	3.01
1718.15	1718.9	0.75	VS075947	0.044	9.39	0.04	3.22
1718.9	1719.4	0.5	VS075949	2.09	41.7	0.87	3.58
1719.4	1719.8	0.4	VS075950	0.776	50.6	0.3	4.05
1719.8	1720.12	0.32	VS075951	0.435	40.7	0.16	3.58
1720.12	1721.3	1.18	VS076191	1.435	38.7	0.55	4.25
1721.3	1721.6	0.3	VS076192	0.046	6.41	0.03	3.05
1721.6	1722.42	0.82	VS076193	0.898	24.7	0.46	3.33
1722.42	1722.96	0.54	VS076194	1.155	25.9	0.59	3.26
1722.96	1723.65	0.69	VS076195	0.019	11	0.09	2.92
1723.65	1724.54	0.89	VS076197	0.032	4.68	0.12	2.84
1724.54	1725.14	0.6	VS076199	0.474	13.35	0.33	3.10
1725.14	1725.88	0.74	VS076200	1.11	16.35	0.81	3.07
1725.88	1726.6	0.72	VS076202	0.146	2.67	0.09	3.03
1726.6	1727.7	1.1	VS076204	1.17	27.4	0.49	2.84
1727.7	1728.65	0.95	VS076205	1.505	29.3	0.76	3.49
1728.65	1728.96	0.31	VS076206	0.043	0.91	0.03	3.30
1728.96	1730.2	1.24	VS076207	1.43	32.8	0.53	3.54
1730.2	1731.4	1.2	VS076208	0.966	18.45	0.74	3.26
1731.4	1732.6	1.2	VS076209	1.31	28	0.56	3.69
1732.6	1733.16	0.56	VS076210	1.135	26	0.62	3.49
1733.16	1734.2	1.04	VS076211	0.152	38.6	0.28	3.62
1734.2	1734.8	0.6	VS076213	0.003	19.4	0.005	3.16
1734.8	1735.55	0.75	VS076214	0.064	44.2	0.07	3.69
1735.55	1736.8	1.25	VS076215	0.148	12.8	0.13	2.94
1736.8	1738	1.2	VS076216	0.09	20.6	0.08	3.21
1738	1738.9	0.9	VS076217	0.054	14.25	0.09	3.21
1738.9	1739.6	0.7	VS076218	0.002	10.5	0.005	2.91
1739.6	1740.85	1.25	VS076219	1.505	8.14	0.44	2.90
1740.85	1741.8	0.95	VS076221	0.152	10.7	0.09	2.97
1741.8	1742.45	0.65	VS076222	0.136	17.15	0.09	3.11
1742.45	1743.5	1.05	VS076223	0.362	12.35	0.18	2.99
1743.5	1744.6	1.1	VS076224	0.064	35.3	0.04	4.09
1744.6	1745.2	0.6	VS076225	0.009	11.15	0.02	2.83
1745.2	1746.04	0.84	VS076227	0.437	54.5	0.08	4.56
1746.04	1746.65	0.61	VS076228	0.341	17.9	0.02	2.86

HOLE ID: VDD24036							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1746.65	1747.9	1.25	VS076230	0.075	7.92	0.02	2.90
1747.9	1748.3	0.4	VS076231	0.333	39.8	0.87	3.80
1748.3	1749.25	0.95	VS076232	0.296	11	0.18	2.94
1749.25	1750.3	1.05	VS076233	0.704	33.7	0.49	3.41
1750.3	1751.45	1.15	VS076234	0.545	13.05	0.3	3.00
1751.45	1752.55	1.1	VS076235	0.42	15.1	0.29	2.99
1752.55	1753.5	0.95	VS076237	0.639	45.4	0.52	3.96
1753.5	1754.3	0.8	VS076238	0.323	44.8	0.32	4.03
1754.3	1755.24	0.94	VS076239	0.253	39.2	0.25	3.95
1755.24	1756	0.76	VS076240	0.605	10.85	0.59	2.96
1756	1756.6	0.6	VS076241	0.379	9.75	0.32	4.47
1756.6	1757.08	0.48	VS076242	0.217	40.4	0.25	3.90
1757.08	1758.25	1.17	VS076243	0.032	5.45	0.06	2.86
1758.25	1759.4	1.15	VS076244	0.204	7.54	0.44	3.07
1759.4	1760.08	0.68	VS076245	0.015	8.13	0.02	2.93
1760.08	1760.8	0.72	VS076246	0.004	5.17	0.005	3.07
1760.8	1762.1	1.3	VS076248	0.256	7.54	0.31	2.93
1762.1	1763.25	1.15	VS076249	0.235	8.57	0.31	2.99
1763.25	1764	0.75	VS076250	0.058	27	0.08	3.50
1764	1764.4	0.4	VS076251	0.623	26.6	0.18	3.68
1764.4	1765.7	1.3	VS076252	0.152	7.9	0.04	2.99
1765.7	1766.7	1	VS076253	0.003	7.01	0.005	2.94
1766.7	1767.7	1	VS076254	0.067	18.6	0.04	3.19
1767.7	1768.4	0.7	VS076255	0.096	8.25	0.04	3.13
1768.4	1769.25	0.85	VS076256	0.131	7.76	0.05	2.88
1769.25	1770.3	1.05	VS076258	0.23	11.35	0.11	2.91
1770.3	1771.42	1.12	VS076259	0.533	4.76	0.2	2.95
1771.42	1772.45	1.03	VS076260	0.039	6.39	0.005	2.96
1772.45	1773.1	0.65	VS076261	0.152	5.21	0.04	2.96
1773.1	1774.3	1.2	VS076262	0.033	5.61	0.005	2.85
1774.3	1775.5	1.2	VS076263	0	4.02	0.005	2.97

HOLE ID: VDD25013D							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
672.5	674.8	2.30	VS077467	0.005	13.6	0.05	3.10
674.8	676.8	2.00	VS077468	0.01	13.7	0.04	3.18
676.8	679	2.20	VS077469	0.014	14.8	0.05	3.08
679	680.3	1.30	VS077470	0.015	12.1	0.05	3.08
680.3	683.1	2.80	VS077471	0.044	14.4	0.09	2.98
683.1	683.5	0.40	VS077472	0.006	12.5	0.03	2.95
683.5	686	2.50	VS077473	0.06	14.05	0.12	2.95
686	688	2.00	VS077474	0.025	14.2	0.04	2.91
688	690.7	2.70	VS077475	0.039	13.7	0.04	2.93
690.7	692	1.30	VS077476	0.008	14.7	0.02	2.93
692	694.05	2.05	VS077478	0.011	13.5	0.03	2.94
694.05	695.55	1.50	VS077479	0.034	15.9	0.06	2.89
695.55	697.5	1.95	VS077480	0.069	14.55	0.1	2.89
697.5	700	2.50	VS077481	0.016	14.2	0.03	2.83
700	703	3.00	VS077482	0.02	13.8	0.03	2.83
703	706	3.00	VS077483	0.019	14	0.03	2.83
706	708	2.00	VS077484	0.01	12.05	0.005	2.82
708	709.8	1.80	VS077485	0.045	13.35	0.06	2.97
709.8	711.7	1.90	VS077487	0.048	12.1	0.07	2.97
711.7	714	2.30	VS077488	0.068	15.8	0.09	3.11
714	716.8	2.80	VS077489	0.054	13.8	0.06	3.06
716.8	718.8	2.00	VS077490	0.011	11.95	0.02	3.06
718.8	719.95	1.15	VS077491	0.003	12	0.005	3.01
719.95	720.35	0.40	VS077492	0.01	10.65	0.03	3.02
720.35	721.75	1.40	VS077493	0.01	9.78	0.02	3.02
722.1	723.7	1.60	VS077494	0.041	11.7	0.04	3.03
723.7	725	1.30	VS077495	0.048	13.45	0.05	3.08
725	727.8	2.80	VS077497	0.039	8.32	0.04	3.08
727.8	730.25	2.45	VS077498	0.047	11.15	0.04	3.12
730.25	732.8	2.55	VS077499	0.021	7.45	0.03	3.01
732.8	734.5	1.70	VS077500	0.013	7.99	0.02	3.01
734.5	736.25	1.75	VS077501	0.02	9.53	0.03	2.9
736.25	738	1.75	VS077502	0.066	9.03	0.06	2.94
738	740.4	2.40	VS077503	0.051	9.35	0.06	2.94
740.4	742	1.60	VS077504	0.012	10.3	0.03	2.97
742	744.3	2.30	VS077506	0.036	11.45	0.06	3.26
744.3	745.8	1.50	VS077507	0.146	17.05	0.15	3.26
745.8	746.5	0.70	VS077508	0.45	27.9	0.35	3.54
746.5	747.05	0.55	VS077509	0.306	16.65	0.26	3.26
747.05	749.45	2.40	VS077510	0.193	13.4	0.16	3.26
749.45	751	1.55	VS077511	0.203	15.75	0.26	2.98
751	753.45	2.45	VS077512	0.136	17.3	0.19	2.98
753.45	754	0.55	VS077513	0.266	9.58	0.58	2.98
754	755	1.00	VS077514	0.292	10.35	0.78	2.97
755	756.1	1.10	VS077516	0.257	11.6	0.69	2.99
756.1	757	0.90	VS077517	0.065	13.8	0.27	2.99
757	758	1.00	VS077518	0.141	13	0.43	3

HOLE ID: VDD25013D							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
758	759	1.00	VS077519	0.176	13.3	0.58	3.00
759	760	1.00	VS077520	0.064	13.5	0.25	3.00
760	760.8	0.80	VS077521	0.087	13.95	0.33	3
760.8	761.85	1.05	VS077522	0.761	20.5	2.67	3.81
761.85	762.75	0.90	VS077523	1.93	38	6.13	4.62
762.75	764	1.25	VS077524	0.258	14.05	0.85	3.77
764	765	1.00	VS077526	0.053	11.45	0.21	3.77
765	766.3	1.30	VS077527	0.171	13.65	0.62	3.77
766.3	767.4	1.10	VS077528	0.032	12.6	0.13	2.91
767.4	768	0.60	VS077529	0.02	12.7	0.08	3.32
768	769.1	1.10	VS077530	0.08	16.15	0.28	3.32
769.1	769.65	0.55	VS077531	0.45	28.7	1.36	3.72
769.65	770	0.35	VS077532	0.862	28.9	1.96	3.8
770	771	1.00	VS077533	0.12	11.75	0.29	2.91
771	772	1.00	VS077534	0.192	10.15	0.47	3.06
772	773	1.00	VS077536	0.177	10.3	0.46	2.92
773	774	1.00	VS077537	0.166	11.9	0.36	3.02
774	775	1.00	VS077538	0.556	12.6	1.4	3.08
775	776.2	1.20	VS077539	0.682	12.95	1.61	3.37
776.2	777	0.80	VS077541	0.036	11.7	0.11	2.99
777	778	1.00	VS077542	0.114	10.3	0.24	3.03
778	779	1.00	VS077543	0.154	11.65	0.35	3.00
779	780	1.00	VS077544	0.26	10.65	0.68	2.96
780	781	1.00	VS077545	0.148	10.8	0.39	3.03
781	781.6	0.60	VS077547	0.111	11.3	0.27	3
781.6	782.8	1.20	VS077548	0.132	10.5	0.38	3.03
782.8	783.65	0.85	VS077549	0.693	10.55	1.62	3.12
783.65	784.5	0.85	VS077550	1.535	9.77	3.4	3.08
784.5	785	0.50	VS077551	1.695	11.05	3.83	3.1
785	786.3	1.30	VS077552	0.924	9.05	2.07	3.18
786.3	787	0.70	VS077553	2.92	10.65	6.32	3.07
787	788.1	1.10	VS077554	1.885	13.55	3.97	3.11
788.1	789	0.90	VS077555	0.322	12.6	0.66	3.11
789	789.65	0.65	VS077557	0.71	12.1	1.46	3.04
789.65	790	0.35	VS077558	0.671	12.25	1.42	3.08
790	791	1.00	VS077559	1.16	13.85	2.27	3.07
791	792	1.00	VS077560	0.981	13.65	1.8	3.11
792	793	1.00	VS077561	0.833	12.85	1.54	2.99
793	794	1.00	VS077562	1.325	10.25	2.24	3.02
794	795	1.00	VS077563	1.015	11.4	1.6	3.11
795	796	1.00	VS077564	0.89	15.45	1.48	3.17
796	796.55	0.55	VS077565	0.614	17.05	1.28	3.24
796.55	797	0.45	VS077567	0.18	13.95	0.35	2.99
797	798	1.00	VS077568	0.351	13.25	0.58	2.99
798	799	1.00	VS077569	0.024	10.7	0.07	3.13
799	800	1.00	VS077570	0.028	11.1	0.07	3.01
800	801	1.00	VS077571	0.161	11.85	0.36	2.95

HOLE ID: VDD25013D							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
801	802	1.00	VS077572	0.247	11.65	1.02	2.94
802	803	1.00	VS077573	0.312	11.9	0.59	3.06
803	804	1.00	VS077574	0.118	12	0.26	3.04
804	805	1.00	VS077575	0.173	12.3	0.33	3.06
805	805.85	0.85	VS077577	0.43	13.2	0.73	3.08
805.85	807	1.15	VS077578	0.881	11.65	1.46	3.11
807	807.85	0.85	VS077579	0.665	10.6	1.08	3.1
807.85	809	1.15	VS077580	0.12	11.45	0.22	3.05
809	809.6	0.60	VS077581	0.213	9.93	0.38	3.06
809.6	810	0.40	VS077582	0.648	11.75	1.04	3.02
810	811	1.00	VS077583	0.592	9.61	1.01	3.02
811	812	1.00	VS077584	0.574	12.95	0.97	2.97
812	813.3	1.30	VS077585	0.122	10.5	0.25	3.29
813.3	814	0.70	VS077587	0.06	10.4	0.11	3.01
814	814.8	0.80	VS077588	0.098	9.79	0.14	3.03
814.8	816	1.20	VS077589	0.034	8.64	0.07	3.07
816	817	1.00	VS077590	0.192	11.7	0.42	3.07
817	817.6	0.60	VS077591	0.038	9.79	0.08	3.1
817.6	818	0.40	VS077592	0.04	9.45	0.06	3.05
818	819.05	1.05	VS077636	0.066	10.45	0.09	3.05
819.05	820	0.95	VS077637	0.072	13.6	0.15	3
820	821	1.00	VS077638	0.16	15.45	0.23	3.02
821	822	1.00	VS077639	0.098	14.8	0.4	3.02
822	823	1.00	VS077640	0.097	14.65	0.21	3.04
823	823.7	0.70	VS077641	0.098	14.95	0.13	3.07
823.7	825	1.30	VS077642	0.112	15.3	0.19	3.07
825	826	1.00	VS077643	0.206	15.3	0.3	3.09
826	826.65	0.65	VS077644	0.142	12.5	0.21	3.13
826.65	827	0.35	VS077645	0.377	15.1	0.53	3.17
827	828	1.00	VS077647	0.047	15	0.08	3.12
828	829.05	1.05	VS077648	0.269	15.5	0.4	3.06
829.05	829.55	0.50	VS077649	1.645	29	2.78	3.58
829.55	830.8	1.25	VS077650	0.901	15.85	1.31	3.30
830.8	832	1.20	VS077651	0.176	13.3	0.27	3.01
832	833	1.00	VS077652	0.122	13.9	0.21	3.03
833	834	1.00	VS077653	0.221	12.4	0.4	3.01
834	835	1.00	VS077654	0.493	13.65	0.73	3.02
835	836	1.00	VS077655	0.236	12.55	0.36	2.97
836	836.95	0.95	VS077656	0.331	12.5	0.52	2.98
836.95	838	1.05	VS077658	0.322	13.3	0.48	3.01
838	839	1.00	VS077659	0.096	11.85	0.14	2.98
839	840	1.00	VS077660	0.269	12.7	0.42	3
840	840.55	0.55	VS077661	0.297	12.65	0.45	3.01
840.55	841	0.45	VS077662	0.897	11.5	1.26	3.01
841	842	1.00	VS077663	0.704	13.45	0.88	3.16
842	843	1.00	VS077664	0.276	12.5	0.34	3.02
843	844	1.00	VS077665	0.31	13.8	0.47	3.13

HOLE ID: VDD25013D							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
844	845	1.00	VS077666	1.125	12.55	1.32	3.08
845	846	1.00	VS077667	1.66	13.6	2.02	3.11
846	847	1.00	VS077669	1.37	10.25	1.62	2.99
847	848	1.00	VS077670	1.135	11.15	1.42	3.01
848	849	1.00	VS077671	0.854	13.35	1.06	3.1
849	850	1.00	VS077672	0.283	10.2	0.35	3.02
850	851	1.00	VS077673	0.589	11.5	0.69	3.05
851	852	1.00	VS077674	0.413	10.5	0.5	2.94
852	853	1.00	VS077675	1.575	12.4	1.84	3.26
853	854	1.00	VS077676	1.025	11.4	1.2	3.03
854	855	1.00	VS077677	1.17	14.9	1.3	3.08
855	856	1.00	VS077678	0.792	12.6	0.97	3.05
856	857	1.00	VS077680	0.633	12	0.77	3.03
857	858	1.00	VS077681	1.355	12.6	1.58	3.29
858	859	1.00	VS077682	0.249	10.75	0.32	3.04
859	860	1.00	VS077683	0.183	11.1	0.22	3.05
860	861	1.00	VS077684	0.274	12.45	0.36	3.05
861	862	1.00	VS077685	0.542	13.2	0.68	3.05
862	863	1.00	VS077686	0.285	11.2	0.41	3.09
863	863.65	0.65	VS077687	0.465	13.25	0.58	3.09
863.65	864	0.35	VS077688	1.745	14.6	2.14	3.13
864	865	1.00	VS077689	0.99	11.45	1.18	3
865	866	1.00	VS077691	0.787	11.4	1.02	3.05
866	867	1.00	VS077692	1.005	11.5	1.23	3.03
867	868	1.00	VS077693	0.183	10.45	0.27	3
868	868.95	0.95	VS077694	0.428	11.85	0.55	2.99
868.95	870	1.05	VS077695	1.26	15.95	1.8	3.16
870	871	1.00	VS077696	0.307	10.85	0.5	2.97
871	871.45	0.45	VS077697	0.841	9.54	1.08	3.01
871.45	872.1	0.65	VS077698	2.02	20.7	2.52	3.75
872.1	873.2	1.10	VS077699	0.481	11.7	0.55	2.98
873.2	874.1	0.90	VS077700	0.901	15.85	1.03	3
874.1	874.75	0.65	VS077702	0.864	13.6	1.07	2.97
874.75	876	1.25	VS077703	0.646	11.3	0.79	3
876	876.4	0.40	VS077704	2.66	12.75	3.14	3.07
876.4	877	0.60	VS077705	1.95	12	2.26	3.03
877	878	1.00	VS077706	1.055	12.1	1.23	2.94
878	879	1.00	VS077707	0.823	12.2	1.04	3.32
879	880	1.00	VS077708	0.759	15.9	0.9	3.05
880	881	1.00	VS077709	0.806	12.9	1.02	2.96
881	881.85	0.85	VS077710	0.584	11.1	0.75	3.03
881.85	883	1.15	VS077711	0.629	14.8	0.78	3.04
883	884	1.00	VS077713	0.44	10.95	0.52	3.03
884	885	1.00	VS077714	0.363	12.6	0.48	3.03
885	886.05	1.05	VS077715	0.358	13.75	0.54	3.01
886.05	886.7	0.65	VS077716	5.52	14.45	5.69	3.15
886.7	888	1.30	VS077717	0.386	12.35	0.4	3.02

HOLE ID: VDD25013D							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
888	889	1.00	VS077718	0.591	14.8	0.66	3.16
889	889.45	0.45	VS077719	0.524	11.5	0.59	2.98
889.45	890	0.55	VS077720	0.285	11.5	0.32	3.01
890	891	1.00	VS077721	0.575	13.8	0.75	3.03
891	892	1.00	VS077722	0.516	11.45	0.56	2.98
892	893	1.00	VS077724	0.47	13	0.52	3.1
893	894	1.00	VS077725	0.295	13.05	0.35	3.23
894	895	1.00	VS077726	0.854	15.2	1.1	2.96
895	896	1.00	VS077727	0.871	12.7	1.01	3.06
896	896.45	0.45	VS077728	0.411	12.05	0.44	3.01
896.45	897.2	0.75	VS077729	0.77	13.65	0.85	3.04
897.2	897.95	0.75	VS077730	1.515	13.1	1.54	3.18
897.95	899	1.05	VS077731	0.258	10.95	0.26	3.09
899	900	1.00	VS077732	0.161	11.55	0.36	3.09
900	901	1.00	VS077733	0.274	9.98	0.34	2.99
901	902	1.00	VS077735	0.666	11.95	0.77	3.00
902	903	1.00	VS077736	0.311	12.2	0.36	3.00
903	904	1.00	VS077737	0.322	11.4	0.37	3.01
904	905	1.00	VS077738	0.956	10.45	1.14	3.09
905	906	1.00	VS077739	0.444	10.75	0.57	3.09
906	907	1.00	VS077740	0.708	10.6	0.77	3.16
907	908	1.00	VS077741	0.166	11.15	0.19	3.12
908	909	1.00	VS077742	0.128	12.2	0.15	3.12
909	910	1.00	VS077743	0.081	12.15	0.09	3.07
910	911	1.00	VS077744	0.088	11.2	0.12	3.13
911	911.4	0.40	VS077746	0.285	11.7	0.43	3.13
911.4	912	0.60	VS077747	0.043	12.15	0.06	3.13
912	913	1.00	VS077748	0.064	12.35	0.1	3.19
913	914	1.00	VS077749	0.084	12.25	0.12	3.16
914	915	1.00	VS077750	0.1	12.55	0.12	3.16
915	916	1.00	VS077751	0.111	12.95	0.16	3.12
916	916.45	0.45	VS077752	0.072	13.15	0.1	3.08
916.45	917	0.55	VS077753	0.391	12.55	0.56	3.08
917	918	1.00	VS077754	0.149	12.6	0.21	3.03
918	918.9	0.90	VS077755	0.457	11.9	0.61	3.04
918.9	920	1.10	VS077757	0.388	14.8	0.46	3.04
920	921	1.00	VS077758	0.329	13.75	0.31	3.04
921	921.65	0.65	VS077759	0.84	16.75	0.94	2.96
921.65	922.45	0.80	VS077760	2.08	20.2	2.29	2.96
922.45	923	0.55	VS077761	0.352	8.84	0.49	2.87
923	924	1.00	VS077762	0.642	9.77	0.71	2.89
924	924.7	0.70	VS077763	1.37	13.25	1.34	2.99
924.7	926	1.30	VS077764	0.754	15.6	0.96	3.12
926	927	1.00	VS077765	0.759	18	0.82	3.14
927	928.2	1.20	VS077766	0.409	13	0.49	3.18
928.2	929	0.80	VS077768	0.872	9.31	0.94	2.88
929	930	1.00	VS077769	0.565	9.91	0.6	2.99

HOLE ID: VDD25013D							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
930	931	1.00	VS077770	0.988	7.61	1.11	2.97
931	932.3	1.30	VS077771	1.125	9.07	1.22	2.96
932.3	933	0.70	VS077772	0.576	10.1	0.64	3.02
933	934	1.00	VS077773	0.395	10.85	0.42	3.21
934	935	1.00	VS077774	0.432	12	0.44	3.19
935	936	1.00	VS077775	0.314	11.3	0.34	3.11
936	936.75	0.75	VS077776	0.376	13.95	0.42	3.17
936.75	938	1.25	VS077777	0.433	12.3	0.44	3.03
938	939	1.00	VS077779	0.379	9.99	0.45	2.97
939	940	1.00	VS077780	0.725	10.35	0.8	2.98
940	941	1.00	VS077781	0.212	9.76	0.22	2.98
941	942	1.00	VS077782	0.588	13.9	0.63	3.31
942	943	1.00	VS077783	0.622	9.61	0.64	3
943	943.85	0.85	VS077784	1.13	9.89	1.26	3.03
943.85	945	1.15	VS077785	0.264	9.36	0.3	3.02
945	946	1.00	VS077786	0.119	10.45	0.11	3.01
946	947	1.00	VS077787	0.5	13	0.54	3.01
947	947.45	0.45	VS077788	0.285	10.95	0.29	3.01
947.45	948	0.55	VS077790	0.645	10.3	0.69	3.01
948	949	1.00	VS077791	0.656	12.7	0.72	3.08
949	949.75	0.75	VS077792	0.363	16.95	0.4	3.08
949.75	951	1.25	VS077793	0.174	14.3	0.19	3.14
951	951.85	0.85	VS077794	0.403	9.67	0.45	3.09
951.85	953	1.15	VS077795	0.42	10.8	0.44	3.03
953	954	1.00	VS077796	0.83	10.85	0.87	3.08
954	955	1.00	VS077797	0.576	13.6	0.65	3.08
955	956	1.00	VS077798	0.47	12.55	0.52	3.12
956	956.7	0.70	VS077799	0.126	10.95	0.13	3.05
956.7	957.4	0.70	VS077801	0.136	10.05	0.16	2.97
957.4	958	0.60	VS077802	0.943	20.8	0.94	3.45
958	959.15	1.15	VS077803	1.395	15	1.3	3
959.15	960	0.85	VS077804	1.29	14.9	1.36	3.32
960	961	1.00	VS077805	0.79	12.3	0.83	2.99
961	962	1.00	VS077806	0.222	11.85	0.2	3.06
962	963	1.00	VS077807	1.205	11.8	1.2	2.99
963	964	1.00	VS077808	0.392	9.1	0.41	3.02
964	965	1.00	VS077809	1.775	14.05	1.74	3.06
965	966	1.00	VS077810	1.495	13.25	1.36	3.58
966	967	1.00	VS077812	0.434	9.99	0.43	3.02
967	968.1	1.10	VS077813	0.198	9.93	0.19	2.99
968.1	969	0.90	VS077814	0.529	9.3	0.52	3
969	969.75	0.75	VS077815	1.035	10.55	0.96	2.99
969.75	971	1.25	VS077816	0.557	10.05	0.55	2.94
971	972.3	1.30	VS077817	0.389	8.05	0.35	2.98
972.3	973.2	0.90	VS077818	0.326	9.63	0.28	3.06
973.2	974.25	1.05	VS077819	0.72	10.4	0.63	3.13
974.25	975.2	0.95	VS077820	1.95	10.8	1.72	3.07

HOLE ID: VDD25013D							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
975.2	976	0.80	VS077821	0.953	12.9	0.74	3.05
976	977.3	1.30	VS077823	0.692	9.91	0.64	3.01
977.3	978.6	1.30	VS077824	0.945	12.7	0.8	3.02
978.6	979.9	1.30	VS077825	0.406	10.1	0.35	3.02
979.9	981.2	1.30	VS077826	0.546	11.6	0.45	3.00
981.2	982.5	1.30	VS077827	0.555	9.87	0.52	3.00
982.5	983.8	1.30	VS077828	0.319	10.55	0.32	2.98
983.8	985.1	1.30	VS077829	0.15	10.9	0.12	2.99
985.1	986.4	1.30	VS077830	0.459	9.94	0.41	3
986.4	987.7	1.30	VS077831	0.565	9.96	0.53	3.01
987.7	989	1.30	VS077832	0.327	11.2	0.3	3.01
989	990.3	1.30	VS077834	0.763	15.05	0.72	3.01
990.3	991.6	1.30	VS077835	0.269	11.7	0.23	3.02
991.6	992.9	1.30	VS077836	0.688	10.95	0.59	3.02
992.9	993.85	0.95	VS077837	0.196	10.9	0.19	3.03
993.85	995.15	1.30	VS077838	0.499	10.35	0.43	2.97
995.15	996.45	1.30	VS077839	0.298	10.7	0.26	3.06
996.45	997.75	1.30	VS077840	0.793	11.6	0.69	3.01
997.75	998.85	1.10	VS077841	1.225	8.39	1.16	2.91
998.85	1000.15	1.30	VS077842	0.372	11.2	0.39	3.01
1000.15	1001.45	1.30	VS077843	0.352	12.2	0.32	3.06
1001.45	1002.75	1.30	VS077845	0.493	11.9	0.49	3.02
1002.75	1004.05	1.30	VS077846	0.597	12.35	0.58	3.02
1004.05	1005.35	1.30	VS077847	0.759	11.2	0.72	3.04
1005.35	1006.4	1.05	VS077848	0.761	11.65	0.74	3.02
1006.4	1007.3	0.90	VS077849	0.801	12.9	0.69	3.01
1007.3	1008.6	1.30	VS077850	0.846	12.25	0.75	3
1008.6	1009.9	1.30	VS077851	0.742	10.35	0.75	3.00
1009.9	1011.2	1.30	VS077852	0.745	11.3	0.78	3.00
1011.2	1012.5	1.30	VS077853	0.088	12.2	0.09	2.99
1012.5	1013.8	1.30	VS077854	0.073	12.55	0.08	3.00
1013.8	1014.9	1.10	VS077856	0.172	13.45	0.19	3.00
1014.9	1016.05	1.15	VS077857	0.162	12.4	0.16	3.01
1016.05	1017.3	1.25	VS077858	0.338	12.2	0.28	3.01
1017.3	1018.6	1.30	VS077859	0.852	12.1	0.69	3.01
1018.6	1019.9	1.30	VS077860	0.353	11.4	0.33	3
1019.9	1021.2	1.30	VS077861	0.498	10.75	0.39	2.99
1021.2	1022.5	1.30	VS077862	0.636	11.75	0.52	2.99
1022.5	1023.8	1.30	VS077863	0.783	10.95	0.63	2.98
1023.8	1024.7	0.90	VS077864	0.372	12.15	0.33	2.99
1024.7	1025.6	0.90	VS077865	0.258	12.2	0.24	2.99
1025.6	1026.9	1.30	VS077867	1.07	12.9	0.88	2.99
1026.9	1028.2	1.30	VS077868	0.963	13.2	0.83	3.12
1028.2	1029.5	1.30	VS077869	1.085	12.3	0.87	2.97
1029.5	1030.8	1.30	VS077870	1.495	11.65	1.29	3.03
1030.8	1032.1	1.30	VS077871	1.42	10.15	1.25	3.09
1032.1	1033.4	1.30	VS077872	1.275	9.92	1.27	3.05

HOLE ID: VDD25013D							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1033.4	1034.7	1.30	VS077873	0.439	9.06	0.38	2.93
1034.7	1035.65	0.95	VS077874	0.801	10.85	0.66	3.07
1035.65	1036.95	1.30	VS077875	1.875	11.3	1.46	3.09
1036.95	1038.25	1.30	VS077876	0.407	10.95	0.31	3
1038.25	1039.55	1.30	VS077878	0.267	11.25	0.21	3.03
1039.55	1040.85	1.30	VS077879	1.455	11.2	1.21	3.08
1040.85	1042.15	1.30	VS077880	1.405	13.1	1.04	3.07
1042.15	1043.2	1.05	VS077881	0.408	12.25	0.34	3.02
1043.2	1044.1	0.90	VS077882	0.636	11.5	0.57	3.05
1044.1	1044.95	0.85	VS077883	0.303	11.65	0.3	3
1044.95	1046.25	1.30	VS077884	0.313	11.65	0.29	2.99
1046.25	1047.55	1.30	VS077885	0.278	11.4	0.25	2.99
1047.55	1048.85	1.30	VS077886	0.227	10.2	0.22	2.98
1048.85	1049.8	0.95	VS077887	0.309	10.65	0.29	3.01
1049.8	1051.1	1.30	VS077889	1.635	12.65	1.38	3.04
1051.1	1052.4	1.30	VS077890	1.33	11.75	1.17	3
1052.4	1053.7	1.30	VS077891	0.569	11.05	0.55	3.09
1053.7	1054.9	1.20	VS077892	0.259	10.5	0.26	3.06
1054.9	1056.2	1.30	VS077893	0.296	11.3	0.32	2.97
1056.2	1057.5	1.30	VS077894	0.265	11.85	0.27	3.02
1057.5	1058.5	1.00	VS077895	0.358	12.25	0.32	3.06
1058.5	1059.5	1.00	VS077896	0.454	11.3	0.38	3.04
1059.5	1060.35	0.85	VS077897	0.255	11.9	0.25	3.04
1060.35	1061.65	1.30	VS077898	0.495	13.25	0.47	3.02
1061.65	1062.6	0.95	VS077900	1.35	13.85	1.25	3.23
1062.6	1063.55	0.95	VS077901	1.47	13.85	1.24	3.17
1063.55	1064.85	1.30	VS077902	0.16	12.25	0.15	2.98
1064.85	1066.15	1.30	VS077903	0.062	11.6	0.06	2.97
1066.15	1067.45	1.30	VS077904	0.296	13.55	0.27	2.97
1067.45	1068.75	1.30	VS077905	0.104	15.95	0.1	2.96
1068.75	1069.9	1.15	VS077906	0.261	14.25	0.23	3.01
1069.9	1070.6	0.70	VS077907	1.05	14.2	1.04	3.05
1070.6	1071.3	0.70	VS077908	0.874	15.7	0.88	3.27
1071.3	1072.6	1.30	VS077909	0.325	13.25	0.36	3.05
1072.6	1073.9	1.30	VS077911	0.09	16.55	0.1	3.05
1073.9	1075.2	1.30	VS077912	0.043	14.8	0.07	3.05
1075.2	1076.5	1.30	VS077913	0.326	12.85	0.38	3.05
1076.5	1077.8	1.30	VS077914	0.088	11.85	0.14	3.02
1077.8	1078.95	1.15	VS077915	0.164	13.8	0.28	3.02
1078.95	1080	1.05	VS077916	0.821	13	1.24	2.98
1080	1081.05	1.05	VS077917	0.495	12.85	0.84	3.09
1081.05	1082.35	1.30	VS077918	0.135	12.15	0.15	2.98
1082.35	1083.65	1.30	VS077919	0.094	13.25	0.12	3.05
1083.65	1084.95	1.30	VS077920	0.228	12.9	0.3	3.11
1084.95	1085.9	0.95	VS077922	0.172	13.85	0.28	3.11
1085.9	1086.9	1.00	VS077923	0.317	12.05	0.38	3.11
1086.9	1087.8	0.90	VS077924	0.393	13.05	0.48	3.1

HOLE ID: VDD25013D							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1087.8	1088.75	0.95	VS077925	0.193	14.1	0.21	3.02
1088.75	1090.05	1.30	VS077926	0.102	16.65	0.18	3.07
1090.05	1091.35	1.30	VS077927	0.079	14.75	0.12	3.09
1091.35	1092.6	1.25	VS077928	0.034	14.3	0.07	3.07
1092.6	1093.9	1.30	VS077929	0.427	11.4	0.78	3.06
1093.9	1094.9	1.00	VS077930	0.736	10.65	1.35	2.97
1094.9	1096.2	1.30	VS077931	0.184	13	0.38	3.06
1096.2	1097.4	1.20	VS077933	0.176	15.05	0.35	3.08
1097.4	1098.55	1.15	VS077934	0.471	15.55	0.72	3.15
1098.55	1099.85	1.30	VS077935	0.427	26.2	0.96	3.73
1099.85	1101	1.15	VS077936	0.28	15.6	0.52	3.01
1101	1102.3	1.30	VS077937	0.027	13	0.08	3.07
1102.3	1103.6	1.30	VS077938	0.028	13.65	0.05	3.03
1103.6	1104.9	1.30	VS077939	0.126	12.85	0.2	3.03
1104.9	1106.2	1.30	VS077940	0.043	13.6	0.09	2.99
1106.2	1107.5	1.30	VS077941	0.041	10.9	0.07	2.96
1107.5	1108.8	1.30	VS077942	0.041	11.2	0.08	2.96
1108.8	1110.1	1.30	VS077944	0.041	8.26	0.09	2.92
1110.1	1111.4	1.30	VS077945	0.051	9.36	0.1	2.93
1111.4	1112.7	1.30	VS077946	0.028	9.77	0.07	2.93
1112.7	1114	1.30	VS077947	0.017	8.89	0.03	2.94
1114	1115.3	1.30	VS077948	0.026	8.41	0.03	2.95
1115.3	1116.6	1.30	VS077949	0.017	8.32	0.03	2.95
1116.6	1117.9	1.30	VS077950	0.018	8.83	0.05	2.95
1117.9	1119	1.10	VS077951	0.025	9.66	0.06	2.96
1119	1120.3	1.30	VS077952	0.066	9.53	0.08	3.00
1120.3	1121.6	1.30	VS077953	0.098	11.3	0.08	3.03
1121.6	1122.6	1.00	VS077955	0.049	9.07	0.05	2.99
1122.6	1123.6	1.00	VS077956	0.026	7.96	0.07	2.99
1123.6	1124.6	1.00	VS077957	0.219	8.88	0.46	2.94
1124.6	1125.65	1.05	VS077958	0.666	10.75	2.13	2.98
1125.65	1126.75	1.10	VS077959	1.72	15.7	5.42	3.13
1126.75	1128.05	1.30	VS077960	0.15	6.02	0.34	2.89
1128.05	1129.35	1.30	VS077961	0.041	6.21	0.14	2.86
1129.35	1130.65	1.30	VS077962	0.23	6.25	0.56	2.86
1130.65	1131.95	1.30	VS077963	0.18	6.08	0.53	2.83
1131.95	1133.25	1.30	VS077964	0.18	7.82	0.55	2.90
1133.25	1134.55	1.30	VS077966	0.02	8.17	0.05	2.90
1134.55	1135.6	1.05	VS077967	0.084	11.3	0.25	2.97
1135.6	1136.7	1.10	VS077968	0.218	11.55	0.66	2.95
1136.7	1138	1.30	VS077969	0.065	6.57	0.11	2.95
1138	1139.2	1.20	VS077970	0.022	10.45	0.05	2.92

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
672.5	674.8	2.3	VS077467	0.005	13.6	0.05	3.1
681.75	683.5	1.75	VS063376	0.012	9.79	0.03	2.96
683.5	685.55	2.05	VS063377	0.015	9.57	0.05	2.96
685.55	685.95	0.4	VS063378	0.486	19.9	1.38	2.77
685.95	687.85	1.9	VS063379	0.028	10.4	0.09	2.77
687.85	689.45	1.6	VS063380	0.008	7.46	0.03	2.77
689.45	691.15	1.7	VS063381	0.003	2.44	0.27	2.58
691.15	693.6	2.45	VS063382	0.049	6.91	0.06	2.7
693.6	695.3	1.7	VS063383	0.096	6.23	0.11	2.7
695.3	697.3	2	VS063384	0.064	5.79	0.06	2.7
697.3	698.4	1.1	VS063385	0.734	13.15	1.18	2.7
698.4	700.25	1.85	VS063387	0.25	8.4	0.29	2.7
700.25	702.8	2.55	VS063388	0.088	5.91	0.12	2.81
702.8	705.2	2.4	VS063389	0.076	6.07	0.11	2.95
705.2	707.98	2.78	VS063390	0.027	5.72	0.05	2.95
707.98	709.75	1.77	VS063391	0.007	6.23	0.02	2.95
709.75	710.3	0.55	VS063392	0.006	9.57	0.03	2.95
710.3	712.9	2.6	VS063393	0.056	12.7	0.1	3.09
712.9	714.95	2.05	VS063394	0.043	11.45	0.12	3.05
714.95	717.45	2.5	VS063395	0.048	11.85	0.11	3.05
717.45	719.95	2.5	VS063396	0.099	10.9	0.19	3.01
719.95	721.45	1.5	VS063398	0.024	6.88	0.04	3.01
721.45	723.55	2.1	VS063399	0.048	6.85	0.07	3.01
723.55	726.35	2.8	VS063400	0.036	10.15	0.06	3
726.35	728.2	1.85	VS063401	0.027	9.31	0.05	2.94
728.2	729.85	1.65	VS063402	0.027	14.95	0.05	2.94
729.85	731.25	1.4	VS063403	0.042	13.2	0.16	2.94
731.25	733	1.75	VS063404	0.007	8.51	0.03	2.94
733	733.75	0.75	VS063405	0.132	8.55	0.24	2.94
733.75	735.5	1.75	VS063407	0.006	7.99	0.02	2.88
735.5	737.1	1.6	VS063408	0.012	7.6	0.02	2.9
737.1	737.95	0.85	VS063409	0.087	14.9	0.26	2.9
737.95	739.45	1.5	VS063685	0.122	13.4	0.29	2.9
739.45	740.45	1	VS063686	0.061	12	0.11	2.9
740.45	741.3	0.85	VS063687	0.128	13.3	0.27	2.9
741.3	742.85	1.55	VS063688	0.028	5.38	0.04	2.9
742.85	744.7	1.85	VS063689	0.015	6.89	0.03	2.92
744.7	746.4	1.7	VS063690	0.004	7.09	0.03	2.89
746.4	748.35	1.95	VS063691	0.007	7.58	0.03	2.89
748.35	750.3	1.95	VS063692	0.004	7.47	0.005	2.89
750.3	752.15	1.85	VS063693	0.004	7.95	0.005	2.86
752.15	754.5	2.35	VS063694	0.004	7.08	0.005	2.85
754.5	757.37	2.87	VS063696	0.002	7.24	0.005	2.85
757.37	760.2	2.83	VS063697	0.003	6.85	0.03	2.84
760.2	763	2.8	VS063698	0.017	7.03	0.05	2.81
763	765.28	2.28	VS063699	0.045	5.81	0.09	2.81
765.45	765.85	0.4	VS063700	0.018	4.54	0.06	2.81

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
765.85	767.05	1.2	VS063701	0.237	15.15	0.77	2.81
767.05	769.75	2.7	VS063702	0.557	12.4	1.22	2.77
769.75	771.55	1.8	VS063703	0.15	5.59	0.35	2.81
771.55	774	2.45	VS063704	0.004	7.63	0.02	2.81
774	776.55	2.55	VS063705	0.002	6.69	0.02	2.81
776.55	779.12	2.57	VS063707	0.004	6.4	0.04	2.85
779.12	781.3	2.18	VS063708	0.003	7.03	0.02	2.97
781.3	782.82	1.52	VS063709	0.005	7.44	0.04	2.97
782.82	784.64	1.82	VS063710	0.009	6.79	0.03	2.97
784.64	786.15	1.51	VS063711	0.013	7.78	0.06	2.97
786.15	787.35	1.2	VS063712	0.039	13.1	0.12	2.97
787.35	790	2.65	VS063713	0.055	10.3	0.12	3.08
790	792.67	2.67	VS063714	0.026	9.48	0.07	2.96
792.88	794.47	1.59	VS063715	0.011	11.05	0.06	2.96
794.47	795.85	1.38	VS063716	0.018	7.39	0.07	2.83
795.85	796.4	0.55	VS063717	0.008	6.99	0.04	2.85
796.4	798.7	2.3	VS063719	0.033	7.36	0.08	2.85
798.7	801.05	2.35	VS063720	0.008	7.88	0.03	2.85
801.05	803.35	2.3	VS063721	0.004	7.58	0.03	2.85
803.35	806.28	2.93	VS063722	0.009	7.42	0.04	2.86
806.28	807.46	1.18	VS063723	0.006	8.07	0.04	2.86
807.46	810.39	2.93	VS063724	0.018	7.96	0.05	2.86
810.39	813.14	2.75	VS063725	0.002	7.88	0.03	2.86
813.14	815.96	2.82	VS063726	0.002	7.95	0.03	2.86
815.96	818.6	2.64	VS063727	0.001	7.5	0.02	2.86
818.6	821.6	3	VS063728	0.009	7.58	0.09	2.86
821.6	824.6	3	VS063730	0.006	7.29	0.04	2.86
824.6	825.7	1.1	VS063731	0	8.24	0.02	2.89
825.7	828.65	2.95	VS063732	0.001	8.66	0.03	2.89
828.65	831.35	2.7	VS063733	0.003	7.58	0.02	2.91
831.35	834.3	2.95	VS063734	0.003	7.85	0.02	2.93
834.3	836.58	2.28	VS063735	0.007	7.69	0.05	2.93
836.58	838.93	2.35	VS063736	0.006	7.79	0.04	2.94
838.93	841	2.07	VS063737	0.02	8.56	0.07	2.92
841	842.2	1.2	VS063738	1.27	9.85	2.61	2.92
842.2	843.4	1.2	VS063739	0.673	10.3	1.43	2.92
843.4	845.2	1.8	VS063741	0.058	8.26	0.14	2.92
845.2	847.2	2	VS063742	0.009	8.45	0.03	2.89
847.2	849.2	2	VS063743	0.027	8.31	0.1	2.87
849.2	852.1	2.9	VS063744	0.042	8.47	0.15	2.87
852.1	854	1.9	VS063745	0.012	7.19	0.04	2.87
854	854.74	0.74	VS063746	1.665	11.6	1.63	2.87
854.74	856.3	1.56	VS063747	0.033	7.33	0.07	2.87
856.3	858.15	1.85	VS063748	0.02	7.49	0.06	2.84
858.15	860.15	2	VS063749	0.038	8.34	0.1	2.89
860.15	862.15	2	VS063750	0.004	7.86	0.04	2.89
862.15	864.22	2.07	VS063752	0.002	8.15	0.03	2.93

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
864.22	866.15	1.93	VS063753	0.01	8.16	0.04	2.92
866.15	868.15	2	VS063754	0.013	8.16	0.07	2.92
868.15	870.15	2	VS063755	0.009	8.72	0.05	2.92
870.15	872.15	2	VS063756	0.033	8.4	0.11	2.92
872.15	874.18	2.03	VS063757	0.03	8.72	0.08	2.9
874.18	876.52	2.34	VS063758	0.012	7.75	0.06	2.9
876.52	878.55	2.03	VS063759	0.009	8.09	0.06	2.9
878.55	879.7	1.15	VS063760	0.029	11.3	0.08	2.9
879.7	881.15	1.45	VS063762	0.049	9.37	0.15	2.9
881.15	881.95	0.8	VS063763	0.369	12	0.98	2.9
881.95	882.75	0.8	VS063764	0.11	7.88	0.35	2.9
882.75	883.5	0.75	VS063765	1.605	10.6	3.74	2.9
883.5	885.1	1.6	VS063767	0.207	6.58	0.46	2.9
885.1	887	1.9	VS063768	0.187	6.17	0.51	2.9
887	888.6	1.6	VS063769	0.067	5.51	0.19	2.89
888.6	890.55	1.95	VS063770	0.087	7.85	0.33	2.91
890.55	892.55	2	VS063771	0.03	7.62	0.16	2.95
892.55	893.78	1.23	VS063772	0.037	7.91	0.14	2.95
893.78	894.3	0.52	VS063774	2.35	9.66	13.75	2.95
894.3	895.85	1.55	VS063775	0.02	8.1	0.09	2.95
895.85	897.25	1.4	VS063776	0.007	7.71	0.04	2.95
897.25	899.35	2.1	VS063777	0.028	7.83	0.11	2.95
899.35	900.7	1.35	VS063778	0.045	8.31	0.16	2.95
900.7	902.17	1.47	VS063779	0.002	7.9	0.03	2.95
902.17	903.15	0.98	VS063780	2.14	8.93	6.5	2.95
903.15	905	1.85	VS063782	0.069	8.05	0.26	2.98
905	906.9	1.9	VS063783	0.075	7.72	0.23	2.95
906.9	907.97	1.07	VS063851	0.035	7.81	0.15	2.95
907.97	908.95	0.98	VS063852	0.32	6.89	1.2	2.95
908.95	910	1.05	VS063853	0.01	7.59	0.08	2.91
910	910.8	0.8	VS063854	0.056	7.33	0.19	2.97
910.8	911.63	0.83	VS063855	0.343	8.37	1.38	2.88
911.63	913.13	1.5	VS063856	0.214	5.01	0.8	2.79
913.13	914.45	1.32	VS063857	0.15	6.07	0.7	2.87
914.45	917.33	2.88	VS063858	0.188	7.61	0.68	2.95
917.33	920.2	2.87	VS063859	0.036	3.66	0.16	2.92
920.2	921.29	1.09	VS063860	0.216	4.99	1.02	2.88
921.29	922.29	1	VS063862	0.876	14.4	3.51	2.96
922.29	923.29	1	VS063863	0.383	8.6	1.7	2.96
923.29	924.31	1.02	VS063864	0.503	6.58	2.2	2.96
924.31	925.35	1.04	VS063865	0.188	9.04	0.78	3.03
925.35	926.33	0.98	VS063866	0.481	9.89	1.54	2.89
926.33	927.33	1	VS063867	0.131	5.05	0.52	2.89
927.33	928.35	1.02	VS063868	0.042	3.74	0.19	2.74
928.35	929.61	1.26	VS063869	0.729	8	2.89	2.85
929.61	930.88	1.27	VS063870	0.818	9.09	3.02	2.95
930.88	932.57	1.69	VS063872	0.051	4.58	0.2	2.73

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
932.57	934.19	1.62	VS063873	0.268	3.95	0.93	2.82
934.19	935.27	1.08	VS063874	0.378	5.22	1.4	2.82
935.27	936.33	1.06	VS063875	0.128	4.87	0.51	2.82
936.33	937.41	1.08	VS063876	0.19	5.39	0.77	2.91
937.41	938.56	1.15	VS063877	0.604	5.58	2.22	2.9
938.56	939.67	1.11	VS063878	0.4	5.58	1.42	2.9
939.67	940.71	1.04	VS063879	0.126	4.23	0.35	2.9
940.71	941.8	1.09	VS063880	0.049	5.32	0.15	2.9
941.8	942.83	1.03	VS063882	0.573	8.17	1.8	2.9
942.83	943.75	0.92	VS063883	0.37	7.83	1.01	2.9
943.75	944.7	0.95	VS063884	0.372	11.8	1.19	2.9
944.7	945.6	0.9	VS063885	0.106	6.11	0.42	2.9
945.6	946.5	0.9	VS063886	0.439	9.14	1.4	2.9
946.5	947.54	1.04	VS063887	0.708	14.25	2.38	2.9
947.54	948.73	1.19	VS063889	0.893	14.3	3.06	4.52
948.73	949.92	1.19	VS063890	0.737	12.9	2.55	2.9
949.92	951.11	1.19	VS063891	0.841	12.3	2.4	2.9
951.11	952.24	1.13	VS063892	0.499	13.35	1.08	2.9
952.24	953.41	1.17	VS063893	0.093	13.6	0.2	2.9
953.41	954.52	1.11	VS063894	0.029	11.8	0.08	2.9
954.52	955.65	1.13	VS063895	0.01	12.55	0.05	3.17
955.65	956.79	1.14	VS063896	0.023	12.95	0.36	2.99
956.79	957.93	1.14	VS063897	0.078	12.3	0.29	2.99
957.93	958.9	0.97	VS063898	0.039	9.05	0.22	2.81
958.9	960	1.1	VS063900	0.042	6.56	0.55	2.7
960	960.68	0.68	VS063901	0.032	6.96	0.1	2.74
960.68	961.12	0.44	VS063902	0.008	6.45	0.86	2.76
961.12	961.91	0.79	VS063903	0.053	5.2	3.97	2.76
961.91	962.7	0.79	VS063904	0.038	7.75	2.24	2.76
963.2	964.04	0.84	VS063905	0.34	11.55	0.66	2.76
964.04	964.88	0.84	VS063907	0.116	9.67	0.15	2.76
964.88	966	1.12	VS063908	0.038	6.68	0.08	2.81
966	967.14	1.14	VS063909	0.004	7.79	0.005	2.85
967.14	968.25	1.11	VS063910	0.029	10.9	0.04	2.85
968.25	969.4	1.15	VS063911	0.001	7.58	0.005	2.85
969.4	970.53	1.13	VS063912	0.002	8.62	0.005	2.85
970.53	971.66	1.13	VS063913	0.002	8.89	0.03	2.85
971.66	972.8	1.14	VS063914	0.001	7.01	0.04	2.85
972.8	973.78	0.98	VS063915	0.021	9.07	0.05	2.89
973.78	974.69	0.91	VS063916	0.025	10.85	0.12	3.06
974.69	975.64	0.95	VS063917	0.02	11	0.08	3.06
975.64	976.93	1.29	VS063919	0.046	13.3	0.07	3.06
976.93	978.23	1.3	VS063920	0.165	11.65	0.18	3.23
978.23	979.41	1.18	VS063921	0.043	14.55	0.05	3.22
979.41	980.45	1.04	VS063922	0.039	13.1	0.06	3.22
980.45	981.55	1.1	VS063923	0.015	10.3	0.03	3.2
981.55	982.66	1.11	VS063924	0.012	14.25	0.03	3.33

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
982.66	983.77	1.11	VS063925	0.054	12.75	0.05	3.33
983.77	984.84	1.07	VS063926	0.06	15.4	0.07	3.33
984.84	985.98	1.14	VS063927	0.021	15.45	0.05	3.33
985.98	987.09	1.11	VS063928	0.001	10.95	0.02	3.33
987.09	987.77	0.68	VS063929	0.692	22	0.41	3.46
987.77	988.45	0.68	VS063931	0.106	16.05	0.11	3.29
988.45	989.6	1.15	VS063932	0.057	12.5	0.06	3.12
989.6	990.83	1.23	VS063933	0.057	15.5	0.04	3.15
990.83	991.98	1.15	VS063934	0.012	15	0.03	3.15
991.98	993.05	1.07	VS063935	0.092	12.9	0.11	3.15
993.05	994.2	1.15	VS063936	0.14	15.8	0.18	3.15
994.2	995.3	1.1	VS063938	0.169	14.25	0.23	3.15
995.3	996.42	1.12	VS063939	0.038	16	0.05	3.15
996.42	997.53	1.11	VS063940	0.009	15.45	0.02	3.2
997.53	998.64	1.11	VS063941	0.08	14.5	0.06	3.15
998.64	999.75	1.11	VS063942	0.02	14.2	0.05	3.15
999.75	1000.85	1.1	VS063943	0.03	14	0.04	3.15
1000.85	1001.97	1.12	VS063945	0.271	13.5	0.21	3.1
1001.97	1003.09	1.12	VS063946	0.697	18.85	0.71	3.35
1003.09	1004.22	1.13	VS063947	1.055	13.25	1.22	3.18
1004.22	1005.33	1.11	VS063948	0.615	12.85	0.63	3.02
1005.33	1006.47	1.14	VS063949	0.625	13.55	0.71	3.34
1006.47	1007.57	1.1	VS063950	0.845	13.35	0.96	3.24
1007.57	1008.69	1.12	VS063951	0.417	14.5	0.46	2.97
1008.69	1009.81	1.12	VS063953	0.472	11.75	0.58	3.07
1009.81	1010.88	1.07	VS063954	2.25	13	2.55	3.21
1010.88	1011.91	1.03	VS063955	2.51	22	3.61	3.16
1011.91	1013.04	1.13	VS063956	1.1	17.5	1.4	3.41
1013.04	1014.12	1.08	VS063957	0.961	20.3	1.24	3.44
1014.12	1015.2	1.08	VS063959	1.18	17.7	1.51	3.31
1015.2	1016.28	1.08	VS063960	1.3	18.15	1.82	3.29
1016.28	1017.32	1.04	VS063961	0.047	13.4	0.04	3.13
1017.32	1018.36	1.04	VS063962	0.13	13.8	0.19	3.18
1018.36	1019.39	1.03	VS063963	0.156	14.25	0.18	2.96
1019.39	1020.43	1.04	VS063965	0.118	13.95	0.18	2.99
1020.43	1021.47	1.04	VS063966	0.192	12.7	0.2	3.05
1021.47	1022.51	1.04	VS063967	0.116	12.8	0.15	2.92
1022.51	1023.55	1.04	VS063968	0.158	12.8	0.15	3.04
1023.55	1024.69	1.14	VS063970	0.521	9.53	0.54	3.33
1024.69	1025.76	1.07	VS063971	0.576	28.8	0.62	3.68
1025.76	1026.873	1.113	VS063972	0.688	20	0.7	3.13
1026.873	1028	1.127	VS063973	0.255	13.7	0.32	3.09
1028	1029.05	1.05	VS063974	0.231	14.85	0.3	3.06
1029.05	1030.13	1.08	VS063975	0.068	13.4	0.29	3.18
1030.13	1031.23	1.1	VS063976	0.023	13.7	0.04	3.15
1031.23	1032.31	1.08	VS063978	0.01	14.6	0.02	3.12
1032.31	1033.39	1.08	VS063979	0.028	13.5	0.04	3.1

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1033.39	1034.51	1.12	VS063980	0.099	12.5	0.12	3.08
1034.51	1035.57	1.06	VS063981	0.071	13.95	0.11	3.12
1035.57	1036.66	1.09	VS063982	0.12	14.75	0.18	3.17
1036.66	1037.79	1.13	VS063984	0.577	15.8	0.59	3.22
1037.79	1038.8	1.01	VS063985	0.611	15.2	0.59	3.16
1038.8	1039.81	1.01	VS063986	0.478	19.2	0.52	3.39
1039.81	1040.94	1.13	VS063987	0.028	11.65	0.04	2.96
1040.94	1042.1	1.16	VS063988	0.05	13.7	0.03	3.04
1042.1	1043.13	1.03	VS063989	0.033	11.7	0.03	2.99
1043.13	1044.29	1.16	VS063991	0.018	14.35	0.02	3.23
1044.29	1045.38	1.09	VS063992	0.018	12.8	0.02	2.93
1045.38	1046.38	1	VS063993	0.016	8.55	0.005	3.05
1046.38	1047.42	1.04	VS063994	0.018	10.15	0.005	3.1
1047.42	1048.35	0.93	VS063995	0.029	9.92	0.05	3.28
1048.35	1049.39	1.04	VS063996	0.021	10.75	0.04	3.35
1049.39	1050.26	0.87	VS063998	0.168	24.3	0.16	4.83
1050.26	1051.23	0.97	VS063999	0.116	15.1	0.15	3.23
1051.23	1052.3	1.07	VS064000	0.053	9.67	0.05	3.19
1052.3	1053.37	1.07	VS064001	0.028	10.4	0.04	2.94
1053.37	1054.4	1.03	VS064002	0.016	11.3	0.005	3.11
1054.4	1055.46	1.06	VS064004	0.032	11.95	0.03	3.09
1055.46	1056.58	1.12	VS064005	0.031	11.45	0.03	3.18
1056.58	1057.65	1.07	VS064006	0.009	9.53	0.02	3.13
1057.65	1058.67	1.02	VS064007	0.032	10.2	0.05	3.08
1058.67	1059.8	1.13	VS064008	0.055	10.45	0.07	3.05
1059.8	1060.9	1.1	VS064009	0.01	12.05	0.05	3.31
1060.9	1062.03	1.13	VS064010	0.656	19.35	0.87	3.65
1062.03	1062.99	0.96	VS064012	0.16	11.45	0.23	3.28
1062.99	1063.95	0.96	VS064013	0.043	10.2	0.07	2.85
1063.95	1064.9	0.95	VS064014	0.053	11.75	0.05	3.02
1064.9	1065.97	1.07	VS064015	0.02	10.5	0.03	3.14
1065.97	1067.03	1.06	VS064016	0.019	9.94	0.03	2.9
1067.03	1068.1	1.07	VS064017	0.07	11.7	0.06	3.29
1068.1	1069.22	1.12	VS064019	0.027	11.4	0.03	3.18
1069.22	1070.24	1.02	VS064020	0.01	10.6	0.02	3.54
1070.24	1071.34	1.1	VS064021	0.059	11.7	0.05	3.12
1071.34	1072.38	1.04	VS064022	0.02	11.55	0.03	2.95
1072.38	1073.47	1.09	VS064023	0.034	9.94	0.06	2.83
1073.47	1074.49	1.02	VS064024	0.498	20.2	0.73	3.31
1074.49	1075.58	1.09	VS064026	0.106	12.1	0.15	3.01
1075.58	1076.65	1.07	VS064027	0.011	10.7	0.02	3.08
1076.65	1077.68	1.03	VS064028	0.154	12.2	0.14	3.32
1077.68	1078.7	1.02	VS064029	0.032	11.05	0.02	3.06
1078.7	1079.77	1.07	VS064030	0.007	10.4	0.02	3.06
1079.77	1080.88	1.11	VS064031	0.016	11.25	0.02	3.06
1080.88	1081.85	0.97	VS064032	0.02	10.95	0.03	2.97
1081.85	1082.96	1.11	VS064033	0.008	10.9	0.005	2.97

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1082.96	1083.96	1	VS064034	0.014	8.89	0.02	2.88
1083.96	1085	1.04	VS064036	0.048	10.3	0.08	2.98
1085	1086.07	1.07	VS064037	0.354	10.4	0.59	2.98
1086.07	1087.1	1.03	VS064038	0.076	10.55	0.14	2.98
1087.1	1088.12	1.02	VS064039	0.042	9.66	0.07	2.98
1088.12	1089.19	1.07	VS064040	0.036	11.1	0.05	3.08
1089.19	1090.26	1.07	VS064041	0.39	13.05	0.77	3.12
1090.26	1090.95	0.69	VS064043	0.869	58.9	1.77	4.51
1090.95	1091.91	0.96	VS064044	0.613	12.5	1.18	3.44
1091.91	1092.88	0.97	VS064045	0.045	9.4	0.09	2.99
1092.88	1093.84	0.96	VS064046	0.077	10.35	0.06	2.96
1093.84	1094.9	1.06	VS064047	0.064	10.3	0.04	3.15
1094.9	1097	2.1	VS065045	0.08	9.08	0.09	2.95
1097	1099.07	2.07	VS065046	0.044	10.15	0.04	2.98
1099.07	1099.95	0.88	VS065047	0.295	10.8	0.19	2.98
1099.95	1101.12	1.17	VS065048	0.045	9.5	0.04	3
1101.12	1103.9	2.78	VS065049	0.084	11.65	0.1	2.96
1103.9	1106.1	2.2	VS065050	0.058	10.65	0.14	2.96
1106.1	1108.45	2.35	VS065051	0.299	11.25	0.56	2.96
1108.45	1111	2.55	VS065052	0.077	11.75	0.22	2.96
1111	1114	3	VS065053	0.038	10.2	0.07	2.96
1114	1117	3	VS065054	0.016	10.7	0.06	2.92
1117	1120	3	VS065055	0.032	11.45	0.11	2.91
1120	1123	3	VS065057	0.053	12.35	0.13	2.95
1123	1125	2	VS065058	0.051	12.05	0.12	2.95
1125	1127.35	2.35	VS065059	0.032	10.45	0.08	2.95
1127.35	1130	2.65	VS065060	0.029	10.65	0.06	2.99
1130	1133	3	VS065061	0.015	10.8	0.02	3
1133	1136	3	VS065062	0.004	11.55	0.005	3
1136	1139	3	VS065063	0.003	11.35	0.005	3.02
1139	1142	3	VS065064	0.017	8.98	0.05	3.01
1142	1145	3	VS065065	0.027	10.95	0.09	3.01
1145	1148	3	VS065066	0.013	9.61	0.02	3.01
1148	1150.85	2.85	VS065068	0.015	9.94	0.02	2.99
1150.85	1153	2.15	VS065069	0.03	11.55	0.09	3.04
1153	1156	3	VS065070	0.016	10.65	0.04	3.04
1156	1159	3	VS065071	0.072	11	0.17	3.04
1159	1162	3	VS065072	0.078	11.7	0.23	3.09
1162	1164.85	2.85	VS065073	0.022	9.87	0.04	3.05
1164.85	1166	1.15	VS065074	0.288	11.65	0.62	3.05
1166	1169	3	VS065075	0.029	11.4	0.08	3.05
1169	1172	3	VS065076	0.022	11.65	0.06	3
1172	1173.6	1.6	VS065077	0.012	11.95	0.05	3
1173.6	1175.65	2.05	VS065078	0.099	12.35	0.3	3
1175.65	1178.35	2.7	VS065127	0.022	12.9	0.03	3
1178.35	1181.21	2.86	VS065128	0.011	11.9	0.02	3
1181.21	1184.18	2.97	VS065129	0.008	10.9	0.02	3

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1184.18	1187.1	2.92	VS065130	0.042	10.45	0.11	3
1187.1	1189.67	2.57	VS065131	0.071	10.05	0.2	3
1189.67	1191.2	1.53	VS065132	0.008	11.25	0.02	3
1191.2	1192.55	1.35	VS065133	0.178	9.35	0.63	3
1192.55	1195.53	2.98	VS065135	0.003	10.4	0.005	3
1195.53	1198.42	2.89	VS065136	0.24	11.15	0.84	3
1198.42	1200	1.58	VS065137	0.025	10.35	0.05	3
1200	1201.52	1.52	VS065138	0.009	11.3	0.03	3
1201.52	1203.55	2.03	VS065139	0.012	11.15	0.05	3
1203.55	1204.97	1.42	VS065140	0.033	10.5	0.07	3
1204.97	1206.46	1.49	VS065141	0.002	10.6	0.005	3
1206.46	1208.11	1.65	VS065142	0.001	10.75	0.005	3
1208.11	1209.58	1.47	VS065143	0.001	10.8	0.005	3
1209.58	1210.8	1.22	VS065145	0.006	10.05	0.02	3
1210.8	1213.7	2.9	VS065146	0.003	10.75	0.005	3
1213.7	1216.54	2.84	VS065147	0.008	10.7	0.04	3
1216.54	1219.25	2.71	VS065148	0.001	10.05	0.005	3
1219.25	1222.05	2.8	VS065149	0.014	11.55	0.05	3
1222.05	1223.85	1.8	VS065150	0.007	11.45	0.02	3
1223.85	1225.13	1.28	VS065151	0.062	12.65	0.2	3
1225.13	1227.5	2.37	VS065152	0.148	13.75	0.32	3
1227.5	1230.48	2.98	VS065153	0.01	13.25	0.03	3
1230.48	1232	1.52	VS065154	0.01	14.95	0.05	3
1232	1233.53	1.53	VS065156	0.003	15.3	0.005	3
1233.53	1236.35	2.82	VS065157	0.016	15.15	0.04	3
1236.35	1237.65	1.3	VS065158	0.004	15.5	0.005	3
1237.65	1239.32	1.67	VS065159	0.022	12.7	0.07	3
1239.32	1241	1.68	VS065160	0.008	12.75	0.02	3
1241	1241.94	0.94	VS065162	0.122	10.85	0.31	3
1241.94	1243.44	1.5	VS065163	0.026	14.7	0.09	3
1243.44	1245.02	1.58	VS065164	0.013	14.9	0.03	3
1245.02	1246.8	1.78	VS065165	0.034	13.95	0.07	3
1246.8	1249.61	2.81	VS065166	0.012	14.95	0.03	3
1249.61	1251.98	2.37	VS065167	0.013	15.05	0.02	3
1251.98	1254.65	2.67	VS065168	0.043	14.05	0.08	3
1254.65	1257.39	2.74	VS065169	0.047	13.9	0.1	3
1257.39	1259.5	2.11	VS065170	0.056	13.6	0.13	3
1259.5	1262.2	2.7	VS065171	0.201	14.85	0.42	3
1262.2	1265.15	2.95	VS065924	0.095	15.6	0.17	3
1265.15	1268.1	2.95	VS065925	0.018	14.55	0.07	3.02
1268.1	1271	2.9	VS065926	0.086	13.45	0.12	3.04
1271	1272.44	1.44	VS065927	0.029	14.3	0.05	3.04
1272.44	1274	1.56	VS065928	0.006	13.25	0.005	3.04
1274	1275.05	1.05	VS065929	0.073	11.4	0.13	3.06
1275.05	1276.35	1.3	VS065930	0.088	9.41	0.15	2.98
1276.35	1277.62	1.27	VS065931	0.078	11.15	0.09	2.96
1277.62	1278.92	1.3	VS065932	0.009	11.2	0.02	3.1

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1278.92	1280.22	1.3	VS065933	0.008	10.85	0.02	3.01
1280.22	1281.41	1.19	VS065935	0.011	10.6	0.03	2.97
1281.41	1282.65	1.24	VS065936	0.001	10.55	0.005	2.97
1282.65	1283.4	0.75	VS065937	0.011	10.4	0.03	2.96
1283.4	1284.65	1.25	VS065938	0.003	10.3	0.02	3.1
1284.65	1285.73	1.08	VS065939	0.105	10.6	0.14	3.06
1285.73	1286.9	1.17	VS065940	0.078	12	0.13	3.29
1286.9	1287.9	1	VS065941	0.601	44.5	0.59	3.97
1287.9	1288.9	1	VS065942	0.682	35.9	0.78	3.86
1288.9	1289.9	1	VS065943	0.641	12.6	0.69	3.12
1289.9	1290.9	1	VS065944	1.64	11.6	1.88	3.08
1290.9	1291.9	1	VS065946	0.55	9.54	0.82	2.97
1291.9	1292.78	0.88	VS065947	0.987	11.95	1.27	2.98
1292.78	1293.66	0.88	VS065948	0.911	11.6	1.02	3.15
1293.66	1294.31	0.65	VS065949	0.492	11	0.49	2.98
1294.31	1294.8	0.49	VS065950	0.539	9.74	1.54	2.92
1294.8	1295.78	0.98	VS065951	1.34	11.6	1.64	2.99
1295.78	1296.44	0.66	VS065952	0.622	11.4	0.84	3.12
1296.44	1297.22	0.78	VS065953	0.796	10.55	0.89	3.11
1297.22	1298	0.78	VS065954	1.675	9.59	1.89	2.92
1298	1299.21	1.21	VS065955	0.406	9.17	0.45	2.92
1299.21	1300.41	1.2	VS065957	0.204	9.55	0.19	2.97
1300.41	1301.5	1.09	VS065958	0.525	9.91	0.59	3.08
1301.5	1302.16	0.66	VS065959	1.88	10.1	2.13	2.96
1302.16	1302.9	0.74	VS065960	0.615	8.24	0.65	3
1302.9	1303.91	1.01	VS065961	0.158	8.26	0.19	2.98
1303.91	1304.9	0.99	VS065962	0.309	8.33	0.32	2.89
1304.9	1305.88	0.98	VS065963	0.274	8.21	0.36	3.07
1305.88	1307	1.12	VS065964	0.752	9.69	0.69	3.05
1307	1308	1	VS065965	1.275	13.4	1.15	3.11
1308	1308.77	0.77	VS065966	1.035	14	1.03	3.28
1308.77	1309.5	0.73	VS065968	1.42	14.9	1.5	3.13
1309.5	1310.23	0.73	VS065969	1.445	12.85	1.64	3.24
1310.23	1311	0.77	VS065970	0.426	12	0.46	3.47
1311	1311.7	0.7	VS065971	2.02	13.05	2.15	2.94
1311.7	1312.65	0.95	VS065972	0.193	6.86	0.19	2.98
1312.65	1313	0.35	VS065973	1.69	8.81	1.92	3.54
1313	1313.35	0.35	VS065974	4.28	16.25	4.49	2.96
1313.35	1314.29	0.94	VS065975	0.947	10.1	0.98	2.94
1314.29	1315.15	0.86	VS065976	0.365	8.45	0.38	3.24
1315.15	1315.96	0.81	VS065977	0.097	7.59	0.13	2.99
1315.96	1316.65	0.69	VS065979	0.07	7.15	0.08	3.06
1316.65	1317.25	0.6	VS065980	0.744	6.34	0.66	2.98
1317.25	1318	0.75	VS065981	0.415	8.09	0.47	3.02
1318	1318.73	0.73	VS065982	1.82	8.19	1.89	3.33
1318.73	1319.4	0.67	VS065983	2.35	11.65	2.39	3.11
1319.4	1319.96	0.56	VS065984	1.455	6.88	1.57	3.02

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1319.96	1320.4	0.44	VS065985	1.59	11.5	1.64	2.96
1320.4	1321.2	0.8	VS065986	2.3	8.63	2.62	2.97
1321.2	1322.1	0.9	VS065987	0.984	7.5	1.08	2.91
1322.1	1322.6	0.5	VS065988	0.264	5.25	0.31	2.76
1322.6	1323.45	0.85	VS065990	0.916	6.2	1.08	3.11
1323.45	1324.34	0.89	VS065991	1.43	7.14	1.64	2.84
1324.34	1325.11	0.77	VS065992	0.84	5.83	0.92	3.24
1325.11	1325.96	0.85	VS065993	1.92	8.35	2.3	2.96
1325.96	1326.8	0.84	VS065994	2.65	8.93	3.22	3.03
1326.8	1327.56	0.76	VS065995	1.78	8.1	2.08	2.91
1327.56	1328.33	0.77	VS065996	1.345	7.66	1.65	3.03
1328.33	1329.2	0.87	VS065997	0.425	6.29	0.53	3.16
1329.2	1329.79	0.59	VS065998	0.875	14.15	0.85	3.6
1329.79	1330.36	0.57	VS066000	0.659	17.55	0.78	3.04
1330.36	1330.95	0.59	VS066001	0.938	13.7	1.22	2.92
1330.95	1332.2	1.25	VS066002	0.088	5.51	0.11	2.68
1332.2	1333.12	0.92	VS066003	0.044	4.49	0.03	3.03
1333.12	1334.35	1.23	VS066004	0.066	4.3	0.06	2.71
1334.35	1335.55	1.2	VS066005	0.005	3.02	0.02	2.93
1335.55	1336.67	1.12	VS066006	0.066	5.77	0.11	2.76
1336.67	1337.76	1.09	VS066007	0.052	5.13	0.04	3.06
1337.76	1338.95	1.19	VS066008	0.021	5.3	0.03	2.81
1338.95	1339.82	0.87	VS066009	0.006	4.06	0.03	2.73
1339.82	1341	1.18	VS066563	0.025	5.2	0.15	2.69
1341	1342.3	1.3	VS066564	0.07	6.04	0.22	2.6
1342.3	1343.6	1.3	VS066565	0.013	3.61	0.05	2.66
1343.6	1344.9	1.3	VS066566	0.01	3.6	0.03	2.66
1344.9	1346	1.1	VS066567	0.113	6.43	0.3	2.63
1346	1346.65	0.65	VS066568	0.048	4.95	0.13	2.6
1346.65	1347.5	0.85	VS066569	0.035	4.4	0.05	2.7
1347.5	1348.7	1.2	VS066570	0.013	3.84	0.02	2.73
1348.7	1349.8	1.1	VS066571	0.003	3.88	0.005	3.96
1349.8	1350.55	0.75	VS066573	0.023	4.2	0.03	2.69
1350.55	1351.1	0.55	VS066574	0.052	3.83	0.03	2.72
1351.1	1352.1	1	VS066575	0.039	3.86	0.04	2.77
1352.1	1353.4	1.3	VS066576	0.011	2.77	0.02	2.71
1353.4	1354.3	0.9	VS066577	0.007	2.39	0.005	2.69
1354.3	1355.15	0.85	VS066578	0.001	2.22	0.005	2.71
1355.15	1356.15	1	VS066579	0.003	2.23	0.005	2.75
1356.15	1357.25	1.1	VS066580	0.003	2.02	0.005	2.72
1357.25	1358.1	0.85	VS066581	0.001	2.83	0.005	2.73
1358.1	1359.05	0.95	VS066582	0.006	3.92	0.03	2.74
1359.05	1359.55	0.5	VS066584	0.265	36.9	0.66	3.83
1359.55	1360.15	0.6	VS066585	0.411	8.01	0.21	2.92
1360.15	1360.9	0.75	VS066586	0.092	4.43	0.08	2.71
1360.9	1362.05	1.15	VS066587	0.138	3.89	0.12	2.81
1362.05	1363.25	1.2	VS066588	0.071	1.34	0.04	2.67

HOLE ID: VDD24115B							
DEPTH_FROM	DEPTH_TO	SAMPLE_LENGTH	SAMPLE_ID	CU_PCT	FE_PCT	AG_PPM	DENSITY
1363.25	1364.2	0.95	VS066589	0.052	1.08	0.07	2.7
1364.2	1365	0.8	VS066590	0.356	1.7	0.31	2.71
1365	1366	1	VS066591	0.337	1.8	0.22	2.7
1366	1367.3	1.3	VS066592	0.287	1.82	0.29	2.72
1367.3	1368.5	1.2	VS066593	0.254	4.53	0.28	2.78
1368.5	1369.25	0.75	VS066594	0.18	9.9	0.14	2.99
1369.25	1370.1	0.85	VS066596	0.136	3.69	0.1	2.75
1370.1	1371.05	0.95	VS066597	0.019	2.68	0.005	2.74
1371.05	1372	0.95	VS066598	0.052	2.64	0.04	2.73
1372	1373.15	1.15	VS066599	0.099	2.39	0.06	2.69
1373.15	1374.35	1.2	VS066600	0.097	2.99	0.07	2.71
1374.35	1374.95	0.6	VS066601	0.02	3	0.03	2.67
1374.95	1375.85	0.9	VS066602	0.073	2.94	0.13	2.66
1375.85	1376.75	0.9	VS066603	0.104	3.47	0.07	2.7
1376.75	1377.7	0.95	VS066604	0.029	2.91	0.02	2.7
1377.7	1378.25	0.55	VS066605	0.011	3.91	0.08	2.62
1378.25	1379.5	1.25	VS066607	0.033	10.4	0.04	3
1379.5	1380.3	0.8	VS066608	0.03	10.6	0.03	2.96
1380.3	1381.2	0.9	VS066609	0.005	11.1	0.005	3.01
1381.2	1382.1	0.9	VS066610	0.013	10.95	0.005	2.99
1382.1	1382.85	0.75	VS066611	0.033	11.4	0.02	2.85
1382.85	1383.5	0.65	VS066612	0.04	10.3	0.04	3.01
1383.5	1384.8	1.3	VS066613	0.026	10.8	0.04	3
1384.8	1385.6	0.8	VS066614	0.055	11.05	0.08	3.06
1385.6	1386	0.4	VS066615	0.048	11.5	0.03	3.02
1386	1386.9	0.9	VS066617	0.029	11	0.03	3.04
1386.9	1387.8	0.9	VS066618	0.056	11.2	0.05	3.03
1387.8	1388.5	0.7	VS066619	0.157	11.4	0.09	3.05
1388.5	1389.35	0.85	VS066620	0.022	10.3	0.02	2.98
1389.35	1390.3	0.95	VS066621	0.012	10.55	0.02	3.02
1390.3	1391.25	0.95	VS066622	0.022	11	0.02	3.06
1391.25	1392	0.75	VS066623	0.023	10.6	0.02	2.98

APPENDIX 3: REFERENCES

Imana M., Armstrong R., Sandoval D., Jez M., Nkioh E., and Kroeckert M. 2023. "A geological update on the Viscaria Cu-Fe deposit, Kiruna District, Northern Sweden." *SGA 17th Biennial Meeting Proceedings* 1: 363-365.

Tasbicen K., Imaña M., Chávez W.X. Jr. 2023. "Sulfide Mineralogy and Cobalt Department at the Viscaria Cu-Fe Deposit, Kiruna District, Northern Sweden." *Poster presented at SEG 2023 Conference: Resourcing the Green Transition*.

Viscaria Kiruna AB. 2025a. "VISCARIA FS Report Executive Summary." Retrieved from <https://www.viscaria.com/en/wp-content/uploads/sites/2/2021/10/viscaria-fs-report-executive-summary-250508-250508.pdf>

Viscaria Kiruna AB. 2025b. "PERC Table 1 Viscaria Resource and Reserves." Retrieved from https://www.viscaria.com/en/wp-content/uploads/sites/2/2021/10/table1-perc-may_2025-250521.pdf

APPENDIX 4: CERTIFICATE OF COMPETENT PERSON

As the Competent Person responsible for the information on which the Public Report entitled "Viscaria Exploration Results, Q3, 2025" is based, I hereby state:

1. My name is Thomas Lindholm.
2. I am a senior associate of GeoVista AB, Luleå, Sweden.
3. I am a Mining Engineer, member of the Fennoscandian Association of Metals and Mining Professionals, FAMMP as well as a Fellow of AusIMM (#230476).
4. I graduated with a M.Sc. in mining engineering from the University of Luleå in 1982 and have since worked in exploration and mine development projects in Sweden and abroad.
5. I have participated in or led several feasibility studies for various types of gold, base metal and iron deposits.
6. I meet the requirements of a 'Competent Person' as defined explicitly in the PERC Reporting Standard.
7. The CP has visited the site several times, lastly in October 2025, to discuss the feasibility study with the local geologists and engineers.
8. The CP is responsible for the overall review of the entire report.
9. I am not aware of any material fact or material change concerning the subject matter of the Public Report that is not reflected in the Public Report, the omission of which would make the Public Report misleading.
10. I declare that this Public Report appropriately reflects the Competent Person's view.
11. I am independent of Gruvaktiebolaget Viscaria.
12. I confirm that I have read all the relevant sections of the PERC Reporting Standard 2021. The Public Report has been prepared under the requirements of the PERC Reporting Standard.
13. I do not have, nor do I expect to receive, a direct or indirect interest in the Viscaria mine of Gruvaktiebolaget Viscaria.
14. I have no conflicts of interest in respect of the reporting entity/issuer Gruvaktiebolaget Viscaria or the Viscaria Mine.
15. At the effective date of the Public Report, to the best of my knowledge, information and belief, the Public Report contains all scientific and technical information required to be disclosed in order to make the Public Report not misleading.

Dated at Luleå, Sweden and 2026-05-07.



Thomas Lindholm, member of FAMMP, Fellow AusIMM (#230476)